



## Standard Guide for Measurement of Thin Chromium Coatings by Spot Test<sup>1</sup>

This standard is issued under the fixed designation B 556; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon ( $\epsilon$ ) indicates an editorial change since the last revision or reapproval.

### 1. Scope

1.1 This guide covers the use of the spot test for the measurement of thicknesses of electrodeposited chromium coatings over nickel and stainless steel with an accuracy of about  $\pm 20\%$  (Section 9). It is applicable to thicknesses up to  $1.2\ \mu\text{m}$ .<sup>2</sup>

NOTE 1—Although this test can be used for coating thicknesses up to  $1.2\ \mu\text{m}$ , there is evidence that the results obtained by this method are high at thicknesses greater than  $0.5\ \mu\text{m}$ .<sup>3</sup> In addition, for coating thicknesses above  $0.5\ \mu\text{m}$ , it is advisable to use a double drop of acid to prevent depletion of the test solution before completion of the test.

1.2 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.*

### 2. Referenced Documents

#### 2.1 ASTM Standards:

B 504 Test Method for Measurement of Thickness of Metallic Coatings by the Coulometric Method<sup>4</sup>

B 568 Test Method for Measurement of Coating Thickness by X-Ray Spectrometry<sup>4</sup>

B 588 Test Method for Measurement of Thickness of Transparent or Opaque Coatings by Double-Beam Interference Microscope Technique<sup>4</sup>

### 3. Summary of Guide

3.1 A drop of hydrochloric acid (test solution) is deposited on the surface of the test specimen, and the time required for the hydrochloric acid to penetrate through the chromium coating (penetration time) is measured. The coating thickness is proportional to this time.

<sup>1</sup> This guide is under the jurisdiction of ASTM Committee B08 on Metallic and Inorganic Coatings and is the direct responsibility of Subcommittee B08.10 on General Test Methods.

Current edition approved Feb. 23, 1990. Published April 1990. Originally published as B 556 – 71. Last previous edition B 556 – 84.

<sup>2</sup> Blum, W., and Olson, W. A., *Proceedings*, Am. Electroplaters Soc., Vol 28, 1940, p. 25.

<sup>3</sup> DuRose, A. H., and Pierce, W. J., *Metal Finishing*, Vol 57, March 1959, p. 54.

<sup>4</sup> *Annual Book of ASTM Standards*, Vol 02.05.

### 4. Significance and Use

4.1 The thickness of a decorative chromium coating is often critical to its performance.

4.2 This procedure is useful for an approximate determination when the best possible accuracy is not required. For more reliable determinations, the following methods are available: Methods B 504, B 568, and B 588.

4.3 This test assumes that the rate of dissolution of the chromium by the hydrochloric acid under the specified conditions is always the same.

### 5. Test Solutions

5.1 For chromium on nickel the test solution is reagent grade hydrochloric acid having a specific gravity at  $16^\circ\text{C}$  of  $1.180 \pm 0.002$ . (This corresponds to  $11.5\ N \pm 0.2\ N$ , which may be checked by titration.) For chromium on stainless steel the test solution is 20 g/L of antimony trioxide dissolved in reagent grade hydrochloric acid having a specific gravity at  $16^\circ\text{C}$  of 1.160.

NOTE 2—As received, reagent grade hydrochloric acid is normally more concentrated than  $11.5\ N$ .

### 6. Preparation of Test Area

6.1 The test area must be free of foreign material. Clean by rubbing the test area with a paste of magnesium oxide, rinse it, and dry it with a clean cloth or filter paper. Draw a ring with a diameter of about 6 mm on the test area with melted paraffin or with a wax pencil.

### 7. Procedure

7.1 Let the test specimen, the test solution, and the dropper stand long enough to reach room temperature, which should be between  $16$  and  $25^\circ\text{C}$ . Temperatures up to  $30^\circ\text{C}$  are permissible, but the measurements become less reliable at the higher temperatures because of increasing sensitivity to temperature. Thin test specimens should be set on a heavy metal plate to avoid a rapid change in temperature which could be produced in such specimens by the heat of reaction.

7.2 To determine the penetration time,  $t$ , deposit a drop ( $0.03$  to  $0.05\ \text{mL}$ ) of the test solution inside the ring of wax, and measure the time between the beginning of the gas formation and the first appearance of nickel. Make this

measurement to the nearest ½ s with a stop watch. If the reaction, that is, the formation of gas bubbles, does not start immediately, it can be started by touching the test surface within the ring with a fine nickel wire. The end point of the penetration is characterized by the cessation of the gassing and the appearance of the yellow color of the nickel surface. There may be an uncertainty of 2 or 3 s in determining when the end point has been reached.

7.3 If the basis metal is 18-8 stainless steel, gassing will stop at the end point; if it is 17 % chromium stainless steel, the rate of gas liberation will decrease when the end point is reached.

7.4 When using the antimony trioxide-hydrochloric acid solution, the absence of a black film will indicate that there is no chromium deposit; if a black film forms, but if there is little or no gassing, the chromium is estimated to be less than 0.1 μm thick.

7.5 Measure the room temperature near the test area to an accuracy of 0.2°C.

**8. Calculation of Thickness**

8.1 Calculate the thickness of the chromium coating by the equation:

$$\text{Thickness} = ut \tag{1}$$

where:

- t* = penetration time, and
- u* = speed of dissolution of the chromium coating as a function of the test temperature (see Fig. 1).

NOTE 3—Fig. 1 is applicable when chromium plate is deposited from the conventional sulfate chromic acid solution under conventional operating conditions. If these procedures are varied, it may be necessary to restandardize the test.

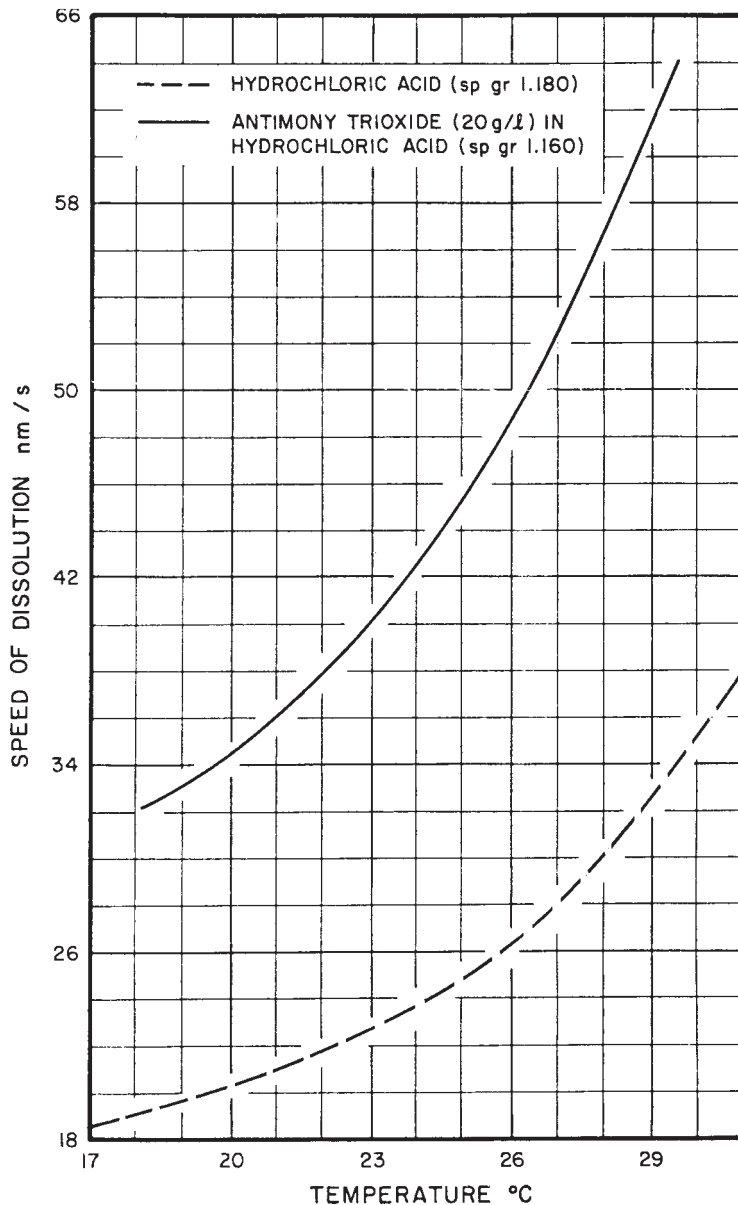


FIG. 1 Temperature Factor for Hydrochloric Acid (sp gr 1.180) and Antimony Trioxide (20 g/L) in Hydrochloric Acid (sp gr 1.160)

8.2 In case of duplex chromium coatings, the thickness will correspond to the combined thickness of the two coatings. metric method covered by Method B 504.

## **9. Precision and Bias**

9.1 This thickness determination has an uncertainty of about  $\pm 20\%$ , and is, therefore, much less accurate than the coulo-

*ASTM International takes no position respecting the validity of any patent rights asserted in connection with any item mentioned in this standard. Users of this standard are expressly advised that determination of the validity of any such patent rights, and the risk of infringement of such rights, are entirely their own responsibility.*

*This standard is subject to revision at any time by the responsible technical committee and must be reviewed every five years and if not revised, either reapproved or withdrawn. Your comments are invited either for revision of this standard or for additional standards and should be addressed to ASTM International Headquarters. Your comments will receive careful consideration at a meeting of the responsible technical committee, which you may attend. If you feel that your comments have not received a fair hearing you should make your views known to the ASTM Committee on Standards, at the address shown below.*

*This standard is copyrighted by ASTM International, 100 Barr Harbor Drive, PO Box C700, West Conshohocken, PA 19428-2959, United States. Individual reprints (single or multiple copies) of this standard may be obtained by contacting ASTM at the above address or at 610-832-9585 (phone), 610-832-9555 (fax), or [service@astm.org](mailto:service@astm.org) (e-mail); or through the ASTM website ([www.astm.org](http://www.astm.org)).*