



Designation: E 426 – 98

## Standard Practice for Electromagnetic (Eddy-Current) Examination of Seamless and Welded Tubular Products, Austenitic Stainless Steel and Similar Alloys<sup>1</sup>

This standard is issued under the fixed designation E 426; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon ( $\epsilon$ ) indicates an editorial change since the last revision or reapproval.

*This specification has been approved for use by agencies of the Department of Defense.*

### 1. Scope

1.1 This practice<sup>2</sup> covers procedures that may be followed for eddy-current examination of seamless and welded tubular products made of stainless steel and similar alloys such as nickel alloys. Austenitic chromium-nickel stainless steels, which are generally considered to be nonmagnetic, are specifically covered as distinguished from the martensitic and ferritic straight chromium stainless steels which are magnetic.

1.2 This practice is intended as a guide for eddy-current examination both seamless and welded tubular products using either an encircling coil or a probe-coil technique. Coils and probes are available that can be used inside the tubular product; however, their use is not specifically covered in this document. This type of examination is usually employed only to examine tubing which has been installed such as in a heat exchanger.

1.3 This practice covers the examination of tubular products ranging in diameter from 0.125 to 5 in. (3.2 to 127.0 mm) and wall thicknesses from 0.005 to 0.250 in. (0.127 to 6.4 mm).

1.4 The values stated in inch-pound units are to be regarded as the standard.

1.5 *This standard does not purport to address all of the safety problems, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.*

### 2. Referenced Documents

#### 2.1 ASTM Standards:

E 543 Practice for Agencies Perform Nondestructive Testing<sup>3</sup>

E 1316 Terminology for Nondestructive Testing<sup>3</sup>

#### 2.2 Other Documents:

SNT-TC-1A Recommended Practice for Personnel Qualification and Certification in Nondestructive Testing<sup>4</sup>

ANSI/ASNT CP-189 ASNT Standard for Qualification and Certification of Nondestructive Testing Personnel<sup>4</sup>

MII-STD-410E Nondestructive Testing Personnel Qualification and Certification<sup>5</sup>

NAS-410 NAS Certification and Qualification of Nondestructive Personnel (Quality Assurance Committee)<sup>6</sup>

### 3. Terminology

3.1 Standard terminology relating to electromagnetic examination may be found in Terminology E 1316, Section C, Electromagnetic Testing.

### 4. Summary of Practice

4.1 The test is conducted using one of two general techniques shown in Fig. 1. One of these techniques employs one or more exciter and sensor coils which encircle the pipe or tube and through which the tubular product to be inspected is passed. Some circuit configurations employ separate exciter and sensor coils; whereas other configurations employ one or more coils that concurrently function as both exciters and sensors. Alternating current passes through the exciting coil which by reason of its proximity induces current in the tubular product. The sensor coil detects the resultant electromagnetic flux related to these currents. The presence of discontinuities in the tubular product will affect the normal flow of currents and this change is detected by the sensor. The encircling coil technique is capable of inspecting the entire 360-deg expanse of the tubular product.

4.2 Another technique employs a probe coil with one or more exciters and sensors which is brought in close proximity of the surface of the tubular product to be examined. Since the

<sup>1</sup> This practice is under the jurisdiction of ASTM Committee E-7 on Nondestructive Testing and is the direct responsibility of Subcommittee E07.07 on Electromagnetic Methods.

Current edition approved Dec. 10, 1998. Published February 1999. Originally published as E 426 – 71. Last previous edition E 426 – 92.


<sup>2</sup> For ASME Boiler and Pressure Vessel Code applications see related Practice SE-426 in Section II of that Code.

<sup>3</sup> *Annual Book of ASTM Standards*, Vol 03.03.

<sup>4</sup> Available from American Society for Nondestructive Testing, 1711 Arlington Plaza, P.O. Box 28518, Columbus, OH 43228-0518.

<sup>5</sup> Available from Standardization Documents Order Desk, Bldg. 4, Section D, 700 Robbins Ave., Phila., PA 19111-5904, Attn: NPODS.

<sup>6</sup> Available from Aerospace Industries Association of America, Inc., 1250 Eye Street, N.W., Washington, DC 20005.

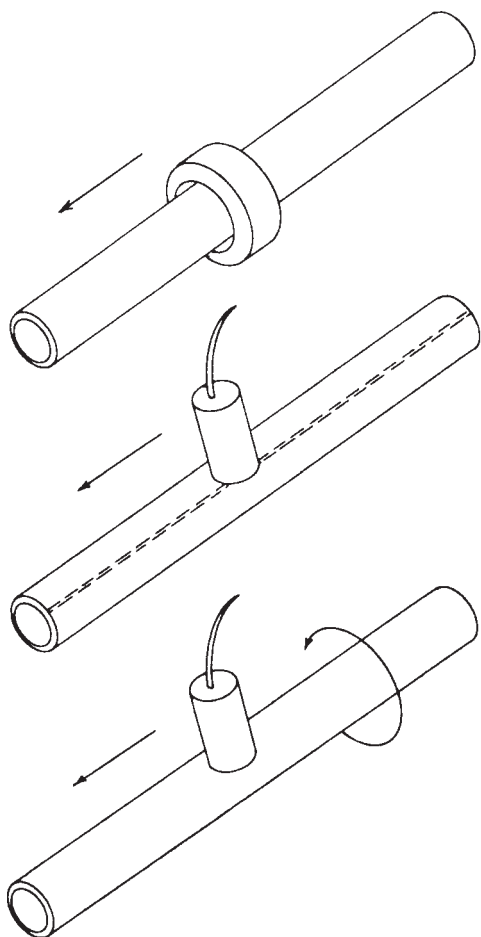

**FIG. 1 Sketch Showing Encircling-Coil and Probe-Coil Techniques for Electromagnetic Examining of Tubular Products**

probe is generally small and does not encircle the article being examined, it examines only a limited area in the vicinity of the probe. If it is desired to examine the entire volume of the tubular product, it is common practice to either rotate the tubular product or the probe. In the case of welded tubular products frequently only the weld is examined by scanning along the weld zone.

## 5. Significance and Use

5.1 Eddy-current testing is a nondestructive method of locating discontinuities in a product. Changes in electromagnetic response caused by the presence of discontinuities are detected by the sensor, amplified and modified in order to actuate audio or visual indicating devices, or both, or a mechanical marker. Signals can be caused by outer surface, inner surface, or subsurface discontinuities. The eddy-current test is sensitive to many factors that occur as a result of processing (such as variations in conductivity, chemical composition, permeability, and geometry) as well as other test factors not related to the tubing. Thus, all received indications are not necessarily indicative of defective tubing.

## 6. Basis of Application

6.1 If specified in the contractual agreement, personnel performing examinations to this practice shall be qualified in

accordance with a nationally recognized NDT personnel qualification practice or standard such as ANSI/ASNT-CP-189, SNT-TC-1A, MIL-STD-410E, NAS-410, ASNT-ACCP, or a similar document and certified by the certifying agency, as applicable. The practice or standard used and its applicable revision shall be identified in the contractual agreement between the using parties.

NOTE 1—MIL-STD-410 is canceled and has been replaced with NAS-410, however, it may be used with agreement between contracting parties.

6.2 If specified in the contractual agreement, NDT agencies shall be qualified and evaluated in accordance with Practice E 543. The applicable edition of Practice E 543 shall be specified in the contractual agreement.

## 7. Apparatus

7.1 *Electronic Apparatus*—The electronic apparatus shall be capable of energizing the test coils or probes with alternating currents of suitable frequencies and shall be capable of sensing the changes in the electromagnetic response of the sensors. Equipment may include a detector, phase discriminator, filter circuits, modulation circuits, magnetic-saturation devices, recorders, and signaling devices as required for the particular application.

7.2 *Test Coils*—Test coils shall be capable of inducing current in the tube and sensing changes in the electrical characteristics of the tube.

NOTE 2—Fill factor effect is an important consideration since coupling variations can affect the test significantly.

7.3 *Probe Coils*—Probe coils shall be capable of inducing current in the tube and sensing changes in the electrical characteristics of the tube (Note 3). Probes generally consist of an exciting coil and sensing coil or Hall element mounted in a common holder. A Hall element is a semiconductor that by reason of the Hall effect is capable of responding in a manner directly proportional to magnetic-flux density. However, when used with an exciting coil, it should be remembered that eddy-current flow is influenced by the excitation frequency.

NOTE 3—Lift-off effect is an important consideration since coupling variations can affect the test significantly.

7.4 *Driving Mechanism*—A mechanical device capable of passing the tube through the test coil or past the probe. It shall operate at a uniform speed with minimum vibration of coil, probe, or tube and maintain the article being examined in proper register or concentricity with the probe or test coil. Where required, the mechanism shall be capable of uniformly rotating the tube or probe.

7.5 *Reference Standard*—The standard used to adjust the sensitivity setting of the apparatus shall be sound and of the same nominal alloy, temper, and nominal dimensions as the lot of tubes or pipes to be tested on a production basis. It shall be of sufficient length to permit the required spacing of the artificial discontinuities (at least 4 ft, and preferably longer). Artificial discontinuities made in the tube or pipe shall be centered as nearly as possible on one inside or outside diameter surface of the tube and shall preferably be of one of the following types:

7.5.1 *Holes*—Holes that are usually drilled completely through the wall may be used. Care should be taken during drilling to avoid distortion of the tube (or pipe) and hole.

7.5.2 *Notches*—Notches may be produced by electric discharge machining (EDM), milling, or other means. Longitudinal or transverse notches or both may be used (Note 4). Orientation, dimensions (width, length, and depth), and configuration of the notches affect the response of the eddy-current system. Notch depth is usually specified as a percentage of nominal wall thickness of the tubular product being examined. Notches may be placed on the outer, inner, or both surfaces of the reference (calibration) standard. Outer surface notches provide an indication of system response to discontinuities originating on the outer tube surface, whereas inner surface notches provide an indication of system response to discontinuities originating on the inner tube surface (Note 5).

NOTE 4—Longitudinal notch standards are normally used when examining with rotating probe systems.

NOTE 5—The density of eddy currents decreases nearly exponentially with increasing distance from the surface nearest the coil, and the sensitivity to subsurface discontinuities decreases with the change in depth allowing the use of phase analysis techniques.

7.5.3 The configuration, orientation, and dimensions (diameter of holes and the width, length, and depth of notches) of the artificial discontinuities to be used for establishing acceptance limits should be subject to agreement between supplier and purchaser.

## 8. Adjustment and Standardization of Apparatus Sensitivity

8.1 Select the apparatus, test frequency, coil or probe, or both, design, phase discrimination, and other circuitry as well as speed of examining which shall demonstrate the system capability for detecting the discontinuities of interest.

8.2 Fabricate the applicable reference standard in accordance with the agreement between the purchaser and tubing supplier.

8.3 Adjust the apparatus to obtain an optimum signal-to-noise ratio with the minimum sensitivity required to detect the artificial discontinuities in the reference standard. Do this under conditions (such as testing speed) identical to those to be used in production examination of the tubular products.

8.4 Determine the end effect by using a special reference tube or pipe containing a series of notches or holes near one or both of the ends and passing this reference standard through the system at production testing speeds. If notches or holes are placed near only one of the ends, pass the tube through the system backwards and forwards.

## 9. Procedure

9.1 Standardize the apparatus at the start of the test run using the reference standard. The recommended maximum interval between restandardization is 4 h although more or less frequent restandardization may be done by agreement between using parties, or whenever improper functioning of the equipment is suspected. If improper functioning is found, restandardize the apparatus and retest all tubes or pipes tested during the period since the last successful standardization.

9.2 Pass the lot of tubes or pipes to be tested through the test coil or past the probe coil of the apparatus adjusted to the sensitivity as described in Section 8. Set aside tubes or pipes with discontinuities indicated by the apparatus. It is recommended that tubes with discontinuity indications be reexamined or retested in accordance with the purchase specification.

9.3 Tubes or pipes may be tested in the final drawn, annealed, heat treated, as-welded, or other step in processing. The point in processing at which inspection is made should be agreed upon by the supplier and the purchaser. The tubes should be free of any substance that may interfere with the test.

## 10. Supplemental Information Regarding Eddy-Current Testing of High Alloy Steels and Similar Alloys

10.1 In the eddy-current testing of austenitic chromium-nickel stainless steels it has been found that test frequencies ranging from less than 1 kHz to more than 1 MHz can be used. The more commonly used operating frequencies are in the range, 1 kHz to 125 kHz. The exact frequency used will depend on the application.

*Example*—If thin-walled tubular products are to be inspected or surface rather than subsurface discontinuities are to be detected, higher frequencies are used. For heavy-walled tubes, subsurface discontinuities well below the surface require the use of a lower frequency. Choice of test frequency will determine the size of discontinuity that can be detected.

10.2 As in any eddy-current test, the depth and orientation of the discontinuity below the entry surface will affect the magnitude of signal received from it. Sensitivity varies significantly with distance from the test coils.

10.3 Under certain conditions austenitic stainless steels can be magnetic. For example, delta ferrite may be present in a welded product. Permeability may vary as a function of cold work. Some nickel alloys, such as Monel Alloy (nickel-copper alloy), are magnetic in nature and others exhibit magnetism if there are slight residual stresses in the material.

10.4 Welded stainless steel products can present a special problem in eddy-current testing. The weld area can usually be distinguished from the parent metal if the tubing has received little or no working after welding. This occurs when the as-welded structure contains delta ferrite which is magnetic and can cause a high-background noise level or spurious indications, or both. If drawn after welding, these effects may be reduced so that welded tubing cannot be distinguished from seamless tubing. These effects do not necessarily preclude the eddy-current testing of as-welded tubing; however, the testing apparatus will probably require different adjustments for materials with as-welded and wrought structures. Thus, the minimum size discontinuity that can be detected may also be different.

10.4.1 For inspecting as-welded tubing, a strong d-c magnetic field is usually applied to improve the signal-to-noise ratio. This bias field is generally applied by an encircling coil or yoke simultaneously with the field from the test coil.

10.4.2 In preparing a reference standard for welded tubing, artificial discontinuities should be placed in both the weld metal and the parent metal if both are to be inspected. The apparatus is then adjusted to obtain an optimum signal-to-noise ratio.

 **E 426 – 98**

10.4.3 When inspecting only the weld area, the discontinuities shall be placed in the weld area.

10.5 Certain austenitic chromium-nickel stainless steels exhibit changes in magnetic properties as a result of cold work. As a result, it may be desirable to prepare reference standards from each lot of material in order to take into account the effect of magnetic permeability. It may also be helpful to employ a magnetic-saturation device to minimize the effects of varying magnetic permeability.

10.6 Both the test frequency and the type of apparatus being used should be considered when choosing the testing speed. Certain types of equipment can detect discontinuities at very slow speeds, while other types require a certain minimum speed. The testing speed may need to be linked to the speed at which the material is being processed at the point of inspection.

10.7 The response from natural discontinuities can be significantly different than that from artificial discontinuities such as drilled holes or notches. For this reason, sufficient work should be done to establish the sensitivity level and set-up required to detect natural discontinuities of consequence to the end use of the product.

## **11. Keywords**

11.1 alloy; austenitic chromium-nickel stainless steels; austenitic stainless steels; conductivity; discontinuities; eddy-current; electromagnetic; encircling coil; hall element; non-magnetic steels; probe coil; seamless tubular products; tubular product; welded tubular products

*ASTM International takes no position respecting the validity of any patent rights asserted in connection with any item mentioned in this standard. Users of this standard are expressly advised that determination of the validity of any such patent rights, and the risk of infringement of such rights, are entirely their own responsibility.*

*This standard is subject to revision at any time by the responsible technical committee and must be reviewed every five years and if not revised, either reapproved or withdrawn. Your comments are invited either for revision of this standard or for additional standards and should be addressed to ASTM International Headquarters. Your comments will receive careful consideration at a meeting of the responsible technical committee, which you may attend. If you feel that your comments have not received a fair hearing you should make your views known to the ASTM Committee on Standards, at the address shown below.*

*This standard is copyrighted by ASTM International, 100 Barr Harbor Drive, PO Box C700, West Conshohocken, PA 19428-2959, United States. Individual reprints (single or multiple copies) of this standard may be obtained by contacting ASTM at the above address or at 610-832-9585 (phone), 610-832-9555 (fax), or service@astm.org (e-mail); or through the ASTM website (www.astm.org).*