



# Standard Test Method for Moisture or Volatile Distillates in Bituminous Paving Mixtures<sup>1</sup>

This standard is issued under the fixed designation D 1461; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon ( $\epsilon$ ) indicates an editorial change since the last revision or reapproval.

*This standard has been approved for use by agencies of the Department of Defense.*

## 1. Scope

1.1 This test method covers the determination, by direct measurement, of moisture or volatile fractions of the bitumen in bituminous paving mixtures.

1.2 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.*

## 2. Referenced Documents

### 2.1 ASTM Standards:

D 244 Test Methods for Emulsified Asphalts<sup>2</sup>

D 979 Test Methods for Sampling Bituminous Paving Mixtures<sup>2</sup>

## 3. Significance and Use

3.1 This test method is used for determining either the amount of moisture or the amount of volatile petroleum distillates in bituminous paving mixtures.

## 4. Apparatus

4.1 *Metal Still*— A vertical cylindrical still, similar to that used in Test Methods D 244, having a faced flange at the top to which the head is tightly attached by means of a clamp. The head shall be of metal, preferably of copper or brass, and shall be provided with a tubulation 25.4 mm (1 in.) in inside diameter.

4.2 *Condenser*, of the water-cooled reflux glass-tube type, having a condenser jacket not less than 400 mm (15 3/4 in.) long with an inner tube 9.5 to 12.7 mm (3/8 to 1/2 in.) in outside diameter. The end of the condenser inserted in the trap shall be ground off at an angle of 30° from the vertical axis of the condenser. For mixtures with very volatile solvents, it may be necessary to supplement this water-cooled condenser with a

second water-cooled condenser of approximately the same dimensions.

4.3 *Trap*, of well-annealed glass, of one of the following types depending upon the purpose of the test:

4.3.1 For determination of water in bituminous paving mixtures, a glass trap of 10 or 25-mL capacity shall be used. The trap shall be graduated in 0.1-mL divisions with  $\pm 0.05$ -mL maximum error below 1 mL, and in 0.2-mL divisions with a  $\pm 0.1$ -mL maximum error above 1 mL, as specified in Table 1 and Fig. 1, Fig. 2, Fig. 3, and Fig. 4. Tapered Ball traps require adaptors for connection to the metal still.

4.3.2 For determination of the volatile fractions of the bitumen, the trap shall conform to the dimensions shown in Fig. 5.

4.4 *Solvent*—For general use, an aromatic solvent is preferred, since it has high solvency and dispersing power for most bituminous materials. Xylene, or a blend of 20 % toluene and 80 % xylene, is recommended. For asphalts and similar petroleum products, a petroleum distillate, 5 % boiling between 90 and 100°C (194 and 212°F), and 90 % distilling below 210°C (410°F) may be used. For coal-tar, water-gas tar, and similar materials, the aromatic solvent must be used.

4.5 *Heating Device*— Any satisfactory source of heat that will be capable of maintaining a rate of distillation of 85 to 95 drops/min.

## 5. Sampling

5.1 Sampling shall be carried out in accordance with the procedures set forth in Test Methods D 979.

5.2 The sample shall be representative of the material and shall be of such size as practical to fill the container in which it is transported to the laboratory. For duplicate tests a 1.9-L (1/2-gal) friction-top tin pail full of the material would be satisfactory.

## 6. Test Specimen and Sample

6.1 Thoroughly mix the sample and weigh out an amount estimated to show a percentage of moisture or diluent within the capacity of the trap calibration. Keep the remainder of the sample in its tightly covered container. The weighed sample


<sup>1</sup> This test method is under the jurisdiction of ASTM Committee D04 on Road and Paving Materials and is the direct responsibility of Subcommittee D04.25 on Analysis of Bituminous Mixtures.

Current edition approved Oct. 25, 1985. Published December 1985. Originally published as D 1461 – 56 T. Last previous edition D 1461 – 79.

<sup>2</sup> *Annual Book of ASTM Standards*, Vol 04.03.


TABLE 1 Dimensions and Sizes of Traps

Style	Description			Figure	Size of Trap, mL	Range, mL	Small-est Scale Division, mL	Scale Error max, mL
	Top of Graduated Tube	Bottom of Graduated Tube	Bottom of Vapor Tube					
A	§ joint	conical	§ joint	7	10	0 to 1.0 over 1.0 to 10.0	0.1 0.2	0.05 0.1
B	§ joint	conical	§ joint	8				
C	§ joint	conical	plain	9				
D	plain	conical	plain	10	25	0 to 1.0 over 1.0 to 25	0.1 0.2	0.05 0.1
E	§ joint	round	§ joint	11	5 10	0 to 5.0 0 to 10.0	0.1 0.1	0.05 0.1

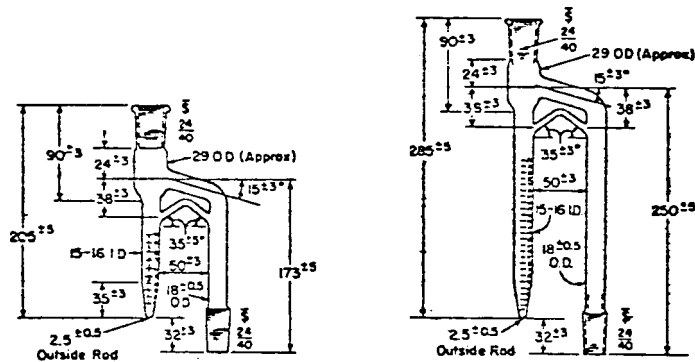

NOTE 1—All dimensions are in millimetres.

FIG. 1 Traps (Style A)

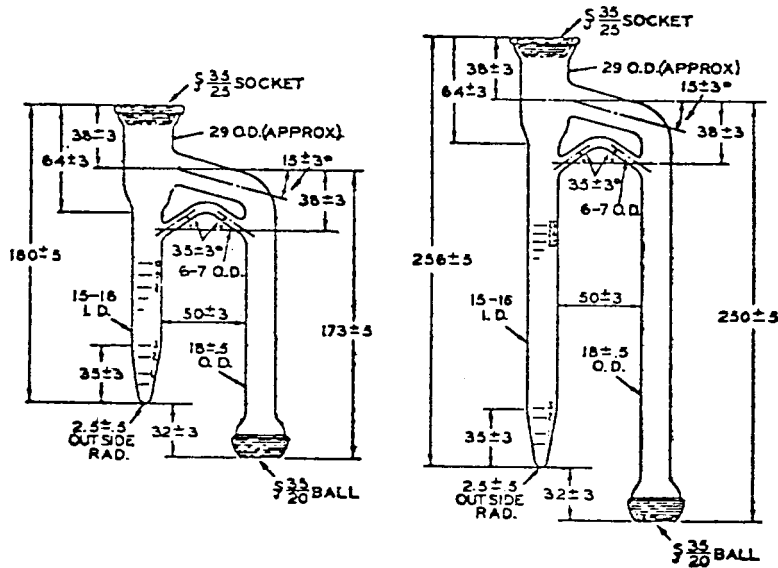

NOTE 1—All dimensions are in millimetres.


FIG. 2 Traps (Style B)

should be preferably not less than 500 g for normal mixtures. Thoroughly break up this sample to avoid larger lumps, and place it in the still.

### 7. Procedure for Determination of Moisture


7.1 After the sample has been placed in the still, add 200 mL of the solvent and quickly stir it into the sample.

7.2 Assemble the components of the apparatus as illustrated in Fig. 6, choosing the trap in accordance with the expected water content of the sample and making all connections vapor and liquid tight. Insert a gasket of heavy paper, moistened with water between the still body and cover. The condenser tube and trap must be chemically clean to assure free drainage of water into the bottom of the trap. Insert a loose cotton plug in the tip

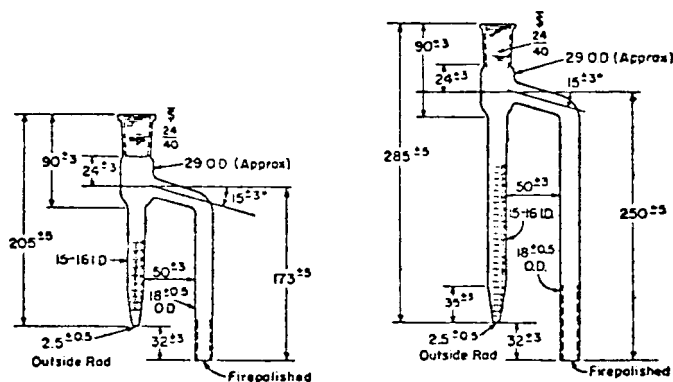

NOTE 1—All dimensions are in millimetres.

FIG. 3 Traps (Style C)

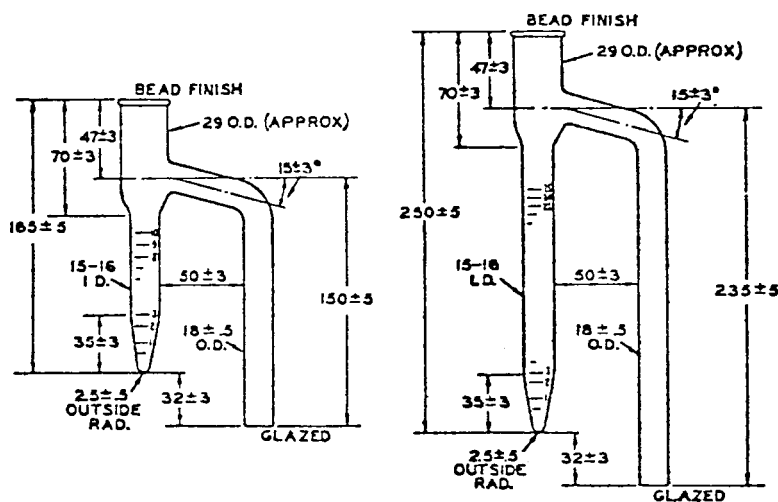

NOTE 1—All dimensions are in millimetres.

FIG. 4 Traps (Style D)

of the condenser to prevent condensation of atmospheric moisture inside it. Circulate cold water through the jacket of the condenser.

7.3 Apply heat at such a rate that refluxing will start within 5 to 10 min after the heat has been applied and the condenser solvent will drip into the trap at a rate of 85 to 95 drops/min. Continue the distillation until three successive readings of the trap at 15-min intervals show no increase in the amount of water being condensed, except that in no case shall distillation continue for more than 1½ h.

7.4 Allow the contents of the trap to reach room temperature and read the volume of water in the trap to the nearest scale division. Record the volume of water and calculate in weight percent as described in 9.1.

### 8. Procedure for Determination of Volatile Distillates

8.1 After the sample has been placed in the still, add 350 mL of water and approximately 3 g of sodium carbonate (Na<sub>2</sub>CO<sub>3</sub>) and quickly stir into the sample. Firmly attach the still cover and assemble the trap and condenser in the manner prescribed in 7.2, except that the gasket is moistened with solvent and the trap used shall be the dilution trap specified in 4.3.2.

8.2 Apply heat at such a rate that the water and solvent will begin to reflux in 5 to 10 min after the heat has been applied

and will drip from the condenser at the rate of 85 to 95 drops per minute. In case the sample contains a large amount of very volatile solvent, it may be necessary to add a second water-cooled condenser above the first one or to reduce the rate of distillation somewhat to prevent escape of the solvent.

8.3 Continue distillation until three successive readings of the upper and lower levels of the diluent at 15-min intervals show no increase in the quantity being collected. Then remove the source of heat and allow the trap and contents to reach room temperature. Allow the trap to stand a minimum of ½h to permit the solvent to separate.

8.4 Record the volume of diluent in the trap to the nearest scale division and calculate in weight percent as described in 9.2. Use the specific gravity of the diluent at 25°C (77°F).

### 9. Calculation

9.1 Calculate the moisture content as follows:

$$\text{Water, \%} = \frac{\text{volume of water in trap}}{\text{weight of sample}} \times 100 \quad (1)$$

9.2 Calculate the volatile distillate as follows:

$$\text{Diluent, \%} = \frac{(\text{volume diluent in trap}) (\text{sp gr diluent at } 25^{\circ}\text{C})}{\text{weight of sample}} \times 100 \quad (2)$$

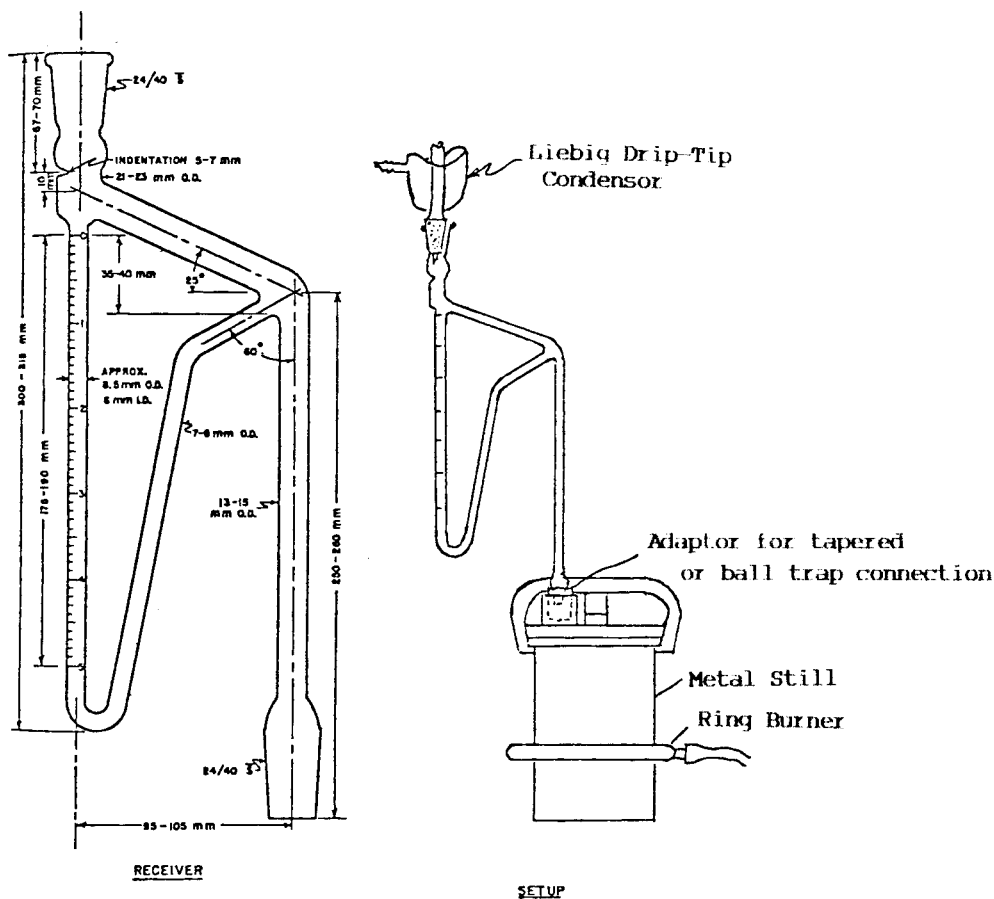


FIG. 5 Apparatus for Determining Volatile Fractions of the Bitumen

10. Report

10.1 Report the moisture content as the weight percent water content in accordance with 9.1.

10.2 Report the volatile distillates as the weight percent diluent content in accordance with 9.2.

NOTE 1—Assume specific gravity of diluent based on knowledge of diluent type or values in the range of 0.85 to 0.90. This only defines volatiles that are obtained at the maximum test temperature.

11. Precision

11.1 Precision for Determination of Moisture—The following criteria should be used for judging the acceptability of results (95 % probability) when using the 10-mL or 25-mL traps.

11.1.1 Repeatability—Duplicate determination of water by the same operator should be considered suspect if they differ by more than the following amounts:

Water Collected, mL	
0 to 1.0	0.1 mL
1.1 to 25	0.1 mL or 2 % of the mean, whichever is greater


11.1.2 Reproducibility—The results submitted by each of two laboratories should be considered suspect if they differ by more than the following amounts:

Water Collected, mL	
0 to 1.0	0.2 mL
1.1 to 25	0.2 mL or 10 % of the mean, whichever is greater

11.2 Precision for Determination of Volatile Distillates—The precision of this method as obtained by statistical examination of interlaboratory test results is as follows:

11.2.1 Repeatability— Duplicate determinations of volatile distillates by the same operator should be considered suspect if they differ by more than 0.6 volume %.

11.2.2 Reproducibility— The results submitted by each of two laboratories should be considered suspect if they differ by more than 1.4 volume %.

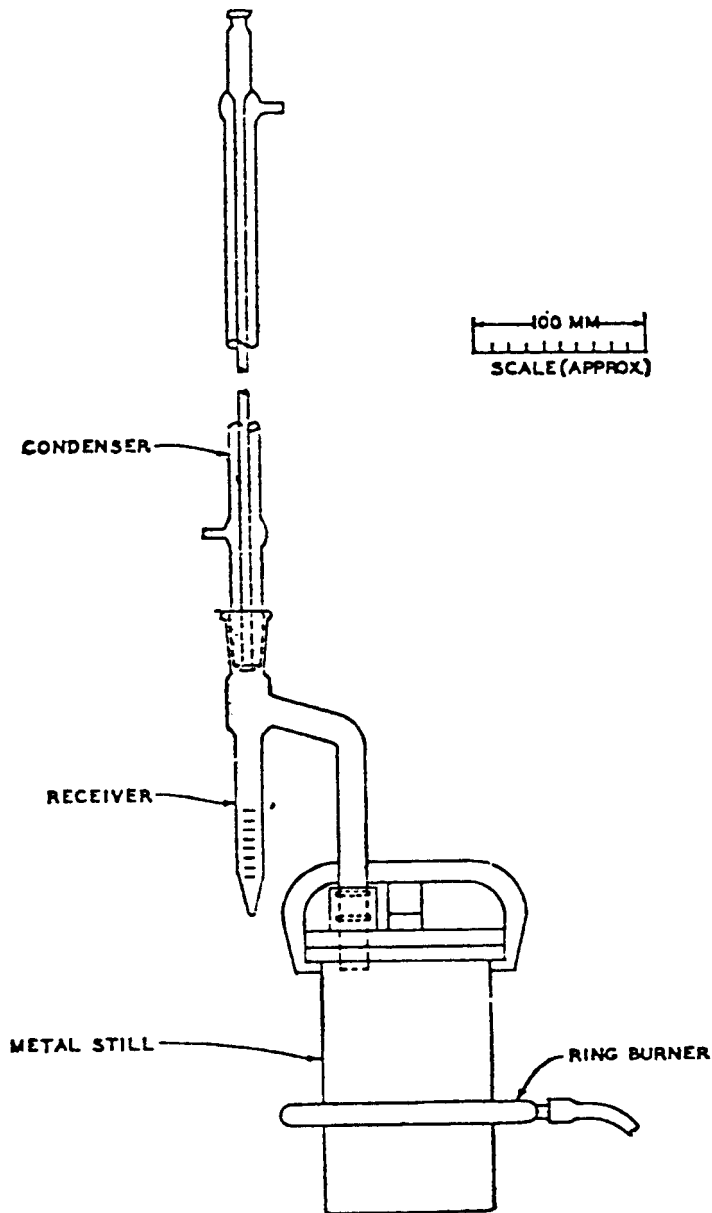

NOTE 1—Trap shall be 15 to 16 mm in inside diameter.

**FIG. 6 Typical Assemblies with Metal Still**

ASTM International takes no position respecting the validity of any patent rights asserted in connection with any item mentioned in this standard. Users of this standard are expressly advised that determination of the validity of any such patent rights, and the risk of infringement of such rights, are entirely their own responsibility.

This standard is subject to revision at any time by the responsible technical committee and must be reviewed every five years and if not revised, either reapproved or withdrawn. Your comments are invited either for revision of this standard or for additional standards and should be addressed to ASTM International Headquarters. Your comments will receive careful consideration at a meeting of the responsible technical committee, which you may attend. If you feel that your comments have not received a fair hearing you should make your views known to the ASTM Committee on Standards, at the address shown below.

This standard is copyrighted by ASTM International, 100 Barr Harbor Drive, PO Box C700, West Conshohocken, PA 19428-2959, United States. Individual reprints (single or multiple copies) of this standard may be obtained by contacting ASTM at the above address or at 610-832-9585 (phone), 610-832-9555 (fax), or [service@astm.org](mailto:service@astm.org) (e-mail); or through the ASTM website ([www.astm.org](http://www.astm.org)).