



Standard Practice for Operation of the Vettermann Drum Tester¹

This standard is issued under the fixed designation D 5417; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon (ϵ) indicates an editorial change since the last revision or reapproval.

1. Scope

1.1 This practice describes the equipment and operation of the Vettermann drum tester for testing pile yarn floor covering to produce changes in appearance and color due to changes in surface structure by mechanical action.

1.2 This practice is only applicable for use in testing unused pile floor covering of all types. It is not applicable for use in testing used pile yarn floor coverings.

1.3 The values stated in inch-pound units are to be regarded as the standard for all measurements except mass. The SI (metric) units for all measurements except mass are provided for information only.

1.4 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.*

2. Referenced Documents

2.1 ASTM Standards:

D 123 Terminology Relating to Textiles²

D 1776 Practice for Conditioning Textiles for Testing³

D 5684 Terminology Relating to Pile Floor Coverings³

3. Terminology

3.1 Definitions:

3.1.1 For definitions of pile yarn floor covering related terms used in this practice, refer to Terminology Relating to Pile Floor Coverings D 5684. For definitions of other textile terms used in this practice refer to Terminology Relating to Textiles.

4. Summary of Practice

4.1 The test specimen is mounted in the rotatable drum with the pile surface towards the center of the drum and the edges under the retaining segments. A steel ball, with 14 rubber studs

rolls randomly inside the drum on the pile surface for a specified number of revolutions.

5. Significance and Use

5.1 This equipment may be used to bring about the changes in texture on the surface of pile floor covering caused by mechanical action.

5.2 The acceptance criteria of this practice shall be set by mutual agreement between the purchaser and the supplier.

6. Apparatus and Material

6.1 Vettermann Drum Tester (See Fig. 1):

6.1.1 *Drum*, incorporating a revolution counter and four adjustable retaining segments (thickness: 15 ± 1 mm (0.6 ± 0.03 in.)) on each side wall of the drum. A free-running circular brush mounted in such a way that it lightly contacts the surface of specimens and loose fibers are continuously extracted by a vacuum cleaner. A vulcanized fiber backing sheet 2320 by 270 by 1.5 mm (93.3 by 10.6 by 0.06 in.) is loosely laid inside the drum. This sheet remains permanently in the drum.

6.1.2 The Vettermann drum dimensions are as follows:

Internal diameter	730 \pm 10 mm	(28.7 \pm 0.39 in.)
Internal depth	270 \pm 5 mm	(10.6 \pm 0.20 in.)
Effective depth	240 \pm 7 mm	(9.4 \pm 0.28 in.)
Thickness of curved surface	8 \pm 0.5 mm	(0.31 \pm 0.02 in.)

6.1.3 *Driving System*, with a speed of 1.65 rad/s (16 ± 1 rpm) and the direction of rotation is reversed every five minutes, stopping between reversals for approximately 1 s time intervals, with approximately one second stationary time.

6.1.4 *Protective Cage*, fits over the drum and must be in place prior to Vettermann drum rotation.

6.1.5 *Round Steel Ball*, fitted with fourteen cylindrical rubber studs located equally spaced on the ball surface. The studs are replaceable and are screwed into flat faces on the surface of the ball. (See Fig. 2.):

Diameter of ball	120 \pm 0.2 mm	(4.7 \pm 0.01 in.)
Distance between diametrically opposed flat stud-mounting faces	118 \pm 0.1 mm	(4.6 \pm 0.01 in.)
Mass without studs	6800 \pm 100 g	(15.0 \pm 0.2 lb)
Mass with studs	7600 \pm 100 g	(16.8 \pm 0.2 lb)

6.1.6 *Replaceable Rubber Studs*, are a composite rubber

¹ This practice is under the jurisdiction of ASTM Committee D-13 on Textiles and is the direct responsibility of Subcommittee D13.21 on Pile Floor Coverings. Current edition approved Feb. 10, 1999. Published March 1999.

² *Annual Book of ASTM Standards*, Vol 07.01.

³ *Annual Book of ASTM Standards*, Vol 07.02.

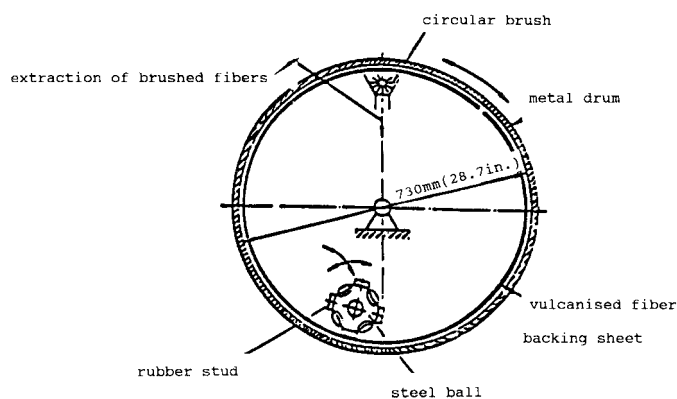


FIG. 1 Vettermann Drum Tester

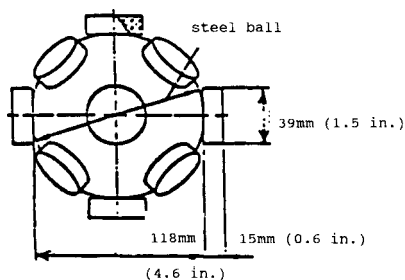


FIG. 2 Round Steel Ball

disk attached to a steel backing plate with integral mounting screw. The dimensions are:

Diameter	39 ± 0.5 mm	(1.54 ± 0.02 in.)
Total height including mounting plate	15 ± 0.5 mm	(0.59 ± 0.02 in.)
Thickness of steel backing plate	3 mm	(0.12 in.)
Rubber hardness	48 ± 3	Type A

6.1.6.1 The studs must be replaced after 500 000 revolutions of the drum. Unscrew the old studs and replace with new studs ensuring that each stud is properly tightened. Place disposable specimens in the drum tester and condition the new studs by running the tester for 10 000 revolutions with the steel ball inside.

6.1.7 *Vacuum Cleaner*, upright type, with a rotating brush and beater bar, unless this type of apparatus is not recommended by the manufacturer of the pile floor covering under test, in that case the appropriate recommended device should be used.

6.1.8 *Cleaning Frame*, with a central rectangular aperture to receive the test specimen. The frame should be the same material as the test specimen or similar in construction to the test specimen. To ensure proper cleaning by the vacuum cleaner, it is recommended the frame and test specimen be mounted on a rigid backing sheet.

7. Reagent

7.1 *Solvent*—Ethyl alcohol (CH₃CH₂OH) or technical grade iso-propyl alcohol (CH₃)₂CHOH) are suitable. Do not use cellosolve, chlorinated or ketone solvents.

8. Preparation of Specimen

8.1 *Marking Specimen*— Before cutting out the test specimen, mark on the secondary backing the direction of manu-

facture with the head of the arrow pointing in the same direction as the lay of the pile.

8.2 *Size of Specimen*— Cut the specimen approximately 570 by 265 mm (22.4 by 10.4 in.). The long dimension shall be parallel to the lengthwise direction of the carpet. Take no specimen within 100 mm (4 in.) of the trimmed selvage.

8.2.1 When testing thick pile floor covering, it may be necessary to shorten the specimen length to approximately 565 mm (22 in.).

8.3 *Preparation*— Clean the specimen with an upright vacuum cleaner, condition it flat with pile surface up for a minimum of 12 h.

9. Conditioning

9.1 Bring the specimen to moisture equilibrium for testing textiles approaching equilibrium from the dry side, without heat. Determine that moisture equilibrium for testing has been attained as directed in Practice D 1776.

10. Procedure

10.1 Perform this practice on a specimen prepared as described in Section 9, maintaining the Vettermann drum test in the standard atmosphere for testing textiles.

10.2 Remove the protective cage from the tester.

10.3 Loosen the outside bolts.

10.4 Wipe the inside of the drum and the steel ball with a clean lint free tissue and one of the recommended reagents.

10.5 Inspect the rubber studs on the steel ball for signs of wear or damage and replace as needed.

10.6 Fit the test specimen into the drum with the pile, surface towards the center of the drum and the edges under the retaining segments and clamp into place by tightening the bolt.

10.7 Place the steel ball in the drum on the pile surface.

10.8 Replace the protective cage over the Vettermann drum.

10.9 Set the revolution counter to 22 000 revolutions unless otherwise specified and switch on the machine. When the machine stops, loosen the bolts, remove the mounted specimen and place in the central aperture of the cleaning frame.

10.10 Using the upright vacuum cleaner, make four forward and four backward passes along the length of the mounted specimen ensuring all the area is covered and the final pass is in the lay of the pile and condition the specimen for 24 h.

11. Report

11.1 Report the following information:

11.1.1 State that the test was conducted as directed in this practice (D 5417),

11.2 Identify the tested specimen,

11.3 Report the atmospheric conditions, if other than standard,

11.4 Report the number of revolutions,

11.5 Report the type of vacuum cleaner used, and

11.6 Detail any deviations from this practice.

12. Keywords

12.1 appearance; floor covering

**NOTICE: This standard has either been superseded and replaced by a new version or discontinued.
Contact ASTM International (www.astm.org) for the latest information.**



The American Society for Testing and Materials takes no position respecting the validity of any patent rights asserted in connection with any item mentioned in this standard. Users of this standard are expressly advised that determination of the validity of any such patent rights, and the risk of infringement of such rights, are entirely their own responsibility.

This standard is subject to revision at any time by the responsible technical committee and must be reviewed every five years and if not revised, either reapproved or withdrawn. Your comments are invited either for revision of this standard or for additional standards and should be addressed to ASTM Headquarters. Your comments will receive careful consideration at a meeting of the responsible technical committee, which you may attend. If you feel that your comments have not received a fair hearing you should make your views known to the ASTM Committee on Standards, at the address shown below.

This standard is copyrighted by ASTM, 100 Barr Harbor Drive, PO Box C700, West Conshohocken, PA 19428-2959, United States. Individual reprints (single or multiple copies) of this standard may be obtained by contacting ASTM at the above address or at 610-832-9585 (phone), 610-832-9555 (fax), or service@astm.org (e-mail); or through the ASTM website (www.astm.org).