

This document is not an ASTM standard and is intended only to provide the user of an ASTM standard an indication of what changes have been made to the previous version. Because it may not be technically possible to adequately depict all changes accurately, ASTM recommends that users consult prior editions as appropriate. In all cases only the current version of the standard as published by ASTM is to be considered the official document.



Designation: D 1004 – 94a (Reapproved 2003)



Designation: D 1004 – 03

Standard Test Method for Initial Tear Tear Resistance (Graves Tear) of Plastic Film and Sheeting¹

This standard is issued under the fixed designation D 1004; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon (ϵ) indicates an editorial change since the last revision or reapproval.

This standard has been approved for use by agencies of the Department of Defense.

¹ This test method is under the jurisdiction of ASTM Committee D20 on Plastics and is the direct responsibility of Subcommittee D20.109 on Mechanical Properties Film and Sheeting.

Current edition approved January–August 10, 2003. Published March–October 2003. Originally approved in 1949. Last previous edition approved in 1994 2003 as D 1004–94a.

An ISO equivalency statement has been added since the prior version of this test method: D 1004 – 94a (03).

1. Scope*

1.1 This test method² covers the determination of the tear resistance of flexible plastic film and sheeting at very low rates of loading, 51 mm [2 in.]/min. ~~This test method and~~ is designed to measure the force to initiate tearing. The specimen geometry of this test method produces a stress concentration in a small area of the specimen. The maximum stress, usually found near the ~~outset~~ onset of tearing, is recorded as the tear resistance in newtons ~~(or pounds-force)~~.

~~1.2 The values stated in SI units are to be regarded as the standard: [or pounds-force]. The values given in parentheses are for information only.~~

~~1.3 This standard does method is not purport to address all of the safety concerns, if any, associated with its use. It applicable for film or sheeting material where brittle failures occur during testing or where maximum extension is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use. Specific cautionary statements are given in Note 2: greater than 101.6 mm [4 in.].~~

NOTE 1—Film has been arbitrarily defined as sheeting having nominal thickness not greater than 0.25 mm [0.010 in.].

~~1.2 Constant-Rate-of-Grip Separation Test—This test method employs a constant rate of separation of the grips holding the test specimen.~~

~~1.2.1 Specimen extension may be measured in this test method by grip separation.~~

~~1.3 The values stated in SI units are to be regarded as the standard. The values given in brackets are provided for information only.~~

~~1.4 This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.~~

NOTE 2—There is no similar or equivalent ISO standard.

2. Referenced Documents

2.1 ASTM Standards:

~~D 374 Test Methods 618 Practice for Thickness of Solid Electrical Insulation Conditioning Plastics for Testing³~~

~~D 618 Practice 882 Test Methods for Conditioning Plastics for Testing⁴ Tensile Properties of Thin Plastic Sheeting³~~

~~D 882 Test Methods for Tensile Properties of Thin Plastic Sheeting⁴ 883 Terminology Relating to Plastics³~~

~~D 4000 Classification System for Specifying Plastic Materials⁴~~

² The following reference may be of interest in connection with this test method: Graves, F. L., “The Evaluation of Tear Resistance in Elastomers,” *India Rubber World*, Vol 111, No. 3, December 1944, pp. 305–308.

³ *Annual Book of ASTM Standards*, Vol 1 08.01.

⁴ *Annual Book of ASTM Standards*, Vol 08.04+2.

D 5947 Test Methods for Physical Dimensions of Solid Plastics Specimens⁵

E 4 Practices for Force Verification of Testing Machines⁶

E 691 Practice for Conducting an Interlaboratory Study to Determine the Precision of a Test Method⁷

3. Significance and Use

3.1 Tear resistance Terminology

3.1 Definitions:

Definitions of plastic film or sheeting is a complex function of its ultimate resistance terms applying to rupture. The specimen geometry and speed of testing in this test method are controlled to produce tearing appear in a small area of stress concentration at rates far below those usually encountered in service.

3.2 The data of this test method furnish comparative information for ranking the tearing resistance of plastic specimens of similar composition. Actual use performance in tearing of some plastics may not necessarily correlate with data from this test method.

3.3 The resistance to tear of plastic film and sheeting, while partly dependent upon thickness, has no simple correlation with specimen thickness. Hence, tearing forces measured in newtons (or pounds-force) cannot be normalized over a wide range of specimen thickness without producing misleading data as to the actual tearing resistance of the material. Data from this test method are comparable only from specimens which vary by no more than $\pm 10\%$ from the nominal or average thickness of all specimens tested. Therefore, the tearing resistance is expressed in maximum newtons (or pounds-force) of force to tear the specimen.

3.4 For many materials, there may be a specification that requires the use of this test method, but with some procedural modifications that take precedence when adhering to the specification. Therefore, it is advisable to refer to that material specification before using this test method. Table 1 of Classification System D 4000 lists the ASTM materials standards that currently exist. Terminology D 883.

4. Summary of Test Method

4.1 The force to initiate tearing across a specific geometry of a film or sheeting specimen is measured using a constant-rate-of-grip separation machine. The force necessary to initiate the tear is calculated from the load-time or load-displacement data.

5. Significance and Use

5.1 Tear resistance of plastic film or sheeting is a complex function of its ultimate resistance to rupture. The specimen geometry and speed of testing in this test method are controlled to produce tearing in a small area of stress concentration at rates far below those usually encountered in service. Experience has shown the test to have its best reliability for materials which do not have brittle failure or do not elongate greater than two hundred percent during testing.

5.2 The data from this test method furnish comparative information for ranking the tearing resistance of plastic specimens of similar composition. Actual use performance in tearing of some plastics may not necessarily correlate with data from this test method.

5.3 The resistance to tear of plastic film and sheeting, while partly dependent upon thickness, has no simple correlation with specimen thickness. Hence, tearing forces measured in newtons [or pounds-force] cannot be normalized over a wide range of specimen thickness without producing misleading data as to the actual tearing resistance of the material. Data from this test method are comparable only from specimens, which vary by no more than $\pm 10\%$ from the nominal or average thickness of all specimens tested. Therefore, the tearing resistance is expressed in maximum newtons [or pounds-force] of force to tear the specimen.

5.4 The tear resistance of plastic film may be a specification that requires the use of this test method, but with some procedural modifications that take precedence when adhering to the specification. Therefore, it is advisable to refer to that material specification before using this test method. Table 1 of Classification System D 4000 lists the ASTM materials standards that currently exist.

6. Apparatus

6.1 Testing Machines—A power-driven testing machine of either of the two following types shall be used:

4.1.1 Static Weighing—Constant Rate constant rate-of crosshead-movement type and comprising essentially the following:

6.1.1 Fixed Member—A fixed or essentially stationary member carrying one grip.

6.1.2 Movable Member—A movable member carrying a second grip.

6.1.3 Grips—Preferably, a set of Grip Separation Type—Negligible movement of self-aligning grips for holding the upper jaw.

4.1.2 Pendulum Weighing—Constant Rate test specimen between the fixed member and the movable member of Powered-Grip Motion Type—Constant rate of lower jaw movement, variable upper jaw movement (Note 2). the testing machine. The machine shall conform grips should minimize both slippage and uneven stress distribution.

⁵ Annual Book of ASTM Standards, Vol 08.023.

⁶ Annual Book of ASTM Standards, Vol 03.01.

⁷ Annual Book of ASTM Standards, Vol 14.02.

~~6.1.3.1 Fixed grips are rigidly attached to requirements given in the appropriate Method A or B fixed and movable members of Test Methods D 882, except the testing machine. Fixed grips may be used if extreme care is taken to ensure that cross-head rates the test specimen is inserted and clamped so that the long axis of other than 51 mm [2 in.]/min the test specimen coincides with the direction of pull through the center line of the grip assembly.~~

~~6.1.3.2 Self-aligning grips are not required. Either maximum load indicating devices or recorders are permissible in attached to the testing machine. The accuracy fixed and movable member of the testing machine shall be verified in accordance with Practices E 4 (Note 3). The applied load, as indicated by such a recorder, dial, or scale, shall be accurate to within $\pm 2\%$. If an indicating device manner that they will move freely into alignment as soon as any load is used, applied so that the indicator shall remain at long axis of the test specimen will coincide with the direction of maximum load after rupture the applied pull through the center line of the test specimen, grip assembly.~~

~~NOTE 2—If both jaws 3—The specimens should be aligned as perfectly as possible with the direction of pull so that no rotary motion that may induce slippage will occur in the machine are power activated; grips; there is a limit to the rate amount of jaw separation shall be nominally 51 mm [2 in.]/min. misalignment self-aligning grips will accommodate.~~

~~NOTE 3—Experience has shown that many testing machines now in use are incapable of maintaining accuracy for as long as the periods between inspection recommended in Practices E 4. Hence, it is recommended that each machine be studied individually and verified as often as may be found necessary. It will frequently be necessary to perform this function daily.~~

~~4.2 Grips—A gripping system that minimizes both slippage and uneven stress distribution on the specimen shall be used.~~

~~NOTE 4—Grips 4—Grips lined with thin rubber. No. 80 emery cloth, or crocus cloth, rubber have been used successfully used. Grips may be of the self-tightening type. In cases where specimens frequently fail at the edge of the grips, the radius of curvature of the edges of the grips may be increased slightly at the point where they come in contact with the specimen.~~

~~6.1.4 Drive Mechanism—A drive mechanism capable of separating the movable member (grip) from the stationary member (grip) at a controlled velocity of 51 mm [2 in.3] $\pm 5\%$ /min.~~

~~6.1.5 Load Indicator—A suitable load-indicating mechanism capable of showing the total tensile load carried by the test specimen held by the grips. The testing machine shall be essentially free from inertial lag at the specified rate of testing and shall indicate the load with an accuracy of $\pm 1\%$. The accuracy of the testing machine shall be verified in accordance with Practices E 4.~~

~~6.1.6 Crosshead Extension Indicator— A suitable extension-indicating mechanism capable of showing the amount of change in the separation of the grips (crosshead movement).~~

~~6.2 Thickness-Measuring Devices—Suitable micrometers, —A micrometer as prescribed in Test Methods D 5947, or thickness gages, an equivalent measuring device, reading to 0.0025 mm [0.0001 in.] or less, shall be used for measuring the thickness of the specimens. less. The pressure exerted by the gage on the specimen being measured shall not distort or deform the specimen. For thin films, ≤ 0.025 mm [0.001 in.], or films which exhibit visual deformation during measurement, a maximum pressure of 70 kPa [10 psi] is recommended. For thicker or stiffer films, the pressure shall be between 0.159 160 and 0.186 MPa 185 kPa [23 and 27 psi] in accordance with Method C of Test Methods D 374.~~

~~4.4 psi].~~

~~6.3 Die⁸—A die having the dimensions shown in Fig. 1 shall be used to cut all specimens. The 90° angle should shall be honed sharp with no radius or have a minimum practical radius. The cutting edge of the die shall have a 5° negative rake, and shall be kept sharp and free from nicks to avoid leaving ragged edges on the specimen. Cutting may be facilitated by wetting Wetting the surface of the sample and the cutting edges of the die with water may facilitate cutting. The sample shall rest on the smooth, slightly yielding surface that will not injure damage the die blade. Light-weight cardboard or a piece of leather belting is suitable. Care should be taken that the cut edges of the specimen are perpendicular to its other surfaces and that the edges have a minimum of concavity.~~

~~4.5 Conditioning Apparatus—Apparatus for maintaining laboratory atmospheric conditions of $23 \pm 1^\circ\text{C}$ [$73.4 \pm 1.8^\circ\text{F}$] and $50 \pm 2\%$ relative humidity for conditioning prior to and during testing shall be used in accordance with Procedure A of Practice D 618, unless otherwise specified.~~

~~5.—~~

7. Test Specimens

~~5.1 The test specimens shall be cut out with a die conforming to the dimensions shown in Fig. 1 and shall not vary by more than 0.5 % from these dimensions.~~

~~5.2 Single specimens shall be used. Where orientation effects are significant and are to be evaluated, duplicate sets of specimens shall be prepared so that their direction of tear is respectively parallel with and normal to the direction of maximum orientation. dimensions. The direction of maximum orientation may be established for transparent materials by examination of the film or sheeting between crossed Polaroids.~~

⁸ Detail drawings of the die are available from ASTM Headquarters. Order Adjunct: ADJD1004.

TABLE 1 Initial Tear Resistance (Graves Tear) Machine Direction

Material	Values Expressed in Units of Grams-Force				
	Average	S_r^A	S_R^B	r^C	R^D
LDPE—LD 104	314.6	31.98	55.79	89.53	156.2
LLDPE	384.9	7.80	41.73	21.84	116.8
Polystyrene	459.8	98.06	261.6	274.6	732.3
HDPE No. 2	474.0	19.82	55.42	55.51	155.2
Polypropylene	503.9	29.87	77.45	83.64	216.9
HDPE No. 1	570.9	36.35	78.20	101.8	219.0
Polyester	2494.0	6407.9	599.2	1142.0	1678.0

^A S_r = within-laboratory standard deviation for the material stated. It is obtained by pooling the standard deviations of the test results from each laboratory:

$$S_r = \left[\frac{[\sum(S_1)^2 + (S_2)^2 \dots + (S_n)^2]/n}{2} \right]^{1/2}$$

^B S_R = between-laboratories standard deviation for the material stated. It is a pooling of the amounts by which the average of the test results for each laboratory deviate from the overall average for that material.

^C r = within-laboratory repeatability limit = $2.8 \times S_r$.

^D R = between-laboratories reproducibility limit = $2.8 \times S_R$.

TABLE 2 Initial Tear Resistance (Graves Tear) Transverse Direction

Material	Values Expressed in Units of Grams-Force				
	Average	S_r^A	S_R^B	r^C	R^D
LDPE—LD 104	325.1	15.24	34.63	42.67	96.96
LLDPE	366.6	20.52	28.53	57.45	79.89
HDPE No. 2	411.1	31.70	82.06	88.76	229.8
Polypropylene	468.0	33.94	86.73	95.02	242.8
Polystyrene	481.4	101.7	263.7	284.7	738.2
HDPE No. 1	523.9	46.02	97.75	128.9	273.7
Polyester	2341.0	317.2	443.2	888.1	1241.0

^A S_r = within-laboratory standard deviation for the material stated. It is obtained by pooling the standard deviations of the test results from each laboratory:

$$S_r = \left[\frac{[\sum(S_1)^2 + (S_2)^2 \dots + (S_n)^2]/n}{2} \right]^{1/2}$$

^B S_R = between-laboratories standard deviation for the material stated. It is a pooling of the amounts by which the average of the test results for each laboratory deviate from the overall average for that material.

^C r = within-laboratory repeatability limit = $2.8 \times S_r$.

^D R = between-laboratories reproducibility limit = $2.8 \times S_R$.

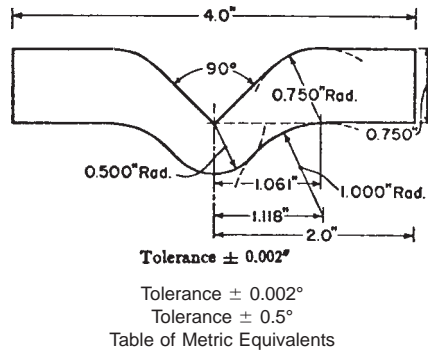


FIG. 1 Die for Tear Test Specimen

5.3 At least 10 specimens shall be tested for each sample, in the case of isotropic materials.

5.4 Twenty specimens, 10 parallel with and 10 normal to the principal axis of anisotropic or maximum orientation, shall be

tested for each sample, in the case of anisotropic material.

~~5.5 Data from specimens which break at some obvious flaw or which break in or at the cutting edges of the grips die shall be discarded kept sharp and retests made, unless such failures constitute a variable whose effect is being studied.~~

~~5.6 Data from specimens which deviate markedly from the mean value free of all tests shall be rejected if nicks to avoid leaving ragged edges on the deviation of the doubtful value is more than five times the standard deviation from the mean value obtained by excluding the doubtful results. specimens.~~

~~NOTE 5—Caution should be used to ensure all samples are the same dimension if multiple specimens are cut at one time by stacking (layering) film.~~

~~7.2 Machine direction specimens are cut perpendicular to the machine direction and transverse direction specimens are cut perpendicular to the transverse direction.~~

~~7.3 At least ten specimens shall be tested for each sample, in the case of isotropic materials.~~

~~7.4 Cut a minimum of ten specimens each in the machine direction and in the transverse direction for each anisotropic test sample.~~

~~7.5 Data from specimens which break at some obvious flaw or which break in or at the edges of the grips shall be discarded and additional specimens tested, unless such failures constitute a variable whose effect is being studied.~~

~~7.6 Data from specimens which deviate markedly from the mean value of all tests shall be rejected if the deviation of the doubtful value is more than five times the standard deviation from the mean value obtained by excluding the doubtful results.~~

~~NOTE 6—For certain materials whose properties vary considerably throughout the film or sheeting, as many as 50 specimens cut from random portions of the sheet must be tested if reliable tear resistance data is are desired.~~

68. Conditioning

~~68.1 Conditioning—Condition the test specimens at $23 \pm 2^\circ\text{C}$ [$73.4 \pm 3.6^\circ\text{F}$] and $50 \pm 5\%$ relative humidity for not less than 40 h prior to test in accordance with Procedure A of Practice D 618, for those tests where conditioning is required. In cases of disagreement, the tolerances shall be $\pm 1^\circ\text{C}$ [$\pm 1.8^\circ\text{F}$] and $\pm 2\%$ relative humidity.~~

~~68.2 Test Conditions—Conduct tests in the standard laboratory atmosphere of $23 \pm 2^\circ\text{C}$ [$73.4 \pm 3.6^\circ\text{F}$] and $50 \pm 5\%$ relative humidity, unless otherwise specified in the test methods or in this test method. applicable ASTM material specification. In cases of disagreements, the tolerances shall be $\pm 1^\circ\text{C}$ [$\pm 1.8^\circ\text{F}$] and $\pm 2\%$ relative humidity.~~

7. Speed of Testing

~~7.1 A~~

9. Procedure

~~9.1 An initial jaw separation of 25.4 mm [1 in.] shall be used. The rate of travel of the power- activated grip shall be 51 mm [2 in.]/min and shall be uniform at all times. 51-mm [2-in.]/min.~~

~~NOTE 67—In this test method, resistance to tear is calculated from the maximum load recorded or indicated by the testing machine. recorded. In testing most plastics, this maximum load is generated at the outset onset of tearing across the 13-mm [0.5-in.] testing width of the specimen. Hence, specimen.~~

~~9.2 Measure the accuracy of the initial advance of the chart pen or dial from its origin is of utmost importance. The testing speed of 51 mm [2 in.]/min is sufficiently slow to make it virtually certain that the recorder pen or dial response is not exceeded. The response of the testing machine recorder pen shall be checked prior to testing specimens.~~

8. Procedure

~~8.1 Measure the thickness of the specimen at several points in the notched area to the accuracy limits of the measuring devices specified in 4.3. 6.2. Record the average thickness in inches.~~

~~8.2 Place microns [mil].~~

~~9.3 Place the specimen in the grips of the testing machine so that the long axis of the enlarged ends of the specimen is in line with the points center line of attachment of the grips to the machine.~~

~~8.3 Apply the load at 51-mm [2-in.]/min rate of grip separation. After assembly.~~

~~9.4 After complete rupture of the specimen, the maximum tearing load in newtons [pounds-force], and the maximum extension in mm [in.] shall be noted from the dial scale or recorder chart and recorded.~~

910. Calculation

~~910.1 Calculate the average mean maximum resistance to tearing, and the maximum extension fromr all specimens tested in each principal direction of orientation. Record-d maximum tear resistance expressed in newtons [pounds-o-f-force] to three significant figures and maximum extension expressed in mm [in.] tao two significant figures.~~

~~NOTE 78—Resistance to tear may be expressed in-pounds newtons per microns, [pounds-force per mil] of specimen thickness where correlation for the particular material being tested has been established. However, it should be realized that comparison between films of dissimilar thickness may not be valid.~~

~~910.2 Calculate standard-deviation (estimated) as follows, or, by any mathematically equivalent expression. Report to two significant figures.~~

$$s = \sqrt{\frac{\sum(X^2) - n\bar{X}^2}{(n - 1)}} \quad (1)$$

where:

- s = estimated standard deviation,
- X = value of a single observation,
- n = number of observations, and
- \bar{X} = arithmetic mean of the set of observations.

10. Report

10.1 Report the following information:

- 10.1.1 Complete identification of the material tested, including type, source, manufacturer's code number, form, principal dimensions, previous history, and orientation of sample with respect to anisotropy, if any.
- 10.1.2 Average thickness of each test specimen and average thickness of all test specimens.
- 10.1.3 Type of testing machine used.
- 10.1.4 Number of specimens tested in each principal direction.
- 10.1.5 Average value of tear strength calculated in newtons (or pounds-force).
- 10.1.6 Standard deviation from the averaged values obtained for specimens tested in each principal direction. deviation.

11. Report

11.1 Report the following information:

- 11.1.1 Complete identification of the material tested, including type, source, manufacturer's code number, form, principal dimensions, previous history, and orientation of sample with respect to anisotropy, if any.
- 11.1.2 Average thickness of each test specimen and average thickness of all test specimens.
- 11.1.3 Type of testing machine used.
- 11.1.4 Number of specimens tested in each principal direction.
- 11.1.5 Average value of tear resistance calculated in newtons [pounds-force] and the maximum extension in mm [in.].
- 11.1.6 Standard deviation from the averaged values obtained for specimens tested in each principal direction.

12. Precision and Bias ⁹

142.1 Table 1 and Table 2 are based on a round robin conducted between 1986 and 1990 in accordance with Practice E 691, involving seven materials tested by seven laboratories. For each material, all the samples were prepared at one source, and randomized sections of film were sent to each of the laboratories which prepared the test specimens and tested them. Each "test result" was the average of ten determinations. Each laboratory obtained two test results for each material. ~~NOTE 8—Caution:~~

12.2 Concept of r and R —Warning—The following explanations of r and R (142.2-142.2.3) are only intended to present a meaningful way of considering the approximate precision of this test method. The data in Table 1 and Table 2 should not be rigorously applied to acceptance or rejection of material, as those data are specific to the round robin and may not be representative of other lots, conditions, materials, or laboratories. Users of this test method should apply the principles outlined in Practice E 691 to generate data specific to their laboratory and materials, or between specific laboratories. The principles of 142.2-142.2.3 would then be valid for such data:

142.2 Concept of r and R —If data. If S_r and S_R have been calculated from a large enough body of data and for test results that were the result of testing ten specimens:

142.2.1 Repeatability Limit, r —(Comparing two test results for the same material, obtained by the same operator using the same equipment on the same day.) The two test results should be judged not equivalent if they differ by more than the " r " value for that material.

142.2.2 Reproducibility Limit, R —(Comparing two test results for the same material, obtained by different operators using different equipment in different laboratories.) The two test results should be judged not equivalent if they differ by more than the " R " value for that material.

142.2.3 Any judgment in accordance with 142.2.1 or 142.2.2 would have an approximate 95 % (0.95) probability of being correct.

142.3 There are no recognized standards to estimate bias of this test method.

123. Keywords

123.1 Graves; plastic film; tear; tear initiation; thin sheeting

⁹ Supporting data are available from ASTM Headquarters. Request RR:20-1177.

SUMMARY OF CHANGES

This section identifies the location of selected changes to this test method. For the convenience of the user, Committee D20 has highlighted those changes that may impact the use of this test method. This section may also include descriptions of the changes or reasons for the changes, or both.

D 1004 - 03:

- (1) Note 1 added.
- (2) Paragraphs 1.2 and 1.2.1 were added.
- (3) Deleted reference to D 374 and added reference to D 5947.
- (4) Section 4 added.
- (5) Apparatus (Section 6) rewritten.
- (6) Speed of Testing section incorporated into Procedure (Section 9).
- (7) Procedure (Section 9) rewritten.
- (8) Calculation (Section 10) rewritten.

ASTM International takes no position respecting the validity of any patent rights asserted in connection with any item mentioned in this standard. Users of this standard are expressly advised that determination of the validity of any such patent rights, and the risk of infringement of such rights, are entirely their own responsibility.

This standard is subject to revision at any time by the responsible technical committee and must be reviewed every five years and if not revised, either reapproved or withdrawn. Your comments are invited either for revision of this standard or for additional standards and should be addressed to ASTM International Headquarters. Your comments will receive careful consideration at a meeting of the responsible technical committee, which you may attend. If you feel that your comments have not received a fair hearing you should make your views known to the ASTM Committee on Standards, at the address shown below.

This standard is copyrighted by ASTM International, 100 Barr Harbor Drive, PO Box C700, West Conshohocken, PA 19428-2959, United States. Individual reprints (single or multiple copies) of this standard may be obtained by contacting ASTM at the above address or at 610-832-9585 (phone), 610-832-9555 (fax), or service@astm.org (e-mail); or through the ASTM website (www.astm.org).