

This document is not an ASTM standard and is intended only to provide the user of an ASTM standard an indication of what changes have been made to the previous version. Because it may not be technically possible to adequately depict all changes accurately, ASTM recommends that users consult prior editions as appropriate. In all cases only the current version of the standard as published by ASTM is to be considered the official document.



**Designation: D 3801 – 96<sup>e1</sup>**


**Designation: D 3801 – 00**

# Standard Test Method for Measuring the Comparative Burning Characteristics of Solid Plastics in a Vertical Position<sup>1</sup>

This standard is issued under the fixed designation D 3801; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reappraisal. A superscript epsilon (ε) indicates an editorial change since the last revision or reappraisal.

---

<sup>ε1</sup> ~~NOTE—Tables 1-3 were corrected editorially in March 1998.~~

---

<sup>1</sup> This test method is under the jurisdiction of ASTM Committee D-20 on Plastics and is the direct responsibility of Subcommittee D20.30 on Thermal Properties (Section D20.30.03).

Current edition approved July 10, 1996; 2000. Published September 1996; March 2001. Originally published as D 3801 – 87. Last previous edition D 3801 – 95. In 1996, the precision and bias statement was updated to include polyamide. D 3801 – 96<sup>ε1</sup>.

## 1. Scope\*

1.1 This fire-test-response standard covers a small-scale laboratory procedure for determining comparative burning characteristics of solid-plastic material, using a 20-mm flame applied to the base of specimens held in a vertical position.

NOTE 1—~~This test method, Clause 9 of IEC 707, method and Test Method B of ISO 1210-1991 IEC 60695-11-10 are technically equivalent. IEC 60695-11-10 has replaced ISO 1210.~~

NOTE 2—For additional information on materials that burn up to the holding clamp by this test method, see Test Method D 635. For test methods of flexible plastics in the form of thin sheets and film, see Test Methods D 4804. For additional information on comparative burning characteristics and resistance to burn-through, see Test Method D 5048. ~~Note 3—See Test Method D 3713 which, unless otherwise specified, uses the same specimens for determining the comparative resistance of solid plastics to ignition by a small flame.~~

1.2 This test method was developed for polymeric materials used for parts in devices and appliances. The results are intended to serve as a preliminary indication of their acceptability with respect to flammability for a particular application. The final acceptance of the material is dependent upon its use in complete equipment that conforms with the standards applicable to such equipment.

1.3 The classification system described in the appendix is intended for quality assurance and the preselection of component materials for products.

1.4 ~~It is possible that this test method may be applied is applicable to other nonmetallic materials if found to be appropriate. other than plastics. Such application is outside the scope of this technical committee.~~

1.5 This test method is not intended to cover plastics when used as materials for building construction or finishing.

1.6 The values stated in SI units are to be regarded as the standard. ~~The values given in parentheses are for information only. standard.~~

1.7 ~~This standard should be is used to measure and describe the response of materials, products, or assemblies to heat and flame under controlled-laboratory conditions and should conditions, but does not be used to describe by itself incorporate all factors required for fire hazard or appraise the fire-hazard or fire-risk fire risk assessment of the materials, products, or assemblies under actual fire conditions. However, results of this test may be used as elements of a fire-hazard assessment or a fire-risk assessment which takes into account all of the factors which are pertinent to an assessment of the fire hazard or fire risk of a particular end use.~~

1.8 ~~This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use. See 9.1.1 for a specific hazard statement.~~

## 2. Referenced Documents

### 2.1 ASTM Standards:

D 635 Test Method for Rate of Burning and/or Extent and Time of Burning of Self-Supporting Plastics in a Horizontal Position<sup>2</sup>

D 883 Terminology Relating to Plastics<sup>2</sup>

~~D-1898 Practice 4804 Test Methods for Sampling Determining the Flammability Characteristics of Plastics<sup>2</sup>~~

<sup>2</sup> Annual Book of ASTM Standards, Vol 08.01.

- ~~D 3713 Test Method for Measuring Response of Nonrigid Solid Plastics to Ignition by a Small Flame<sup>3</sup>~~  
~~D 4804 Test Methods 5025 Specification for Determining the Flammability Characteristics of Nonrigid Solid Plastics<sup>4</sup> a Laboratory Burner Used for Small-Scale Burning Tests on Plastic Materials<sup>3</sup>~~  
~~D 5025 Specification 5048 Test Method for a Laboratory Burner Used for Small-Scale Measuring the Comparative Burning Tests on Plastic Materials<sup>4</sup> Characteristics and Resistance to Burn-Through of Solid Plastics Using a 125-mm Flame<sup>3</sup>~~  
~~D 5048 Test Method 5207 Practice for Measuring the Comparative Burning Characteristics and Resistance to Burn-Through of Solid Plastics Using a 125-mm Flame<sup>4</sup>~~  
~~D 5207 Practice for Calibration of 20 and 125-mm Test Flames for Small-Scale Burning Tests on Plastic Materials<sup>3</sup>~~  
E 176 Terminology of Fire Standards<sup>4</sup>

---

<sup>3</sup> *Annual Book of ASTM Standards*, Vol 08.023.

<sup>4</sup> *Annual Book of ASTM Standards*, Vol 08.03: 04.07.

E 691 Practice for Conducting an Interlaboratory Study to Determine the Precision of a Test Method<sup>5</sup>

2.2 *IEC Standard*.<sup>6</sup>

~~707 Methods of~~

~~60695-11-10 Fire Hazard Testing—Part 11-10: Test for the Determination of the Flammability of Solid Electrical Insulating Materials When Exposed to an Igniting Source~~ Flames—50W Horizontal and Vertical Flame Test Methods

2.3 *ISO Standard*.<sup>6</sup>

~~ISO 1210-1991~~ Plastics—Determination of the Burning Behaviour of Horizontal and Vertical Specimens in Contact with a Small-Flame Ignition Source

### 3. Terminology

3.1 *Definitions*—For terms relating to plastics, the definitions in this test method are in accordance with Terminology D 883. For terms relating to fire, the definitions used in this test method are in accordance with Terminology E 176.

3.2 *Definitions of Terms Specific to This Standard*:

3.2.1 *afterflame*—persistence of flaming of a material, after the ignition source has been removed.

3.2.2 *afterflame time*—the length of time for which a material continues to flame, under specified conditions, after the ignition source has been removed.

3.2.3 *afterglow*—persistence of glowing of a material, after cessation of flaming or, if no flaming occurs, after removal of the ignition source.

3.2.4 *afterglow time*—the length of time for which a material continues to glow under specified test conditions, after the ignition source has been removed or cessation of flaming, or both.

3.2.5 *flame-impingement time*—the time in seconds that the flame from the burner is in contact with the specimen.

3.2.6 *flaming material*—flaming drips or particles from the specimen that ignite the absorbent 100 % cotton.

### 4. Summary of Test Method

4.1 The procedure consists of subjecting a set of specimens of identical composition and geometry to a standard test flame for two 10-s flame applications. The afterflame time is recorded after the first flame application, and the afterflame and afterglow times are recorded after the second flame application. Information is also recorded on whether or not flaming material drips from the specimen.

### 5. Significance and Use

5.1 The tests results represent afterflame and afterglow time in seconds for a material of specified shape, under the conditions of this test method.

5.2 The effect of material thickness, color additives, and possible loss of volatile components is measurable.

5.3 The results, when tabulated, serve as a potentially useful as a reference for comparing the relative performance of materials and can be as an aid in material selection.

5.4 In this procedure, the specimens are subjected to one or more specific sets of laboratory test conditions. If different test conditions are substituted or the end-use conditions are changed, it may not be possible by or from this test method to predict changes in the fire-test-response characteristics measured. Therefore, the results are valid only for the fire-test-exposure conditions described in this test method.

### 6. Apparatus

6.1 *Test Chamber*, enclosed laboratory hood or chamber, free of induced or forced draft during test, having an inside volume of at least 0.5 m<sup>3</sup>. An enclosed laboratory hood with a heat-resistant glass window and an exhaust fan for removing the products of combustion after the tests is recommended.

NOTE 43—Laboratory hoods may have induced drafts even with the exhaust fan off. A positive-closing damper may be needed.

NOTE 54—A mirror in the chamber, to provide a rear view of the specimen, has been found useful in some enclosures.

6.2 *Laboratory Burner*, constructed in accordance with Specification D 5025.

6.3 *Ring Stand*, with a clamp or the equivalent, adjustable for vertical positioning of specimens.

6.4 *Gas Supply*, a supply of technical-grade methane gas, minimum 98 % pure, with suitable regulator and meter for uniform gas flow. Natural gas having an energy density of approximately 37 ± 1 MJ/m<sup>3</sup> has been found to provide similar results. However, technical-grade methane gas shall be used as the referee gas in cases of dispute.

6.5 *Timing Device*, accurate to 0.5 s.

6.6 *Cotton*, absorbent 100 % cotton.

<sup>5</sup> Annual Book of ASTM Standards, Vol 04.07: 14.02.  
*Annual Book*

<sup>6</sup> Publications of ASTM Standards, Vol 14.02; the International Electrotechnical Commission (IEC) and International Organization for Standardization (ISO) are available from ANSI, 11 W. 42nd St., 13th Floor, New York, NY 10036.

6.7 *Desiccator*, containing anhydrous calcium chloride or other drying agent, capable of being maintained at  $23 \pm 2^\circ\text{C}$  and relative humidity not exceeding 20 %.

6.8 *Conditioning Room or Chamber*, capable of being maintained at  $23 \pm 2^\circ\text{C}$  and a relative humidity of  $50 \pm 5\%$ .

6.9 *Conditioning Oven*, a full-draft circulating-air oven capable of being maintained at  $70 \pm 1^\circ\text{C}$ .

6.10 *Micrometer*, having a resolution of at least 0.01 mm.

## 7. Sampling

7.1 Unless otherwise agreed upon, material shall be sampled in accordance with the General and Specific Sampling Procedures of Practice D 1898.

## 8. Test Specimens

8.1 The standard specimen geometry shall be  $13.0 \pm 0.5$  by  $125 \pm 5$  mm in the thickness appropriate to the objectives of the determination. Materials thicker than 13 mm shall not be tested by this test method.

8.2 Surfaces ~~must~~ shall be smooth and unbroken. Corner radius shall not exceed 1.3 mm. After any cutting operation, edges ~~must~~ shall be fine-sanded to remove burrs, saw marks, and residual filaments.

## 9. Conditioning

9.1 Condition specimen sets as follows:

9.1.1 Condition one set of five specimens for at least 48 h at a temperature of  $23 \pm 2^\circ\text{C}$  and a relative humidity of  $50 \pm 5\%$  prior to testing. Once removed from the conditioning room or chamber, specimens shall be tested within one hour.

9.1.2 Condition a second set of five specimens in a circulating-air oven for 168 h at  $70 \pm 1^\circ\text{C}$  and then cool in a desiccator for at least 4 h at room temperature prior to testing. Once removed from the desiccator, specimens shall be tested within 30 min.

9.2 All specimens shall be tested in a laboratory atmosphere of 15 to  $35^\circ\text{C}$  and 45 to 75 % relative humidity.

~~10.~~

## 9. Procedure

9.1 Conduct the burning test in a chamber, enclosure, or laboratory hood free of induced or forced draft.

9.1.1 ~~Warning—Products of combustion may be toxic. An enclosed laboratory hood—Combustion products contain toxic compounds. A system to contain and an exhaust fan for removing remove the products of combustion after the tests are recommended.~~

9.2 ~~Clamp a test, such as a laboratory hood with an exhaust fan, is required.~~

9.2 Clamp a specimen from the upper 6 mm of its length, with the longitudinal axis vertical, so that the lower end of the specimen is  $300 \pm 10$  mm above a horizontal layer of cotton, approximately 50 by 50 mm, thinned to a maximum uncompressed thickness of 6 mm, maximum ~~weight~~ mass of 0.08 g. See Fig. 1.

9.3 Place the burner remote from the specimen, ignite, and adjust it to produce a blue flame  $20 \pm 2$  mm high. Adjust the gas supply and the air ports of the burner until a 20-mm yellow-tipped blue flame is produced, and then increase the air supply until the yellow tip just disappears. Measure the height of the flame. If the flame height is not  $20 \pm 2$  mm, adjust the burner gas supply to give the proper flame height.

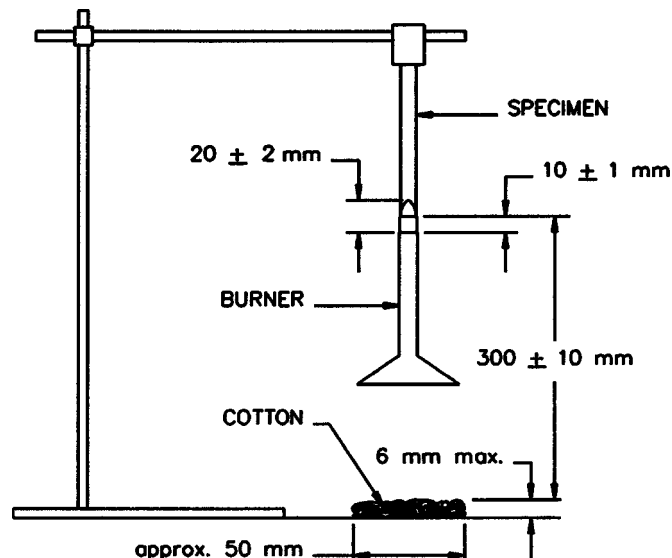


FIG. 1 Vertical Burning Test for V-0, V-1, and V-2 Classification

NOTE 65—See Practice D 5207 for recommended back pressure and flow rate for the gas supply and calibration procedure for the 20-mm flame.

409.4 Place the test flame centrally under the lower end of the test specimen with the burner tube  $10 \pm 1$  mm below the specimen and maintain that distance for a flame-impingement time of  $10.0 \pm 0.5$  s, moving the burner as necessary in response to any changes in the length or position of the specimen. Withdraw the test flame sufficiently so that there is no effect on the burning specimen (see Note-7) 6) and measure the afterflame time, in seconds. When the flaming of the specimen ceases, immediately place the test flame under the specimen again (see Note-8) 7) maintaining a distance of  $10 \pm 1$  mm for a flame-impingement time of  $10.0 \pm 0.5$  s. After this second flame application, withdraw the test flame (see Note-7) 6) and measure the afterflame and afterglow times, in seconds. Record the afterflame time after the first flame application as  $t_1$ . Record the afterflame and afterglow times after the second flame application as  $t_2$  and  $t_3$ , respectively. Note and record whether any particles fall from the specimen and, if so, whether they ignite the cotton.

NOTE 76—Withdrawing the burner a distance of 150 mm from the specimen while measuring  $t_1$ ,  $t_2$ , and  $t_3$  has been found suitable.

NOTE 87—When the flaming of the specimen ceases after the first flame application, the second flame application ~~must~~ shall be started immediately. The test shall not be interrupted, for example, to record data or replace cotton.

#### ~~10.5~~ If

NOTE 8—Measuring and recording the afterflame time  $t_2$  and then continuing the measurement of the sum of the afterflame time  $t_2$  and the afterglow time  $t_3$ , (without resetting the timing device) has been found satisfactory in the recording of  $t_3$ .

9.5 If the specimen drips molten or flaming material during either flame application, tilt the burner to an angle up to  $45^\circ$ , and withdraw the burner slightly from one of the sides of the specimens during the flame application to avoid dripping into the tube of the burner. If the specimen drips molten or flaming material, or is consumed during the test, hand-hold the burner and maintain the proper distance between the bottom of the specimen and the top of the burner tube during the flame application. ~~Ignore~~ Disregard any molten strings of the material ~~and always~~ for purposes of positioning the top of the burner tube. Always apply the flame to the bottom of the major portion of the specimen.

~~409.6~~ Repeat the procedure in ~~10.2-10.5~~ 9.2-9.5 on the remaining specimens for each set.

## 110. Calculation

110.1 Calculate the total afterflame time for each set of five specimens,  $t_f$ , using the following formula:

$$t_f = \sum_{i=1}^5 (t_{1,i} + t_{2,i}) \quad (1)$$

where:

$t_f$  = total flaming time, s,

$t_{1,i}$  = afterflame time after the first flame impingement, s, of the  $i^{\text{th}}$  specimen, and

$t_{2,i}$  = afterflame time after the second flame impingement, s, of the  $i^{\text{th}}$  specimen.

110.2 Calculate the arithmetic mean of the afterflame time for each flame impingement,  $t_1$  and  $t_2$ , and the afterflame plus afterglow time for the second flame impingement,  $t_2$  plus  $t_3$ , recorded for each set of five specimens to the nearest second.

## 121. Report

121.1 The complete report shall include the following:

121.1.1 *Material Identification*—Include generic description, manufacturer, commercial designation, lot number, and color.

121.1.2 Conditioning or aging.

121.1.2.1 Conditioning time at  $23 \pm 2^\circ\text{C}$ , h.

121.1.2.2 Cooling time in desiccator, h.

121.1.3 Individual test specimen data.

121.1.3.1 Thickness.

121.1.3.2 Afterflame time after first flame impingement.

121.1.3.3 Afterflame time after second flame impingement.

121.1.3.4 Afterflame plus afterglow time after second flame impingement.

121.1.3.5 Whether or not the specimen burned up to the holding clamp.

121.1.3.6 Whether or not the specimen dripped flaming material which ignited the cotton.

121.1.4 The total afterflame time for each set of five specimens.

121.1.5 Arithmetic mean of burning times (afterflame and afterglow) for each specimen-set.

## ~~13-~~ set.

## 12. Precision and Bias

132.1 *Precision*—Table 1, Table 2, and Table 3 are based on a round robin conducted in accordance with Practice E 691. For each material, all the samples were prepared at one source, but the individual specimens were conducted in accordance with ~~9~~ 8.1.1 by the laboratories that tested them. Each test result was the average of five individual determinations.

**TABLE 1 First Impingement, Afterflame Time<sup>A BCD</sup>**

Material	Values in the units of second, s				
	Average	$S_r^A$	$S_R^B$	$r^C$	$R^D$
Polyamide	0.7	0.2	0.4	0.6	1.1
Polypropylene II	2.0	0.6	2.1	1.6	5.8
Polyphthalamide	2.6	0.8	1.5	2.1	4.3
Polypropylene I	2.7	0.9	1.8	2.4	5.0
Polysulfone	5.4	1.6	2.9	4.5	8.1

<sup>A</sup>  $S_r$  = within-laboratory standard deviation for the indicated material. It is obtained by pooling the within-laboratory standard deviations of the test results from all of the participating laboratories:

a

$$S_r = \left[ \frac{(S_1)^2 + (S_2)^2 \dots + (S_n)^2}{n} \right]^{1/2} \quad (1)$$

<sup>B</sup>  $S_R$  = between-laboratories reproducibility, expressed as standard deviation:

$$(2) \quad S_R = [S_r^2 + S_L^2]^{1/2} \text{ where:}$$

$S_L$  = standard deviation of laboratory means, standard deviation of laboratory means.

<sup>C</sup>  $r$  = within-laboratory critical interval between two test results =  $2.8 \times S_r$ .

<sup>D</sup>  $R$  = between-laboratories critical interval between two test results =  $2.8 \times S_R$ .

**TABLE 2 Second Impingement, Afterflame Time<sup>A BCD</sup>**

Material	Values in the units of second, s				
	Average	$S_r^A$	$S_R^B$	$r^C$	$R^D$
Polyamide	3.0	1.1	3.2	3.0	9.0
Polypropylene I	1.4	0.6	1.2	1.6	3.2
Polyphthalamide	4.4	1.4	3.2	3.9	8.8
Polypropylene II	4.5	1.5	4.2	4.2	11.7
Polysulfone	8.8	2.6	3.1	7.3	8.6

<sup>A</sup>  $S_r$  = within-laboratory standard deviation for the indicated material. It is obtained by pooling the within-laboratory standard deviations of the test results from all of the participating laboratories:

$$S_r = \left[ \frac{(S_1)^2 + (S_2)^2 \dots + (S_n)^2}{n} \right]^{1/2} \quad (3)$$

<sup>B</sup>  $S_R$  = between-laboratories reproducibility, expressed as standard deviation:

$$S_R = [S_r^2 + S_L^2]^{1/2} \quad (4)$$

where:

$S_L$  = standard deviation of laboratory means, standard deviation of laboratory means.

<sup>C</sup>  $r$  = within-laboratory critical interval between two test results =  $2.8 \times S_r$ .

<sup>D</sup>  $R$  = between-laboratories critical interval between two test results =  $2.8 \times S_R$ .

132.1.1 The polypropylene (I and II), polyphthalamide, and polysulfone materials were tested by 18 laboratories. Each laboratory obtained two test results for each material. The round robin was conducted in 1994.

13.1.2 The<sup>7</sup>

12.1.2 The polyamide material was tested by seven laboratories. Each laboratory obtained four test results. The round robin was conducted in 1995.<sup>8</sup>

NOTE 9—**Caution:** The following explanations of  $r$  and  $R$  (132.2-132.2.3) are only intended to present a meaningful way of considering the approximate precision of this test method. The data in Table 1, Table 2, and Table 3 should not be applied to the acceptance or rejection of materials, as these data apply only to the materials tested in the round robin and are unlikely to be rigorously representative of other lots, formulations, conditions, materials, or laboratories. Users of this test method should apply the principles outlined in Practice E 691 to generate data specific to their laboratory and materials, or between specific laboratories. The principles of 132.2-132.2.3 would then be valid for such data.

132.2 *Concept of  $r$  and  $R$* —If  $S_r$  and  $S_R$  have been calculated from a large enough body of data, and for test results that were averages from testing five specimens, then:

132.2.1 *Repeatability*— $r$  is the interval representing the critical difference between two test results for the same material, obtained by the same operator using the same equipment on the same day in the same laboratory. The two test results shall be judged not equivalent if they differ by more than the  $r$  value for that material.

132.2.2 *Reproducibility*— $R$  is the interval representing the critical difference between two test results for the same material, obtained by different operators using different equipment in different laboratories, not necessarily on the same day. The two test

<sup>7</sup> Publications of the International Electrotechnical Commission (IEC) and International Organization for Standardization (ISO)

<sup>7</sup> Supporting data are available from ANSI, 11 W. 42nd St., 13th Floor, New York, NY 10036; ASTM Headquarters. Request RR: D20-K069.

<sup>8</sup> Supporting data are available from ASTM Headquarters. Request RR: D20-K069; RR: D20-1188.

**TABLE 3 Second Impingement, Afterflame Plus Afterglow<sup>A B C D</sup>**

Material	Values in the units of second, s				
	Average	$S_r^A$	$S_R^B$	$r^C$	$R^D$
Polyamide	3.0	1.1	3.2	3.0	9.0
Polypropylene I	3.1	1.1	2.3	3.1	6.5
Polyphthalamide	4.7	1.3	3.1	3.8	8.7
Polypropylene II	4.7	1.5	4.1	4.2	11.5
Polysulfone	9.2	2.7	3.2	7.7	8.9

<sup>A</sup>  $S_r$  = within-laboratory standard deviation for the indicated material. It is obtained by pooling the within-laboratory standard deviations of the test results from all of the participating laboratories:

$$S_r = \left[ \frac{(S_1)^2 + (S_2)^2 \dots + (S_n)^2}{n} \right]^{1/2} \quad (5)$$

<sup>B</sup>  $S_R$  = between-laboratories reproducibility, expressed as standard deviation:

$$S_R = \left[ S_r^2 + S_L^2 \right]^{1/2} \quad (6)$$

where:

$S_L$  = standard deviation of laboratory means. standard deviation of laboratory means.

<sup>C</sup>  $r$  = within-laboratory critical interval between two test results =  $2.8 \times S_r$ .

<sup>D</sup>  $R$  = between-laboratories critical interval between two test results =  $2.8 \times S_R$ .

results shall be judged not equivalent if they differ by more than the  $R$  value for that material.

132.2.3 Any judgment in accordance with 132.2.1 and 132.2.2 would have an approximate 95 % (0.95) probability of being correct.

132.3 *Bias*—There are no recognized standards by which to estimate bias of this test method.

### 143. Keywords

143.1 burning characteristics; flammability; plastics; solid; small-scale burning tests; vertical burning tests

## APPENDIX

### (Nonmandatory Information)

#### X1. CLASSIFICATION SYSTEM FOR DETERMINING THE COMPARATIVE BURNING CHARACTERISTICS OF SOLID PLASTICS IN A VERTICAL POSITION

X1.1 This appendix describes a classification system that can be used to characterize the burning behavior of rigid materials, supported in a vertical position, in response to a small-flame ignition source. The use of a category designation code is optional and is determined by examining the test results of materials tested by this test method. Each category code represents a preferred range of performance levels that simplifies description in material designations or specifications and may assist certification bodies to determine compliance with applicable requirements.



X1.2 The behavior of specimens may be classified in one of the categories shown in Table X1.1 by selecting the appropriate

**TABLE X1.1 Materials Classifications<sup>A</sup>**

Criteria Conditions	V-0	V-1	V-2
Afterflame time for each individual specimen, $t_1$ or $t_2$	≤10 s	≤30 s	≤30 s
Total afterflame time for any condition set ( $t_1$ plus $t_2$ for the five specimens)	≤50 s	≤250 s	≤250 s
Afterflame plus afterglow time for each individual specimen after the second flame application ( $t_2 + t_3$ )	≤30 s	≤60 s	≤60 s
Afterflame or afterglow of any specimen up to the holding clamp	No	No	No
Cotton indicator ignited by flaming particles or drops	No	No	Yes

<sup>A</sup> If only one specimen from a set of five specimens does not comply with the requirements, another set of five specimens shall be tested. In the case of the total number of seconds of flaming, an additional set of five specimens shall be tested if the totals are in the range from 51 to 55 s for V-0 and from 251 to 255 s for V-1 and V-2. All specimens from this second set shall comply with the appropriate requirements in order for the material in that thickness to be classified V-0, V-1, or V-2.

column using test results to answer the conditional questions posed.

X1.3 Recording the category designation in the test report is optional.

### SUMMARY OF CHANGES

This section identifies the location of selected changes to this test method. For the convenience of the user, Committee D20 has highlighted those changes that may impact the use of this test method. This section may also include descriptions of the changes or reasons for the changes, or both.

#### D 3801 – 00:

- (1) Updated ISO/IEC equivalency statement.
- (2) Deleted reference to ASTM D 3713.
- (3) Deleted section on sampling.
- (4) Added tolerances on gas supply in 6.4.
- (5) Added micrometer to Apparatus, new 6.10.
- (6) Added requirement to 9.1.1 to test within one hour after removal of specimens from conditioning room or chamber.
- (7) Added Note 8.

*ASTM International takes no position respecting the validity of any patent rights asserted in connection with any item mentioned in this standard. Users of this standard are expressly advised that determination of the validity of any such patent rights, and the risk of infringement of such rights, are entirely their own responsibility.*

*This standard is subject to revision at any time by the responsible technical committee and must be reviewed every five years and if not revised, either reapproved or withdrawn. Your comments are invited either for revision of this standard or for additional standards and should be addressed to ASTM International Headquarters. Your comments will receive careful consideration at a meeting of the responsible technical committee, which you may attend. If you feel that your comments have not received a fair hearing you should make your views known to the ASTM Committee on Standards, at the address shown below.*

*This standard is copyrighted by ASTM International, 100 Barr Harbor Drive, PO Box C700, West Conshohocken, PA 19428-2959, United States. Individual reprints (single or multiple copies) of this standard may be obtained by contacting ASTM at the above address or at 610-832-9585 (phone), 610-832-9555 (fax), or service@astm.org (e-mail); or through the ASTM website (www.astm.org).*