



# Standard Test Method for Measuring the Dynamic Mechanical Properties of Plastics Using a Dual Cantilever Beam<sup>1</sup>

This standard is issued under the fixed designation D 5418; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon ( $\epsilon$ ) indicates an editorial change since the last revision or reapproval.

## 1. Scope

1.1 This test method covers the use of dynamic mechanical instrumentation for gathering and reporting the viscoelastic properties of thermoplastic and thermosetting resins and composite systems in the form of rectangular bars molded directly or cut from sheets, plates, or molded shapes. The elastic modulus data generated may be used to identify the thermomechanical properties of a plastics material or composition.

1.2 This test method is intended to provide means for determining the modulus as a function of temperature of plastics using nonresonant forced-vibration techniques, as outlined in Practice D 4065. Plots of the elastic (storage), loss (viscous) and complex moduli, and tan delta as a function of frequency, time, or temperature are indicative of significant transitions in the thermomechanical performance of the polymeric material system.

1.3 This test method is valid for a wide range of frequencies, typically from 0.01 to 100 Hz.

1.4 Apparent discrepancies may arise in results obtained under differing experimental conditions. These apparent differences from results observed in another study can usually be reconciled, without changing the observed data, by reporting in full (as described in this test method) the conditions under which the data were obtained.

1.5 Test data obtained by this test method is relevant and appropriate for use in engineering design.

1.6 The values stated in SI units are to be regarded as standard.

1.7 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.*

NOTE 1—There is no similar or equivalent ISO standard.

## 2. Referenced Documents

### 2.1 ASTM Standards:

D 4065 Practice for Determining and Reporting Dynamic

Mechanical Properties of Plastics<sup>2</sup>

D 4092 Terminology Relating to Dynamic Mechanical Measurements on Plastics<sup>2</sup>

D 5279 Test Method for Measuring the Dynamic Mechanical Properties of Plastics in Torsion<sup>3</sup>

## 3. Terminology

3.1 For definitions applicable to this practice see Terminology D 4092.

## 4. Summary of Test Method

4.1 This test method covers the determination of the elastic modulus of plastics using dynamic mechanical techniques. A bar of rectangular cross section is tested as a beam in dynamic linear displacement or bending. The dual-cantilever beam specimen is gripped between two clamps. The specimen of known geometry is placed in mechanical linear displacement, with the displacement strain or deformation applied at the center of the dual-cantilever beam. The forced-strain displacement is at either a fixed frequency, or variable frequencies at either isothermal condition, or with a linear temperature increase. The elastic or loss modulus, or both, of the polymeric material system are measured in flexure.<sup>4</sup>

## 5. Significance and Use

5.1 This test method provides a simple means of characterizing the thermomechanical behavior of plastics materials using a very small amount of material. Since small test specimen geometries are used, it is essential that the specimens be representative of the material being tested. The data obtained may be used for quality control, research and development, and establishment of optimum processing conditions.

5.2 Dynamic mechanical testing provides a sensitive method for determining thermomechanical characteristics by measuring the elastic and loss moduli as a function of frequency, temperature, or time. Plots of moduli and tan delta of a material versus temperature provide graphic representations indicative of functional properties, effectiveness of cure (thermosetting-resin systems), and damping behavior under specified conditions.

<sup>1</sup> This test method is under the jurisdiction of ASTM Committee D-20 on Plastics and is the direct responsibility of Subcommittee D20.10 on Mechanical Properties.

Current edition approved March 10, 1999. Published June 1999. Originally published as D 5418 – 93. Last previous edition D 5418 – 95a.

<sup>2</sup> *Annual Book of ASTM Standards*, Vol 08.02.

<sup>3</sup> *Annual Book of ASTM Standards*, Vol 08.03.

<sup>4</sup> The particular method for measurement of the elastic and loss moduli and tan delta depends upon the individual instrument's operating principles.

5.3 This test method can be used to assess the following:

5.3.1 The modulus as a function of temperature or aging, or both,

5.3.2 The modulus as a function of frequency,

5.3.3 The effects of processing treatment, including orientation, induced stress, and degradation of physical and chemical structure,

5.3.4 Relative resin behavioral properties, including cure and damping,

5.3.5 The effects of substrate types and orientation (fabrication) on elastic modulus, and

5.3.6 The effects of formulation additives that might affect processability or performance.

## 6. Apparatus

6.1 The function of the apparatus is to hold in a horizontal position a dual cantilever beam (a rectangular cross-sectional bar) so that the material acts as the elastic and dissipative element in a mechanically driven linear displacement system. Dynamic mechanical instruments operate at a forced, constant amplitude and at either a fixed frequency or variable frequencies.

6.2 The apparatus consists of the following:

6.2.1 *Fixed Grips*—A fixed or essentially stationary grip consisting of two grips to secure the rectilinear specimen in a horizontal position in a dual cantilever fashion.

6.2.2 *Movable Grip*—A movable grip applying the linear displacement at the center of the rectilinear beam.

6.2.3 *Grips*—Grips for holding the test specimen between the fixed grip and the movable grip. The grips shall be mechanically aligned or centered, that is, they shall be attached to the fixed and movable grip, respectively, in such a manner that they will move into alignment as soon as any load is applied.

6.2.3.1 The test specimen shall be held in such a way that slippage relative to the grips is minimized as much as possible.

6.2.4 *Deformation (Strain) Device*—A device for applying a continuous linear deformation (strain) to the specimen. In the force-displacement device the deformation (strain) is applied and then released (see Table 1 of Practice D 4065).

6.2.5 *Detectors*—Devices for determining dependent and independent experimental parameters, such as force (stress), deformation (strain), frequency, and temperature. Temperature should be measurable with a precision of  $\pm 1^\circ\text{C}$ , frequency and force to  $\pm 1\%$ .

6.2.6 *Temperature Controller and Oven*—A device for controlling the temperature, either by heating (in steps or ramps), cooling (in steps or ramps), or maintaining a constant specimen environment, or a combination thereof. A temperature controller should be sufficiently stable to permit measurement of environmental chamber temperature to within  $1^\circ\text{C}$ .

6.3 *Nitrogen*, or other inert-gas supply for purging purposes.

## 7. Test Specimens

7.1 The specimens may be cut from sheets, plates, or molded shapes or may be molded to the desired finished dimensions. Typically, the rectangular cross-sectional bar is 44.5 by 6.4 by 1.6 mm; rectangular cross-sectional bars of

other dimensions can be used but should be clearly identified in the report section.

## 8. Calibration

8.1 Calibrate the instrument according to procedures recommended by the manufacturer.

## 9. Conditioning

9.1 *Conditioning*—Condition the test specimens at  $23.0 \pm 2.0^\circ\text{C}$  and  $50 \pm 5\%$  relative humidity for not fewer than 40 h prior to test in accordance with Procedure A of Practice D 618 for those materials requiring conditioning.

## 10. Procedure

10.1 Use an untested specimen for each measurement. Measure the width and thickness of the specimen to the nearest 0.03 mm at the center of the specimen.

10.2 Clamp the test specimen between the movable and stationary members; use shim stock, if necessary, to minimize slippage within the clamp.

10.3 Pre-load the test specimen so that there is a positive force. The positive pre-load should be sufficient to maintain a positive deflection during testing unless the test mode allows a zero-displacement measurement.

10.4 Measure the length of the specimen between the stationary end grips to the nearest 0.03 mm.

10.5 Select the desired frequency (or frequencies) for dynamic linear displacement.

10.6 Select the linear displacement amplitude.

10.7 *Temperature Sweep*:

10.7.1 Temperature increases should be controlled to 1 to  $2^\circ\text{C}/\text{min}$  for linear increases or 2 to  $5^\circ\text{C}/\text{min}$  with a minimum of 1-min thermal-soak time for step increases. This will allow characterizing the modulus from the glassy region, through the glass-transition region, up to the softening or glassy-rubbery state.

10.8 The tan delta peak will coincide with a significant decrease in the  $E'$  (elastic or storage) modulus, with increasing temperature, through the glass-transition region. Another indication of the glass-transition is a maximum value of the  $E''$  (loss or viscous) modulus. The indicated temperature may not be the actual temperature of the material being tested.

## 11. Calculation

11.1 The equations listed in Practice D 4065 are used to calculate the important rheological properties measured in forced, nonresonant dynamic displacement,

where:

$E'$  = storage (elastic) modulus in bending,

$E''$  = loss (viscous) modulus in bending,

$E^*$  = complex modulus in bending, and

$\delta^*$  = tan delta.

## 12. Report

12.1 Report the following information:

12.1.1 Complete identification of the material tested, including type, source, manufacturer's code, number, form, principal dimensions, and previous history,

- 12.1.2 Description and direction of cutting and loading specimen, including pre-load force,
- 12.1.3 Conditioning procedure,
- 12.1.4 Description of the instrument used for the test,
- 12.1.5 Description of the calibration procedure,
- 12.1.6 Identification of the sample atmosphere by gas composition, purity, and rate used,
- 12.1.7 Width and thickness of specimen,
- 12.1.8 Grip separation distance of the beam,
- 12.1.9 Frequency of dynamic displacement,
- 12.1.10 Amplitude of displacement,
- 12.1.11 Thermal gradient; heat rate,
- 12.1.12 Number of specimens tested,
- 12.1.13 Equations used to calculate values,
- 12.1.14 Table of data and results, including moduli and tan delta as a function of temperature, and
- 12.1.15 A plot of the modulus (moduli) and tan delta as a function of temperature (see Fig. 1).

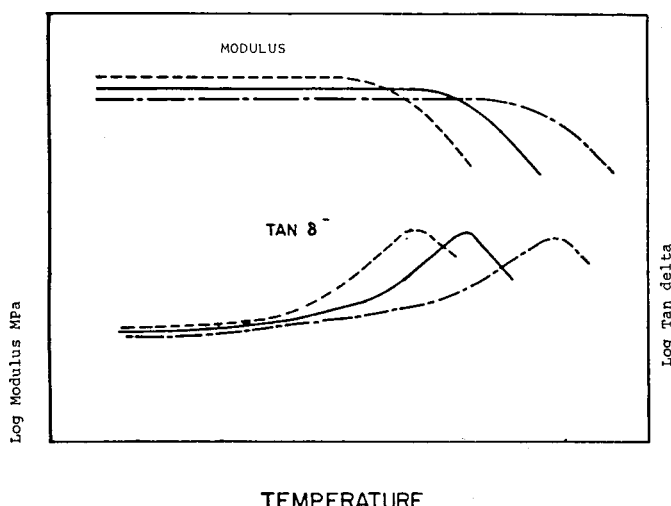


FIG. 1 Dynamic Mechanical Modulus in Bending as a Function of Temperature at Different Frequencies

**13. Precision and Bias**

13.1 The repeatability standard deviation has been determined for the following materials. A single laboratory evaluated a polyurethane sample and the values in Table 1 were obtained with the same test method in the same laboratory by the same operator using the same equipment in the shortest practical period of time using test specimens taken at random from a single quantity of homogeneous material. This laboratory tested the same polyurethane material used for the precision and bias statement in Test Method D 5279 and obtained the results in Table 1.

TABLE 1 DMRT—Dual Cantilever Beam, Elastic Modulus, E' (E<sup>9</sup> Pascals) or (E<sup>10</sup> dynes/cm<sup>2</sup>) at Selected Temperatures

	-40°C	0°C
Mean	1.162	0.04953
Standard deviation	0.004	0.00373

**14. Keywords**

14.1 dual cantilever; dynamic mechanical rheological properties; linear displacement; modulus (storage; viscous; loss modulus; and complex); tan delta; viscoelastic behavior

**SUMMARY OF CHANGES**

This section identifies the location of selected changes to this test method. For the convenience of the user, Committee D-20 has highlighted those changes that may impact the use of this test method. This section may also include descriptions of the changes or reasons for the changes, or both.

D 5418 – 99:

(1) Revised Precision and Bias statement.

(2) Added Summary of Changes.

*The American Society for Testing and Materials takes no position respecting the validity of any patent rights asserted in connection with any item mentioned in this standard. Users of this standard are expressly advised that determination of the validity of any such patent rights, and the risk of infringement of such rights, are entirely their own responsibility.*

*This standard is subject to revision at any time by the responsible technical committee and must be reviewed every five years and if not revised, either reapproved or withdrawn. Your comments are invited either for revision of this standard or for additional standards and should be addressed to ASTM Headquarters. Your comments will receive careful consideration at a meeting of the responsible technical committee, which you may attend. If you feel that your comments have not received a fair hearing you should make your views known to the ASTM Committee on Standards, 100 Barr Harbor Drive, West Conshohocken, PA 19428.*