



# Standard Specification for Ultra-High-Molecular-Weight Polyethylene (UHMW-PE) Solid Plastic Shapes<sup>1</sup>

This standard is issued under the fixed designation D 6712; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon ( $\epsilon$ ) indicates an editorial change since the last revision or reapproval.

## INTRODUCTION

This specification is intended to be a means of defining Ultra-High-Molecular-Weight<sup>2</sup> Polyethylene (UHMW-PE) solid plastic shapes for commercial use.

### 1. Scope

1.1 This specification covers requirements and test methods for the material and properties of solid plastic shapes manufactured from UHMW-PE.

1.2 The properties included in this specification are those required for the compositions covered and are derived from molded samples or fabricated from sheet, rod and profiles. Requirements necessary to identify particular characteristics important to specialized applications may be described by using the classification system given in Section 4.

1.3 This specification allows for the use of recycled plastics (as defined in Guide D 5033).

1.4 The values are stated in SI units and are regarded as the standard in all property tables. For reference purposes, English units are also included in Table S-UHMW-PE and Table A.

1.5 The following precautionary caveat pertains only to the test method portions of this specification. *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory requirements prior to use.*

NOTE 1—There is no ISO equivalent standard.

### 2. Referenced Documents

#### 2.1 ASTM Standards:

- D 618 Practice for Conditioning Plastics for Testing<sup>3</sup>
- D 638 Test Method for Tensile Properties of Plastics<sup>3</sup>
- D 883 Terminology Relating to Plastics<sup>3</sup>

<sup>1</sup> This specification is under the jurisdiction of ASTM Committee D20 on Plastics and is the direct responsibility of Subcommittee D20.20 on Plastic Products (Section D20.20.02).

Current edition approved August 10, 2001. Published October 2001.

<sup>2</sup> Ultra High Molecular Weight refers to a polyethylene resin meeting the requirements of Specification D 4020.

<sup>3</sup> Annual Book of ASTM Standards, Vol 08.01.

D 1600 Terminology for Abbreviated Terms Relating to Plastics<sup>3</sup>

D 3892 Practice for Packaging/Packing of Plastics<sup>4</sup>

D 4000 Classification System for Specifying Plastic Materials<sup>4</sup>

D 4020 Specification for Ultra-High-Molecular-Weight Polyethylene Molding and Extrusion Materials<sup>4</sup>

D 5033 Guide for Development of ASTM Standards Relating to Recycling and Use of Recycled Plastic<sup>5</sup>

#### 2.2 ISO Standard:

ISO 11542-2 Ultra-High-Molecular Weight Polyethylene (PE-UHMW) Moulding Materials—Part 2: Preparation of Test Specimens and Determination of Properties

### 3. Terminology

#### 3.1 Definitions:

3.1.1 For definitions of other technical terms pertaining to plastics used in this specification, see Terminology D 883, D 1600, or Guide D 5033.

#### 3.2 Definitions of Terms Specific to This Standard:

3.2.1 *additive, n*—any material added to the polymer such as processing aids, stabilizers, and colorants.

3.2.2 *recycled-plastic shape, n*—a product made from up to 100 % post-consumer material.

3.2.3 *regrind (plastic), n*—a product or scrap such as edge trim that have been reclaimed by shredding and granulating for use in-house.

3.2.4 *rod, n*—an extruded solid cylindrical shape with a minimum diameter of  $\frac{1}{16}$  in.

3.2.5 *sheet, n*—flat stock greater than 10 mils thickness.

3.2.6 *solid plastic shape, n*—a product of various geometries made up of UHMW-PE, such as sheet, rod, and so forth.

<sup>4</sup> Annual Book of ASTM Standards, Vol 08.02.

<sup>5</sup> Annual Book of ASTM Standards, Vol 08.03.

**4. Classification and Material**

4.1 Product shape and size as defined in the applicable purchase order.

4.2 This standard covers product as listed in Table S-UHMW-PE.

**TABLE S-UHMW-PE Physical Property Requirements for Ultra High Molecular Weight Polyethylene Solid Plastic Shapes**

Description	Type	Class	Description	Grade	Applicable Specification Callout	Description	Izod impact, Test Method for D 4020, min, kJ/m <sup>2</sup> (ft-lbs/in. <sup>2</sup> )	Elongational Stress, Test Method for ISO 11542-2 (Annex 1), min, Mpa	Tensile Elongation, Test Method for D 638, % at break, min	
UHMW-PE	01	1	unfilled	1	ASTM D 4020 see Table A	General purpose	37 (18)	>0.20	200	
				2			Recycled		...	...
				0						
	0	as specified	1	see Table A	General purpose	...	...	...		
			2			Recycled	...	...		
			0							
Other UHMW-PE	00	0	...	0	...	...	...	...		

4.2.1 The type of UHMW-PE product may be categorized by grade and type depending on resin and additives present, as defined in Table S-UHMW-PE.

4.2.2 Every type of UHMW-PE solid plastic shape may be categorized into one of two grades as follows:

4.2.2.1 *Grade 1: General Purpose (Virgin) UHMW-PE*—UHMW-PE solid plastic shapes are made using only 100 % virgin UHMW polyethylene resin which meets the requirements of Specification D 4020. If appropriate, the resin may contain additives, such as processing aids, stabilizers and colorants. Virgin product should not contain materials of unknown origin or composition.

4.2.2.2 *Grade 2: Recycled/Regrind UHMW-PE*—UHMW-PE solid plastic shapes are made using any amount up to 100 percent of recycled, or regrind UHMW-PE plastic, or both.

**TABLE A Additional Requirements for UHMW-PE Solid Plastic Shapes**

NOTE—The values listed in Table A are minimum values.

Designation Order Number	Property	0	1	9
1	Izod impact, Test Method for D 4020, min KJ/m <sup>2</sup> (ft-lbs/in. <sup>2</sup> )	Unspecified	30 (14)	Specify value
2	Elongational stress, Test Method for ISO 11542-2 (Annex 1), min, MPa	Unspecified	>0.20	Specify value
3	Elongation at break, Test Method for D 638, %, min	Unspecified	200	Specify value
4	To be determined	...	...	...


**4.3 Property Tables:**

4.3.1 Table S-UHMW-PE may be used to describe UHMW-PE solid plastic shapes.

4.3.2 To facilitate the incorporation of future UHMW-PE or special UHMW-PE formulations not covered by Table A, the “as specified” category (00) for grade is shown on the table with the basic properties to be obtained from Table S-UHMW-PE, as they apply.

4.4 *Callout Designation*—A one-line system shall be used to specify polyethylene materials covered by this specification.

4.4.1 The system uses pre-defined cells to refer to specific aspects of this specification as illustrated below in Examples 1–3:

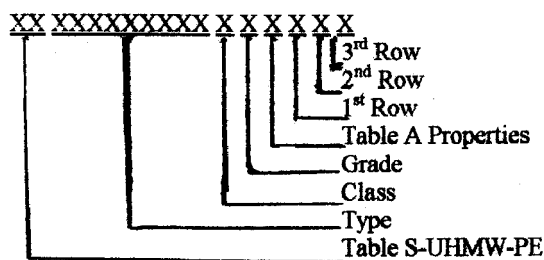

**FIG. 1 Callout Designation Layout**

4.4.2 *Example 1*—Product made from virgin Type UHMW-PE resin.

CELL CALLOUT: S-UHMW-PE0111

where:

S-UHMW-PE01 = product made from general purpose resin per Table S-UHMW-PE,

1 = unfilled class, and  
1 = general purpose.

4.4.3 *Example 2*—Product made using virgin resin, or regrind/recycled UHMW-PE, or both, with an Izod impact 30 kJ/m<sup>2</sup>(14 ft-lb/m<sup>2</sup>), minimum and elongation at break more than 200 %.

CELL CALLOUT: S-UHMW-PE0112A101

where:

S-UHMW-PE01 = product made from general purpose resin per Table S-UHMW-PE,

1 = unfilled class,  
2 = product made using virgin resin, or reprocessed/recycled UHMW-PE, or both, per Table S-UHMW-PE,

A = Table A properties,  
1 = Izod impact, 30 kJ/m<sup>2</sup> (14 ft-lb/in.<sup>2</sup>), min,

0 = unspecified, and  
1 = elongation at break, 200 %, min.

4.4.4 *Example 3*—Product made using virgin UHMW-PE resin and having an Izod impact strength of 105 kJ/m<sup>2</sup> (50 ft-lb/in.<sup>2</sup>).

CELL CALLOUT: S-UHMW-PE0101A911PX105

where:

S-UHMW-PE01	= product made from virgin resin per Table S-UHMW-PE,
0	= as specified,
1	= general purpose,
A	= Table A properties,
9	= specify value,
1	= elongational stress $\geq 0.2$ (MPa),
1	= elongation at break, 200 %,
PX	= D 4020 suffix P, and
105	= 105 kJ/m <sup>2</sup> (50 ft-lb/in. <sup>2</sup> ) (for 9 above).

4.4.5 The three examples illustrate how a one-line, alpha-numeric sequence can identify the product composition, commercial parameters and physical characteristics of UHMW-PE sheet and rod product.

## 5. Physical Property Requirements

5.1 The data listed within this specification's tables are to be considered minimum values. Any requirement for specific test data for a given production lot should be specified at the time of order. All physical property data listed in Table S-UHMW-PE shall be provided by the supplier of the solid plastic shapes on demand. Physical property data for products not yet included in Table S-UHMW-PE may be specified using Table A for UHMW-PE solid plastic shapes.

## 6. Dimensional Requirements

6.1 Products shall be supplied in the unfinished condition, unless otherwise specified at the time of order, sufficient to finish to the nominal dimension ordered.

## 7. Workmanship, Finish, and Appearance

7.1 *Appearance*—The color of products shall be as published by the manufacturer, within commercial tolerances. They shall be uniform in color throughout the thickness. Specific colors and color matching only as agreed to by order. Physical properties may be affected by colors.

7.2 *Finish*—All products shall have a finish consistent with current manufacturing processes.

## 8. Sampling

8.1 Sampling shall be statistically adequate to satisfy the requirements of this standard.

## 9. Number of Tests

9.1 The criteria listed in these product tables and definitions are sufficient to establish conformity of the sheet to this specification. When the number of test specimens is not stated in the test method, single determination may be made. If more than single determinations and separate portions of the same sample are made, the results shall be averaged. The final result shall conform to the requirements prescribed in this specification.

## 10. Test Conditions

10.1 *Conditioning of Specimens*—The specification values and dimensions are based on conditioning techniques outlined in Practice D 618 Procedure A.

10.2 *Testing of Specimens*—The tests shall be conducted at the standard laboratory conditions at (23°C  $\pm$  2°C).

## 11. Test Methods

11.1 Elongation at break per Test Method D 638, at the rate of 2.0 in./min  $\pm$  10 %.

11.2 Izod impact per Specification D 4020, ¼-in. thick specimen.

11.3 Elongational stress per ISO 11542-2.

## 12. Certification

12.1 When requested at the time of order, the purchaser shall be furnished a certification that the lot is made from UHMW-PE plastic and meets the requirements of this standard.

## 13. Packing, Packaging and Marking

13.1 All packing, packaging, and marking provisions of Practice D 3892 shall apply to this specification.

## 14. Ordering Information

14.1 All solid plastic shapes that are covered by this standard shall be ordered using the proper callout designation (see 4.4).

## 15. Keywords

15.1 recycled UHMW-PE; reprocessed UHMW-PE; sheet UHMW-PE

*ASTM International takes no position respecting the validity of any patent rights asserted in connection with any item mentioned in this standard. Users of this standard are expressly advised that determination of the validity of any such patent rights, and the risk of infringement of such rights, are entirely their own responsibility.*

*This standard is subject to revision at any time by the responsible technical committee and must be reviewed every five years and if not revised, either reapproved or withdrawn. Your comments are invited either for revision of this standard or for additional standards and should be addressed to ASTM International Headquarters. Your comments will receive careful consideration at a meeting of the responsible technical committee, which you may attend. If you feel that your comments have not received a fair hearing you should make your views known to the ASTM Committee on Standards, at the address shown below.*

*This standard is copyrighted by ASTM International, 100 Barr Harbor Drive, PO Box C700, West Conshohocken, PA 19428-2959, United States. Individual reprints (single or multiple copies) of this standard may be obtained by contacting ASTM at the above address or at 610-832-9585 (phone), 610-832-9555 (fax), or service@astm.org (e-mail); or through the ASTM website (www.astm.org).*