



Standard Classification for Rubber Compounding Materials—Antidegradents¹

This standard is issued under the fixed designation D 4676; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon (ϵ) indicates an editorial change since the last revision or reapproval.

1. Scope

1.1 This document classifies and describes antidegradants used in rubber and where appropriate defines their important chemical and physical characteristics for use in rubber.

1.2 The general term “antidegradant” describes materials used in rubber to protect against the effects of oxygen and ozone. Materials that fall in this general category include both antioxidants and antiozonants.

1.3 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.*

2. Referenced Documents

2.1 ASTM Standards:

- D 1218 Test Method for Refractive Index and Refractive Dispersion of Hydrocarbon Liquids²
- D 1519 Test Method for Rubber Chemicals—Melting Range³
- D 1747 Test Method for Refractive Index of Viscous Materials²
- D 2702 Practice for Rubber Chemicals—Determination of Infrared Absorption Characteristics³
- D 3461 Test Method for Softening Point of Asphalt and Pitch (Mettler Cup-and-Ball Method)⁴
- D 4571 Test Methods for Rubber Chemicals—Determination of Volatile Material³
- D 4574 Test Methods for Rubber Chemicals—Determination of Ash Content³
- D 4937 Test Method for *p*-Phenylenediamine Antidegradants—Purity by Gas Chromatography³
- D 5376 Test Method for Rubber Chemicals—Determination of the Percent Nitrogen in Rubber Antioxidant: Polymerized TMQ³

¹ This classification is under the jurisdiction of ASTM Committee D-11 on Rubber and is the direct responsibility of Subcommittee D11.20 on Compounding Materials and Procedures.

Current edition approved Feb. 15, 1994. Published May 1994. Originally published as D 4676 – 87. Last previous edition D 4676 – 87.

² *Annual Book of ASTM Standards*, Vol 05.01.

³ *Annual Book of ASTM Standards*, Vol 09.01.

⁴ *Annual Book of ASTM Standards*, Vol 04.04.

E 28 Test Method for Softening Point by Ring-and-Ball Apparatus⁵

3. Significance and Use

3.1 There are many different antidegradants available for use in the rubber industry.

3.2 This classification of the various materials covers their chemical structure along with a brief reference to their overall use and their properties.

4. Basis of Classification

4.1 Rubber antidegradants included in this classification document are divided into the six classes shown below. The classification in general is based on the chemical structure categorization but in most cases it also classifies the materials according to their potential rubber applications.

4.2 *Class 1, p-Phenylenediamines (PPDs)*—This group of additives represents the primary materials used in tires and other mechanical goods to impart ozone protection. These additives are also used as antioxidants and antiflex agents in a number of applications but are considered to be strongly staining and thus limited to black rubber applications. They can also be used as raw polymer stabilizers.

4.2.1 Although all PPDs have similar performance characteristics, the different types are frequently preferred for certain end use conditions; for example, selection is based on the type and degree of flexing to be experienced by the rubber article.

4.3 *Class 2, Trimethyl-dihydroquinolines (TMQs)*—These materials are primarily used to protect rubber articles from degradation by atmospheric oxygen at higher temperatures. They are moderately staining.

4.3.1 Although all TMQs have similar performance characteristics, different types are frequently preferred to accommodate processing or end use needs.

4.4 *Class 3, Phenolics*—Phenolic antidegradants represent a group of “nonstaining” and “nondiscoloring” additives used primarily in light colored mechanical goods and tires. They can also be employed as raw polymer stabilizers. The term “non-discoloring” is used somewhat loosely, as products yielding slight discoloration are included in this classification. This is done to distinguish them from the strongly staining and discoloring amine type antidegradants (for example, PPDs).

4.4.1 The different types of phenolic antidegradant afford varying degrees of protection against oxidation, heat aging,

⁵ *Annual Book of ASTM Standards*, Vol 06.03.

rubber“ poisons,” and crazing. In general they are weaker antioxidants than the staining amines types.

4.5 *Class 4, Alkylated Diphenylamines (DPAs)*—This class of additives is generally considered representative of substituted amine antioxidants and they are used as raw polymer stabilizers and in vulcanizate applications. They are moderately discoloring and staining.

4.6 *Class 5, Aromatic Phosphites*—These are phosphorous containing fully nonstaining-nondiscoloring additives used as stabilizers for synthetic elastomers in “white rubber” applications. They also have application as peroxide decomposers and radical traps in many polymer systems.

4.7 *Class 6, Diphenylamine-Ketone Condensates*—This group of additives is used primarily in carbon black loaded compounds to protect against both oxygen and heat deterioration.

5. Basic Description of Antidegradants

5.1 *p-Phenylenediamines*—The individual materials in the class of compounds designated as *p*-phenylenediamines vary in chemical structure and in performance characteristics depending on the substitution on the nitrogen atoms in the parent compound, *p*-phenylenediamine. The three general types of PPDs used in rubber are defined below:

5.1.1 *PPD Type I: N,N'-dialkyl-p-phenylenediamines* (see Fig. 1)—*R* and *R*₁ are secondary alkyl groups, usually C6 or larger. These additives are generally liquids at ambient conditions and represent single chemical components (>90 %).

5.1.2 *PPD Type II: N-alkyl-N'-aryl-p-phenylenediamines* (see Fig. 2)—*R* is a secondary alkyl group and *R*₁ is hydrogen or a primary alkyl substituent (usually methyl). These products generally consist of a single component or purposeful mixture of two or more major components. They can be either liquids or solids.

5.1.3 *PPD Type III: N,N'-diaryl-p-phenylenediamines* (see Fig. 3)—*R* and *R*₁ can be the same or different groups consisting of hydrogen or alkyl groups (usually methyl). Therefore, this type can be individual components or mixtures of three or more isomers. This type of PPD is generally solid at ambient conditions.

5.2 *Trimethyl-dihydroquinolines*—Compounds designated as TMQs represent a group of antidegradants based on polymerized aniline-acetone condensation products. The individual products differ by the degree of polymerization as well as the ratio of aniline to acetone in the monomer preparation.

5.2.1 Since these products are complex mixtures they are best described with chemical reactions (see Fig. 4).

5.2.2 The generally accepted chemical structure for TMQ oligomers (polymers) is given in Fig. 5.

5.2.3 Alternate structures may also be present containing aniline end groups or acetone bridges, or both, as shown in Fig. 6.

5.2.4 Other complex structures are also present in all TMQ products. The precise nature of the oligomeric mixture is a




FIG. 1 Type I—N,N'-dialkyl-*p*-phenylenediamines




FIG. 2 Type II—N-alkyl-N'-aryl-*p*-phenylenediamines




FIG. 3 Type III—N,N'-diaryl-*p*-phenylenediamines


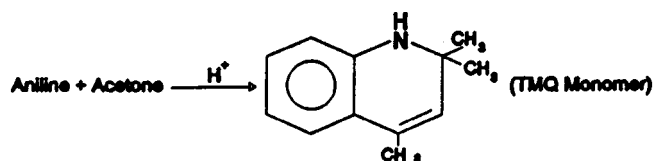


FIG. 4 TMQ Chemistry

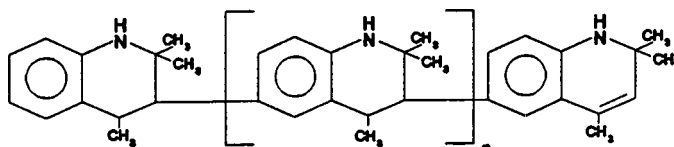


FIG. 5 TMQ Oligomeric Structure




FIG. 6 TMQ Oligomers with Aniline End Groups and an Acetone Bridge

function of the monomer preparation conditions, monomer purification, and polymerization conditions.

5.3 *Phenolics*—Phenolic antioxidants are classified chemically according to the number of phenolic groups in the molecule. In general the more sterically hindered phenolic antioxidants are less discoloring but have lower antioxidant activity in rubber applications.

5.3.1 *Monofunctional phenols (Type I)* are frequently referred to as hindered phenols. They develop little discoloration however they show the weakest antioxidant activity and are relatively volatile due to the low molecular mass. Their primary use is as polymer stabilizers. In the general structure (see Fig. 7), *R*₁, *R*₂, and *R*₃ can be hydrogen, alkyl, aryl, aralkyl or thioalkyl groups, or a combination thereof. These groups may also contain carboxylic acid esters, thioesters, or triazine functions.

5.3.2 *Bifunctional phenols (Type II)* are also referred to as hindered bisphenols. They represent the most important class




FIG. 7 Type I Phenolic Antioxidants

of phenolic antioxidants used in rubber applications. In general they have good antioxidant activity with minimal discoloration. In the general structure (see Fig. 8 and Fig. 9), the *R* groups are normally located in the “ortho” or “para” position in relation to the phenol function. *R* is generally alkylidene (methylene) or thio. *R*₁, *R*₂, *R*₃, and *R*₄ can be hydrogen, alkyl, aryl, aralkyl or thioalkyl groups, or a combination thereof. The “ortho” bridged structures (Fig. 8) are commonly used in rubber.

5.3.3 *Multifunctional phenols (Type III)* are similar to the bifunctional phenols in activity and discoloration but are more persistent in the end use product due to higher molecular mass and lower volatility. In the generalized structure (see Fig. 10 and Fig. 11), the *R* groups are defined in 5.3.2. The substitution is also normally in the “ortho” and “para” positions relative to the phenol group.

5.4 *Alkylated Diphenylamines*—These antioxidants are complex reaction products of diphenylamine and various alkylating agents. The substituents are selected to achieve a desired balance of cost and performance characteristics. In the general structure (see Fig. 12) *R* can be hydrogen, alkyl, or aralkyl groups. There can be multiple substituents on either or both rings. Alternate structures also have substituents on the nitrogen atom.

5.5 *Aromatic Phosphites*—Aromatic phosphites are phosphorous esters of aromatic phenols. In the general structure (see Fig. 13) the *R* groups can be hydrogen, alkyl, aryl, or aralkyl.

5.6 *Diphenylamine-Ketone Condensates*—These antioxidants are complex reaction products of diphenylamine and alkyl ketones, primarily acetone (see Fig. 14), some of which are further condensed with formaldehyde producing products of high molecular weight. They are low melting resins or liquids, essentially non-volatile and readily dispersible in rubber.

6. Composition and Properties

6.1 The important properties and characteristics of anti-degradants vary with anti-degradant class and intended application. Those composition and property characteristics listed below are judged to be more significant for one or more of the classes or individual types of anti-degradants being considered.

6.2 *Purity of Assay*—Even though performance is not directly related to chemical purity a measurement of purity is generally specified for those anti-degradants used in high performance applications. This parameter is particularly applicable to those anti-degradants that represent individual (or a defined number) of specific chemical entities; that is, PPDs and most phenolics.

6.2.1 PPD purity should be determined according to a gas chromatographic method defined in Test Method D 4937.

6.2.2 The purity of phenolic antioxidants can be determined by various chromatographic techniques including gas chroma-




FIG. 8 “Ortho” Bridged Type II Phenolic Antioxidants

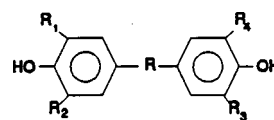


FIG. 9 “Para” Bridged Type II Phenolic Antioxidants




FIG. 10 “Ortho” Bridged Type III Phenolic Antioxidants




FIG. 11 “Para” Bridged Type III Phenolic Antioxidants




FIG. 12 Alkylated Diphenylamine General Structure




FIG. 13 Aromatic Phosphites General Structure

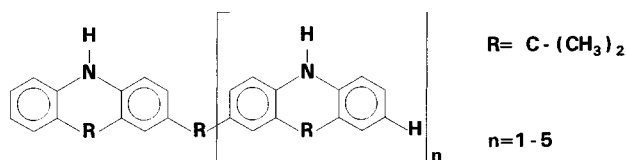


FIG. 14 Diphenylamine-Ketone Condensate General Structure

tography (GC) and high pressure liquid chromatography (HPLC). ASTM methods specific to these materials have not yet been developed. The melting point of solids (Test Method D 1519) and the refractive index of liquids (Test Methods D 1218 and D 1747) are often used as an indicator of purity.

6.2.3 Since TMQs, alkylated diphenylamines, and phosphite anti-degradants generally represent reaction mixtures rather than individual chemical entities, their quality is usually established by indirect methods. HPLC or GC techniques, or both, are being utilized to analyze these materials but ASTM procedures have not been developed.

6.2.3.1 This is accomplished for TMQs by measuring the amount of basic nitrogen by a perchloric acid titration (Test Method D 5376). This indirectly defines the relative proportion of reactants in the mixed product.

6.2.3.2 The relative purity of the complex alkylated diphenylamines can be assessed by comparison of the ultraviolet spectrum with that of standard or reference materials.

6.2.3.3 The relative purity of mixed aromatic phosphites can best be established from the infrared (IR) spectrum obtained according to Practice D 2702. Comparison of the spectra with standard or reference materials is required to obtain a quality parameter.

6.2.3.4 Melting range gives an indication of the diphenylamine-ketone condensate type and relative molecular weight within types. The infrared spectrum also is an indicator of antidegradant type.

6.3 *Volatile Materials* (including moisture) in anti-degradants can be important in some end use applications. A method for this determination in PPDs is given in Test Method D 4571.

6.4 *Ash Content*—The presence of ash or noncombustibles in antidegradants is important for applications where inorganic residues in the rubber compound would present an end use problem (undissolved or undispersed inorganics in rubber formulations could initiate flaws). Ash measurement on PPDs is described in Test Methods D 4574. This methodology could be adapted to the other antidegradant classes.

6.5 *Softening Point*—This parameter has typically been used to characterize TMQ antidegradants since these materials are generally not crystalline solids. The softening point is

indicative of the degree of TMQ oligomerization. The determination can be done according to Test Method D 3461 or with Test Method E 28.

6.6 *Hydrolysis Stability*—One particularly important characteristic of aromatic phosphite antioxidants is their relative resistance to hydrolysis, since these materials are typically added as aqueous emulsions. The hydrolysis is acid catalyzed; thus a neutral pH of the aqueous emulsion is required for good stability. The relative rate of phosphite hydrolysis can also be directly monitored by using an appropriate analytical tool to determine acidic hydrolysis products or free alkylated phenols.

7. Keywords

7.1 alkylated diphenylamines; antidegradants; antioxidants; antiozonants; aromatic phosphites; diphenylamine-ketone condensates; phenolics; *p*-phenylenediamines; trimethyl-dihydroquinolines

The American Society for Testing and Materials takes no position respecting the validity of any patent rights asserted in connection with any item mentioned in this standard. Users of this standard are expressly advised that determination of the validity of any such patent rights, and the risk of infringement of such rights, are entirely their own responsibility.

This standard is subject to revision at any time by the responsible technical committee and must be reviewed every five years and if not revised, either reapproved or withdrawn. Your comments are invited either for revision of this standard or for additional standards and should be addressed to ASTM Headquarters. Your comments will receive careful consideration at a meeting of the responsible technical committee, which you may attend. If you feel that your comments have not received a fair hearing you should make your views known to the ASTM Committee on Standards, 100 Barr Harbor Drive, West Conshohocken, PA 19428.