



Designation: D 6746 – 02a

Standard Test Method for Raw Rubber or Unvulcanized Compounds—Determination of Tensile Green Strength¹

This standard is issued under the fixed designation D 6746; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon (ϵ) indicates an editorial change since the last revision or reapproval.

1. Scope

1.1 This test method describes a method to evaluate a characteristic of raw rubber or unvulcanized rubber compounds, or both, that is designated as tensile green strength. This special strength property for uncured rubbers is an important processing performance attribute in rubber product manufacturing.

1.2 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.*

2. Referenced Documents

2.1 ASTM Standards:

D 412 Test Methods for Vulcanized Rubber and Thermoplastic Elastomers—Tension²

D 1349 Practice for Rubber—Standard Temperatures for Testing²

D 3182 Practice for Rubber—Materials, Equipment, and Procedures for Mixing Standard Compounds and Preparing Standard Vulcanized Sheets²

3. Terminology

3.1 Definitions:

3.1.1 *green strength, n*—a characteristic property of a raw or unvulcanized rubber compound that indicates the capability of retaining mechanical or structural integrity when the rubber is subjected to deformation of any type.

3.1.1.1 *Discussion*—The word “green” is a synonym for uncured or unvulcanized.

3.1.2 *tensile green strength, n*—green strength of a raw or unvulcanized rubber compound that is evaluated by the application of tensile stress or strain.

4. Summary of Test Method

4.1 The tensile stress-strain characteristics of a dumbbell or another recommended test piece of raw or unvulcanized

compounded rubber are determined on a tensile testing machine capable of maintaining a constant rate of separation of the moving jaws.

4.2 In evaluating tensile green strength, several types of stress-strain behavior may be observed, depending on the rubber and the composition of the unvulcanized compound. (See Section 5.) Fig. 1 indicates three typical stress-strain curves. Type 1 has a yield point and exhibits elongational flow beyond the yield point, culminating in rupture at a higher stress and elongation compared to the initial yield stress. Type 2 also has a yield point, but beyond this point follows a decreasing stress behavior as the maximum rupture elongation is attained. Type 3 has a stress-strain curve that is similar to cured rubbers, with no yield or elongation beyond the point of rupture at maximum stress.

5. Significance and Use

5.1 The stress-strain properties of unvulcanized rubber (either a prepared mix or in the raw state) are important to certain processing operations in the rubber industry. These unvulcanized rubber properties are frequently referred to as “tensile green strength,” denoting that the final vulcanization cycle has not yet been achieved.

5.2 Tensile green strength is determined primarily by the physical and chemical characteristics of polymers, such as molecular weight, tendency to crystallize, degree of branching, and so forth. It is also related to the compound formulation, particularly filler and plasticizer content, and the presence of peptizers. Tensile green strength can be a good indication of processing behavior. It is a particularly important characteristic for all processing operations in which elongation predominates.

5.3 Tensile green strength is dependent on the test piece preparation, rate of extension, and test temperature. Therefore, a single-point method cannot be expected to give correlation between tensile green strength and processing behavior over the whole range of processing conditions.

6. Interferences


6.1 For reliable test results, it is important that test specimens are of accurate dimensions and are free of air inclusions, blisters, and contaminants.

6.2 A defective cutting die or slippage of the test specimen


¹ This test method is under the jurisdiction of ASTM Committee D11 on Rubber and is the direct responsibility of Subcommittee D11.12 on Processability Tests.

Current edition approved June 10, 2002. Published July 2002. Originally published as D 6746–02. Last previous edition D 6746–02.


² *Annual Book of ASTM Standards*, Vol 09.01.

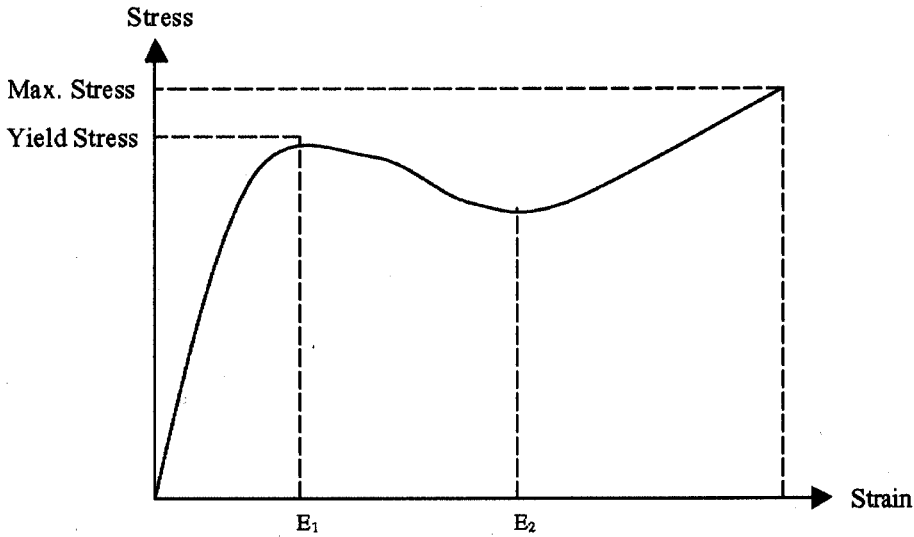

Type 1

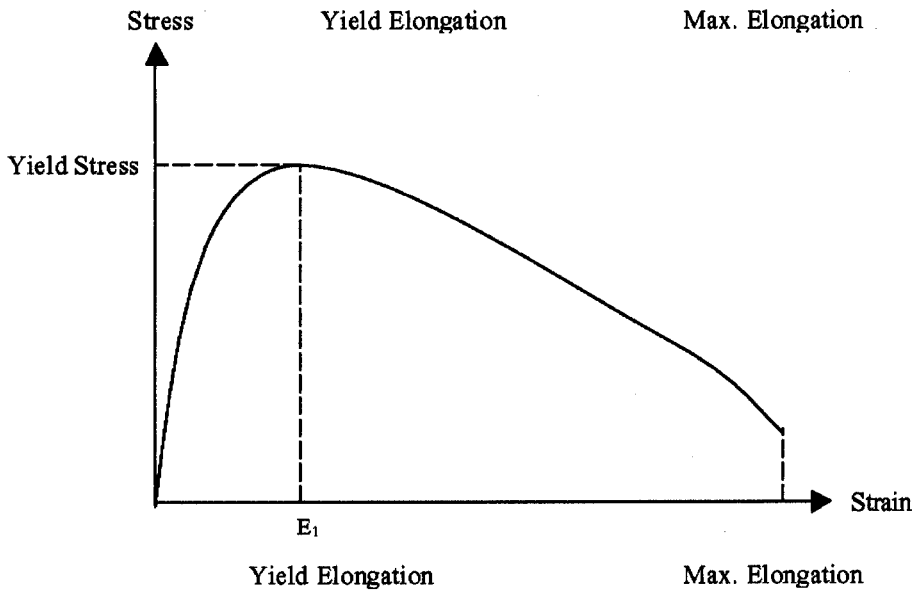

Type 2

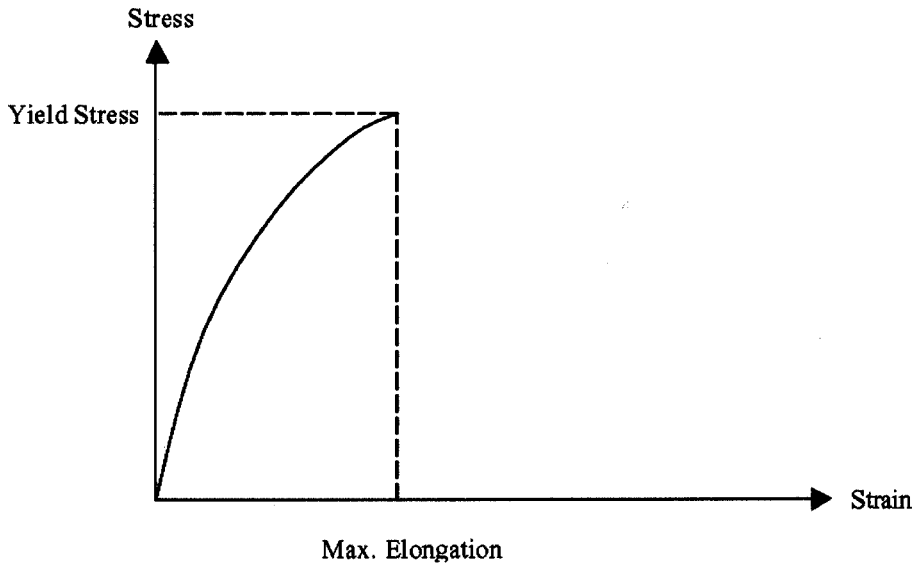

Type 3

FIG. 1 Typical Tensile Stress-Strain Curves



in the clamps may cause incorrect results.

6.3 Exposure to excessive ultraviolet radiation or chemical vapors may also affect the results.

7. Apparatus

7.1 *Tensile Testing Machine*—The tensile testing machine shall be in accordance with the requirements of Test Methods D 412. It shall be capable of maintaining a constant rate of separation of the jaws at 100 ± 10 mm/min or, for special cases, at a value within the range of 20 to 1000 mm/min. It should have means to test the force on the test piece and the elongation by the distance between the gauge marks on the dumbbell. It should be capable of recording the force/elongation curve obtained during the test. If using an automatic extensometer, a non-contacting type of extensometer is preferred.

7.2 *Mold*—The mold shall meet the requirements of Practice D 3182.

8. Hazards

8.1 There are no hazards inherent to the techniques described. Caution should be exercised and the user should be aware of any possible pinch points.

8.2 Normal safety precautions, including the use of personal protective equipment and good laboratory practice, should be observed when using any equipment. This is especially true when performing tests at elevated temperatures.

9. Test Specimen

9.1 The preferred test specimen is the dumbbell Die C specimen in accordance with Test Methods D 412. Other types of test specimens may also be used. Since surface conditions can affect the results, there may be cases where a wider specimen would be preferred, such as Die A from Test Methods D 412.

9.2 Since different types of test specimens do not necessarily give the same values, comparison of results from different specimen types should be avoided.

10. Preparation

10.1 Raw rubber and unvulcanized compounds shall be sheeted out to approximately 2.5-mm thickness and placed in the mold with the grain direction oriented so as to have the grain direction parallel with the length of the dumbbells. It is also permissible to test against the grain, but this must be noted in the report section. (See Section 15.) Only fresh stock shall be used.

10.2 Polyester film (0.05-mm thickness) shall be placed between the mold walls and the rubber in order to promote mold release. The sample shall be compressed for 5 ± 1 min at $100 \pm 2^\circ\text{C}$ under a minimum of 2.5 MPa platen pressure, allowed to cool to laboratory temperature for 30 ± 2 min under adequate pressure to keep test specimen flat, then removed. The cooling shall be done out of the press using room temperature metal plates.

10.3 For some raw rubbers, longer times or higher temperatures may be necessary in order to obtain a smooth sheet free from porosity. For some compounds, a lower temperature may be necessary when there is a danger of scorch at the preferred temperature.

10.4 A sample may also be acquired during processing by sheeting off a mill, calender, or by extrusion and then cut with a die. Special care should be taken to ensure that the sample is free of trapped air.

10.5 Cut three test specimens from the sheet, using a suitable die. (See 9.1.)

11. Calibration and Standardization

11.1 The tensile testing machine shall be calibrated according to the procedure in Test Methods D 412.

12. Conditioning

12.1 The test specimens shall be conditioned at a temperature of $23 \pm 2^\circ\text{C}$ for at least 16 h and not more than 24 h before testing.

12.2 Some slow crystallizing polymers, such as polychloroprene, may need a longer conditioning period in order to accurately measure the maximum green strength.

13. Procedure

13.1 Place the dumbbell in the grips of the testing machine in accordance with the procedure in Test Methods D 412. Adjust the rate of displacement of the moving jaw to 100 ± 10 mm/min and start the tensile test. If the sample breaks at the grips, that result shall be discarded and a retest carried out.

13.1.1 The preferred rate of separation of the jaws is 100 ± 10 mm/min. In special cases, other rates may be used, but only tests carried out at the same rate can be compared. Rollover or self-tightening grips may help prevent slippage.

13.2 The test shall be carried out on three test specimens. If the standard deviation is greater than 20 % of the mean value, then five specimens should be tested.

13.3 Unless otherwise specified, the standard test temperature shall be $23 \pm 2^\circ\text{C}$.

13.4 When it is necessary to test at other temperatures, use one of the standard temperatures listed in Practice D 1349. Specimens shall be conditioned at these test temperatures for 15 ± 2 min prior to testing.

14. Calculation or Interpretation of Results

14.1 Using the typical stress-strain curves given in Fig. 1, determine the yield stress or maximum stress in MPa. Other parameters may be determined, such as yield elongation (E_f) or the stress at a definite reference elongation corresponding to the deformation entailed by a subsequent processing operation. The median value is the preferred value to report.

14.2 Calculate the tensile stress at any specified elongation as follows:

$$T_{(xxx)} = F_{(xxx)}/A \quad (1)$$

where:

$T_{(xxx)}$ = tensile stress at (xxx) % elongation, MPa,
 $F_{(xxx)}$ = force at specified elongation, MN, and
 A = cross-sectional area of unstrained specimen, m^2 .

14.3 Calculate the yield stress as follows:

$$Y_{(stress)} = F_{(y)}/A \quad (2)$$

where:



$Y_{(stress)}$ = yield stress, that stress level where the yield point occurs, MPa,
 $F_{(y)}$ = magnitude of force at the yield point, MN, and
 A = cross-sectional area of unstrained specimen, m^2 .

14.4 Evaluate the yield strain as that strain or elongation magnitude, where the rate of change of stress with respect to strain goes through a zero value.

14.5 Calculate the elongation (at any degree of extension) as follows:

$$E = 100[L - L_{(o)}]/L_{(o)} \quad (3)$$

where:

E = the elongation in percent (of original bench mark distance),
 L = observed distance between bench marks on the extended specimen, and
 $L_{(o)}$ = original distance between bench marks (use same units for L and $L_{(o)}$).

14.6 The maximum elongation is evaluated when L is equal to the distance between benchmarks at the point of specimen rupture.

15. Report

15.1 Report the following information:

- 15.1.1 Full description of the sample and its origin,
- 15.1.2 Method of preparation of the test specimen, that is, time and temperature of molding, if not at standard conditions,
- 15.1.3 Type and dimensions of test specimen, if not a Die C dumbbell,
- 15.1.4 Grain direction, if not at the standard condition of testing with the grain,
- 15.1.5 Date of test,
- 15.1.6 Rate of extension, if not at standard conditions,
- 15.1.7 Temperature and humidity of test room, if not at standard conditions,
- 15.1.8 Time of conditioning,
- 15.1.9 Temperature of test if at other than $23 \pm 2^\circ\text{C}$,
- 15.1.10 Number of test specimens tested if not three, and
- 15.1.11 Median of all results (yield stress, maximum stress, yield elongation, maximum elongation).

16. Precision and Bias

16.1 Not yet available.

17. Keywords

17.1 green; raw rubber; rubber; tensile green strength; unvulcanized compounds

ASTM International takes no position respecting the validity of any patent rights asserted in connection with any item mentioned in this standard. Users of this standard are expressly advised that determination of the validity of any such patent rights, and the risk of infringement of such rights, are entirely their own responsibility.

This standard is subject to revision at any time by the responsible technical committee and must be reviewed every five years and if not revised, either reapproved or withdrawn. Your comments are invited either for revision of this standard or for additional standards and should be addressed to ASTM International Headquarters. Your comments will receive careful consideration at a meeting of the responsible technical committee, which you may attend. If you feel that your comments have not received a fair hearing you should make your views known to the ASTM Committee on Standards, at the address shown below.

This standard is copyrighted by ASTM International, 100 Barr Harbor Drive, PO Box C700, West Conshohocken, PA 19428-2959, United States. Individual reprints (single or multiple copies) of this standard may be obtained by contacting ASTM at the above address or at 610-832-9585 (phone), 610-832-9555 (fax), or service@astm.org (e-mail); or through the ASTM website (www.astm.org).