



# Standard Test Method for Rubber Property—Volume Resistivity Of Electrically Conductive and Antistatic Products<sup>1</sup>

This standard is issued under the fixed designation D 991; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon ( $\epsilon$ ) indicates an editorial change since the last revision or reapproval.

*This standard has been approved for use by agencies of the Department of Defense.*

<sup>ε1</sup> NOTE—Sections 4.1 and 5.2 were corrected editorially in May 2000.

## 1. Scope

1.1 This test method covers the determination of volume resistivity of rubbers used in electrically conductive and antistatic products.

1.2 This test method assumes that the surface conductivity is negligible compared to the conductivity through the specimen.

1.3 The values stated in SI units are to be regarded as the standard. The values given in parentheses are for information only.

1.4 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.*

## 2. Referenced Documents

### 2.1 ASTM Standards:

D 3182 Practice for Rubber—Materials, Equipment, and Procedures for Mixing Standard Compounds and Preparing Standard Vulcanized Sheets<sup>2</sup>

D 4483 Practice for Determining Precision for Test Method Standards in the Rubber and Carbon Black Industries<sup>2</sup>

## 3. Terminology

### 3.1 Definitions of Terms Specific to This Standard:

3.1.1 *rubber product, antistatic*—a rubber product sufficiently conductive to prevent a build-up of an electrical charge on the surface and sufficiently insulating to prevent an electrical hazard.

3.1.1.1 *Discussion*—Generally, antistatic rubber products are considered to have a resistance of  $10^4$  to  $10^8 \Omega$ .

3.1.2 *rubber product, conductive*—a rubber product having an electrical conductivity of sufficient magnitude that might be considered an electrical or thermal hazard.

<sup>1</sup> This test method is under the jurisdiction of ASTM Committee D11 on Rubber and is the direct responsibility of Subcommittee D11.10 on Physical Testing.

Current edition approved March 31, 1989. Published May 1989. Originally published as D991 – 48 T. Last previous edition D991 – 85.

<sup>2</sup> *Annual Book of ASTM Standards*, Vol 09.01.

3.1.2.1 *Discussion*—Generally, conductive rubber products are considered to have a resistance of less than  $10^4 \Omega$  at 120 V.

3.1.3 *volume resistivity*—the ratio of the electric potential gradient to the current density when the gradient is parallel to the current in the material.


## 4. Significance and Use

4.1 The electrical behavior of rubber products used in particular applications is important for a variety of reasons such as safety, static changes, current transmission, etc. This test method is useful in predicting the behavior of such rubber products.

## 5. Apparatus

5.1 *Electrode Assembly*—The electrode assembly (Fig. 1) shall consist of a rigid base made from an electrically insulating material having a resistivity greater than  $10 \text{ T}\Omega\text{-m}$  (for example, hard rubber, polyethylene, polystyrene, etc.) to which a pair of current electrodes and a pair of potential electrodes are fastened in such a manner that the four electrodes are parallel and their top surfaces are in the same horizontal plane. Another pair of current electrodes identical with the first pair shall be fastened to a second piece of insulating material so that they can be superimposed on the specimen directly above the first pair. The current electrodes shall have a length at least 10 mm (0.4 in.) greater than the specimen width, a width between 5 and 8 mm (0.2 and 0.3 in.), and a height uniform within 0.05 mm (0.002 in.) between 10 and 15 mm (0.4 and 0.6 in.). The potential electrodes shall have a length and height equal to the current electrodes and shall be tapered to an edge having a radius of 0.5 mm (0.02 in.) maximum at the top surface. The distance between the potential electrodes shall not be less than 10 mm (0.4 in.) nor more than 66 mm (2.6 in.) and shall be known within  $\pm 2\%$ . The current electrodes shall be equidistant outside the potential electrodes and separated from them by at least 20 mm (0.8 in.). The electrodes shall be made from a corrosion-resistant metal such as brass, nickel, stainless steel, etc. Insulation resistance between electrodes shall be greater than  $1 \text{ T}\Omega$ .

5.2 *Resistance-Measuring Device*—Resistance may be

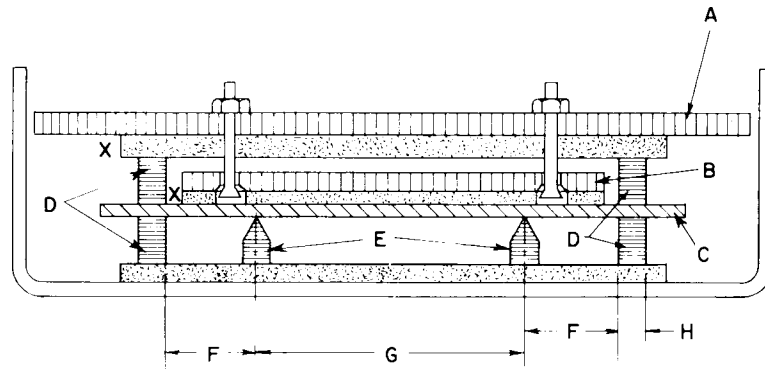

- A — Mass for applying contact force between current electrodes and specimen (300 N/m times specimen width in meters) (Note 1)
- B — Mass for applying contact force between potential electrodes and specimen (60 N/m times specimen width in meters) (Note 2)
- C — Specimen
- D — Current Electrodes
- E — Potential Electrodes

- F — Distance between current and potential electrodes (20 mm minimum)
- G — Distance between potential electrodes (see Note 2 in Section 9) depends on specimen size.
- H — Width of current electrode, 5 to 8 mm (0.2 to 0.3 in.)
- X — Insulation

NOTE 1—For a specimen 150 mm (6 in.) wide, mass is approximately 4.5 kg (10 lb).

NOTE 2—For a specimen 150 mm (6 in.) wide, mass is approximately 0.9 kg (2 lb).

FIG. 1 Electrode Assembly

measured by any electrical circuit that enables the current through the current electrodes and the potential across the potential electrodes to be measured within 2%. Suitable devices for measuring current are: (1) a precision milliammeter, or (2) potential measurement across a reference resistor (resistance value known within 2% in series with the current electrodes). Suitable devices for measuring potential are: (1) a galvanometer having a sensitivity of 1  $\mu$ A or less per scale division in a null-voltage circuit; (2) an electrostatic voltmeter having a d-c resistance greater than 19 T $\Omega$ ; or (3) an electrometer such as a multirange voltmeter having an input d-c impedance greater than 0.1 T $\Omega$  (Note 1). In any case, the current through the potential electrodes during measurement must be less than 1% of that through the current electrodes. A stable source of d-c potential shall be provided which can be adjusted to limit the power dissipated in the specimen between potential electrodes to approximately 0.1 W. Because of the large range of resistances covered by conductive and antistatic rubbers, separate equipment for measuring resistances above and below approximately 50,000  $\Omega$  is generally desirable.

NOTE 1—Schematic diagrams of a typical apparatus that have been found to be satisfactory are shown in Fig. X1.1 and Fig. X1.2.

5.3 *Electrode Contacts*—Masses shall be provided to produce a uniform contacting force across the width of the specimen of approximately 300 N/m (4.5 kg (10 lb)) on the standard sheet, 150 mm (6 in.) wide, by the current electrodes and 60 N/m (0.9 kg (2 lb)) on the standard sheet, 150 mm (6 in.) wide, by the potential electrodes.

## 6. Specimens

6.1 *Size*—The width of the specimen shall be between 10 and 150 mm (0.4 and 6 in.) and the length shall be between 70 and 150 mm (2.8 and 6 in.). The width shall be uniform within  $\pm 1\%$ . The thickness of cut specimens is specified in 6.3. Molded specimens are specially prepared as described in 6.2

and therefore have a thickness of  $2.0 \pm 0.2$  mm ( $0.08 \pm 0.008$  in.).

6.2 *Molded Specimen*—Standard sheets prepared in accordance with Practice D 3182 may be used, provided the surface of the uncured rubber is kept free of soapstone or other contamination, and the surface of the vulcanized sheet is not contaminated with mold lubricant. To avoid surface contamination and minimize distortion of specimen prior to test, sheets may be molded between sheets of moisture-sensitive cellophane, which can be readily removed after brief immersion in warm water. After removing the cellophane, the surface of the sheet should be patted dry, taking care not to bend or stretch the sheet.

6.3 *Cut Specimen*—The specimen shall be cut from a product that has not been buffed or abraded. Surfaces of the specimen shall be cleaned if necessary by rubbing with Fuller's earth and water, washing with distilled water, and drying in air. The specimen shall be uniform in thickness within  $\pm 5\%$ , not more than 6.6 mm (0.26 in.), and if possible, not less than 2 mm (0.08 in.) thick. Care shall be taken to avoid distortion of the specimen during preparation.

## 7. Conditioning

7.1 The time between vulcanization and testing shall be not less than 16 h nor more than 4 weeks for molded specimens. Products shall be tested within 2 months after receipt by the customer.

7.2 Specimens cut from products or molded specimens that have been inadvertently distorted shall be annealed in air for 3 h at  $23 \pm 2^\circ\text{C}$  ( $73.4 \pm 3.6^\circ\text{F}$ ) to remove strains or other effects of handling.

7.3 Specimens shall be conditioned for at least 16 h and tested at a temperature of  $23 \pm 2^\circ\text{C}$  ( $73.4 \pm 3.6^\circ\text{F}$ ) and a maximum relative humidity of 65%. Molded specimens can be conditioned in a desiccator. Specimens annealed at room

temperature may be stored in a closed container during the conditioning period.

**8. Procedure**

8.1 After conditioning, place the specimen in the electrode assembly, taking care to avoid flexing or distortion. The identification portion of standard sheets shall be normal to the calender grain and shall not be in contact with, nor lie between, the current electrodes.

8.2 Adjust the current through the specimen after connection to the d-c source so that the power dissipation in the specimen between potential electrodes is approximately 0.1 W. The following values should not be exceeded for the maximum current in the specimen for various potentials across the potential electrodes:

Potential	Current, mA
3	50
6	25
10	15
30	5
75	2
150	1
300	0.5

8.3 As soon as the current has stabilized, in a maximum time of 5 s, measure the potential difference across the potential electrodes and the current through the current electrodes to the nearest 1 % of the respective values.

8.4 Measure the thickness and width of the specimen.

8.5 Make the measurements on three specimens.

**9. Calculation**

9.1 Calculate the volume resistivity as follows for each specimen:

$$\rho = Vwdk/II \tag{1}$$

where:

- $\rho$  = volume resistivity,  $\Omega \cdot m$ ,
- $V$  = potential difference, V, across potential electrodes,
- $I$  = current, A, through the current electrodes,
- $w$  = width of specimen,
- $d$  = thickness of specimen,
- $l$  = distance between potential electrodes,
- $k$  = factor depending on units in which,  $w$ ,  $d$ , and  $l$  are measured; that is,  $k$  is 0.001 if  $w$ ,  $d$ , and  $l$  are in millimetres and 0.0254 if they are in inches.

NOTE 2—If  $l$  is made 64.5 mm (2.54 in.) and  $w$  and  $d$  are measured in inches, the equation becomes:

$$\rho = 0.01 Vwd/II \tag{2}$$

9.2 Report the median value for the three specimens as the volume resistivity.

**10. Report**

- 10.1 Report the following information:
  - 10.1.1 Temperature during conditioning and test,
  - 10.1.2 Relative humidity during conditioning and testing,
  - 10.1.3 Size of specimen,

- 10.1.4 Current through specimen in amperes,
- 10.1.5 Voltage across potential electrodes, and
- 10.1.6 Volume resistivity in ohm-metres, kilohm-metres, or megohm-metres.

**11. Precision and Bias <sup>3</sup>**

11.1 These precision and bias statements have been prepared in accordance with Practice D 4483. Refer to Practice D 4483 for terminology and other testing and statistical concepts.

11.2 Because of the special nature of this test and its lack of widespread use in the industry, a limited interlaboratory Type 1 test program was used to assess precision. Two materials (rubber compositions) of different volume resistivity in the form of cured sheets were prepared in one laboratory and sent to the other participating laboratory. Both laboratories were experienced in this testing.

11.3 In each laboratory the cured rubber sheets were measured for volume resistivity on two days, on each day by two different operators. The within laboratory variation, therefore, contains an “operator” and “day” component of variation.

11.4 A test result is the median value of three measurements of volume resistivity.

11.4.1 Table 1 gives the precision results. Due to the wide

**TABLE 1 Type 1 Precision for Log( $\rho$ )**

NOTE 1—Only two laboratories participated in the program for these results.

Material	Mean Level	Within Laboratory <sup>A</sup>			Between Laboratory <sup>A</sup>		
		$S_r$	$r$	( $\bar{r}$ )	$S_R$	$R$	( $\bar{R}$ )
1	3.392 <sup>B</sup>	0.065	0.184	5.4	0.329	0.931	27.4
2	4.855	0.132	0.374	7.7	0.577	1.63	33.6

- <sup>A</sup>  
 $S_r$  = within laboratory standard deviation.
- $r$  = repeatability (in measurement units).
- ( $\bar{r}$ ) = repeatability (in percent).
- $S_R$  = between laboratory standard deviation.
- $R$  = reproducibility (in measurement units).
- ( $\bar{R}$ ) = reproducibility (in percent).
- <sup>B</sup>Tabulated values (as used for analysis),  $\log_{10}(\rho)$ .

range of volume resistivity values that are possible (10–1000 fold variation) the analysis was conducted using the (base 10) logarithms of the (test result) volume resistivity,  $\rho$ .

11.4.2 The rather large between laboratory variation indicates the difficulty frequently experienced with this measurement by experienced laboratories and operators.

11.4.3 *Bias*—In test method statistical terminology, bias is the difference between an average test value and the reference or true test property value. Reference values do not exist for this test method since the value or level of the test property is exclusively defined by the test method. Bias, therefore, cannot be determined.

<sup>3</sup> Supporting data are available from ASTM Headquarters. Request RR: D11-1030.

(Nonmandatory Information)

**X1. CIRCUIT DIAGRAMS AND EXPLANATORY MATERIAL**


X1.1 With switch  $Sw_1$  closed and the milliammeter set at 0–15 mA, turn the rotary switch  $Sw_2$  to develop current with maximum values as follows:

Switch Contacts	Maximum Current, mA
1–4	15
5–6	3
7–9	1

Fine adjustment of current can be accomplished by resistances  $R_1$ ,  $R_2$ , and  $R_3$ .

X1.2 With switch  $Sw_3$  closed and rotary switch  $Sw_4$  swung

to approximate position, or one or two contacts less than  $Sw_2$ , close switch  $Sw_7$ , set  $R_7$  for minimum resistance (least sensitive position for galvanometer), and then close switch  $Sw_5$ . For null balance (zero reading on galvanometer), adjust  $R_4$ ,  $R_5$ , and  $R_6$  and increase the sensitivity of the galvanometer by increasing  $R_7$ , eventually opening switch  $Sw_7$  to eliminate  $R_7$  altogether. Close switch  $Sw_6$  to read voltage. It is desirable to limit the wattage dissipated in the sample to 0.1 W between voltage electrodes. This condition is satisfied by the product of volts times milliamperes being not greater than 100.

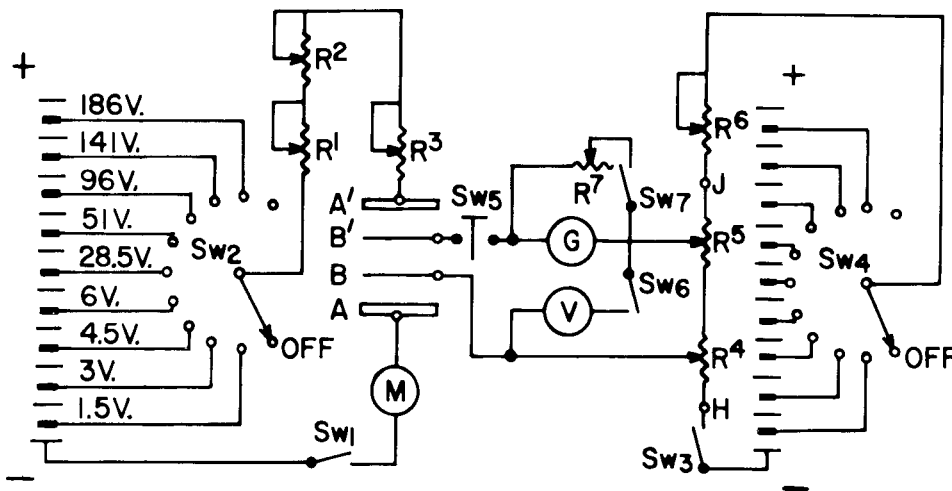


- A and A'—Current electrodes.
- B and B'—Voltage electrodes.
- $Sw_1$ ,  $Sw_3$ ,  $Sw_6$ , and  $Sw_7$ —On-off toggle switches.
- $Sw_2$  and  $Sw_4$ —Single-pole, 11-contact radio type rotary selector switches.
- $Sw_5$ —Normally open momentary contact switch.
- Source of Voltage—Two banks of dry cells each consisting of four  $1\frac{1}{2}$ -V cells, and four 45-V "B" batteries—one connected at  $22\frac{1}{2}$  V.
- M—Milliammeter, Weston D-C. Model 430, ranged 0–0.15, 1.5, 15 mA scale divisions 150; or equivalent milliammeter.
- G—Galvanometer, having a sensitivity of  $1\ \mu\text{A}$  per scale division.
- V—Voltmeter, Vacuum Tube Voltohm, Electronic Designs Model 100, Electronic Designs, Inc., New York City; or equivalent performance vacuum

- tube or solid state voltmeter. If desired, a multi-range d-c. voltmeter with a sensitivity of  $1000\ \Omega/\text{V}$  or better may be used. For protection of this voltmeter, it is suggested that a two "gang" 11-contact rotary selector switch be substituted for  $Sw_4$  and the resistance multipliers for the voltmeter be connected to the proper points on the second set of switch contacts. In this case switch  $Sw_6$  could be eliminated.
- $R_1$ ,  $R_2$ ,  $R_4$ , and  $R_6$ —2-W, 0–10 000- $\Omega$  potentiometers, Mallory wire wound or equivalent.
- $R_3$  and  $R_5$ —2-W, 0–5000- $\Omega$  potentiometers, Mallory wire wound or equivalent.
- $R_7$ —2-W, 0–3000- $\Omega$  potentiometer, Mallory wire wound or equivalent.

NOTE 1—Where it may be desirable to extend the range of this equipment, more batteries may be added. Caution must be exercised to prevent electrical shock.

**FIG. X1.1 Resistance-Measuring Device—Special Null Voltage Circuit**

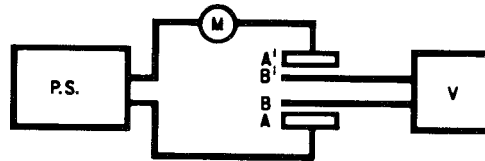

A and B — Current electrodes.

A' and B' — Voltage electrodes.

M — Milliammeter, Weston D-C. Model 430, ranged 0-0.15, 1.5, 15 mA scale divisions 150; or equivalent.

V — Voltmeter, multirange with input resistance of at least 100 M or input current of less than 1. For example, Gould Alpha IV Digital Multimeter, Keithly 616 Digital Electrometer, Penril Corp. Data Tech. Model 30L; or equivalent.

P.S. — Variable, regulated, D.C. power supply to provide up to 200 VDC. For example, EICO 1030, Hope Electronics PS-200-IEM, Kepco Inc. ABC 200M, Veepco Instruments Inc. (Lambda) LP-415-FM; or equivalent. For samples requiring under 30 volts supply voltage, a lower voltage supply such as EICO 1032 may be used.

**FIG. X1.2 Alternative Circuitry**

*The American Society for Testing and Materials takes no position respecting the validity of any patent rights asserted in connection with any item mentioned in this standard. Users of this standard are expressly advised that determination of the validity of any such patent rights, and the risk of infringement of such rights, are entirely their own responsibility.*

*This standard is subject to revision at any time by the responsible technical committee and must be reviewed every five years and if not revised, either reapproved or withdrawn. Your comments are invited either for revision of this standard or for additional standards and should be addressed to ASTM Headquarters. Your comments will receive careful consideration at a meeting of the responsible technical committee, which you may attend. If you feel that your comments have not received a fair hearing you should make your views known to the ASTM Committee on Standards, at the address shown below.*

*This standard is copyrighted by ASTM, 100 Barr Harbor Drive, PO Box C700, West Conshohocken, PA 19428-2959, United States. Individual reprints (single or multiple copies) of this standard may be obtained by contacting ASTM at the above address or at 610-832-9585 (phone), 610-832-9555 (fax), or service@astm.org (e-mail); or through the ASTM website (www.astm.org).*