



Designation: E 693 – 9401

Standard Practice for Characterizing Neutron Exposures in Iron and Low Alloy Steels in Terms of Displacements Per Atom (DPA), E 706(ID)¹

This standard is issued under the fixed designation E 693; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon (ϵ) indicates an editorial change since the last revision or reapproval.

1. Scope

1.1 This practice describes a standard procedure for characterizing neutron irradiations of iron (and low alloy steels) in terms of the exposure index displacements per atom (dpa) for iron.

1.2 Although the general procedures of this practice apply to any material for which a displacement cross section $\sigma_d(E)$ is known (see Practice E 521), this practice is written specifically for iron.

1.3 It is assumed that the displacement cross section for iron is an adequate approximation for calculating displacements in steels that are mostly iron (95 to 100 %) in radiation fields for which secondary damage processes are not important.

1.4 Procedures analogous to this one can be formulated for calculating dpa in charged particle irradiations. (See Practice E 521.)

1.5 The application of this practice requires knowledge of the total neutron fluence and ~~the neutron flux~~ flux spectrum. Refer to Practice E 521 for determining these quantities.

1.6 The correlation of radiation effects data is beyond the scope of this practice.

1.7 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.*

2. Referenced Documents

2.1 *ASTM Standards:*

¹ This practice is under the jurisdiction of ASTM Committee E10 on Nuclear Technology and Applications and is the direct responsibility of Subcommittee E10.05 on Nuclear Radiation Metrology.

Current edition approved ~~June 15, 1994~~, Jan. 10, 2001. Published ~~August 1994~~, June 2001. Originally published as E 693 – 79. Last previous edition ~~E 693 – 79 (1985)~~ ~~E 693 – 94~~.

E 170 Terminology Relating to Radiation Measurements and Dosimetry²

E 521 Practice for Neutron Radiation Damage Simulation by Charged-Particle Irradiation²

E 560 Practice for Extrapolating Reactor Vessel Surveillance Dosimetry Results, E 706 (IC)²

E 853²¹ Practice for Measurement of Mechanical Properties During Charged-Particle Irradiation²

E 853 Practice for Analysis and Interpretation of Light-Water Reactor Surveillance Results, E 706 (IA)²

3. Terminology

3.1 Definitions for terms used in this practice can be found in Terminology E 170.

4. Significance and Use

4.1 A pressure vessel surveillance program requires a methodology for relating radiation-induced changes in materials exposed in accelerated surveillance locations to the condition of the pressure vessel (see Practices E 560 and E 853). An important consideration is that the irradiation exposures be expressed in a unit that is physically related to the damage mechanisms.

4.2 A major source of neutron radiation damage in metals is the displacement of atoms from their normal lattice sites. Hence, an appropriate damage exposure index is the number of times, on the average, that an atom has been displaced during an irradiation. This can be expressed as the total number of displaced atoms per unit volume, per unit mass, or per atom of the material. Displacements per atom is the most common way of expressing this quantity. The number of dpa associated with a particular irradiation depends on the amount of energy deposited in the material by the neutrons, and hence, depends on the neutron spectrum. (For a more extended discussion, see Practice E 521.)

4.3 No simple correspondence exists in general between dpa and a particular change in a material property. A reasonable starting point, however, for relative correlations of property changes produced in different neutron spectra is the dpa value associated with each environment. That is, the dpa values themselves provide a spectrum-sensitive index that may be a useful correlation parameter, or some function of the dpa values may affect correlation.

4.4 Since dpa is a construct that depends on a model of the neutron interaction processes in the material lattice, as well as the cross section (probability) for each of these processes, the value of dpa would be different if improved models or cross sections are used. The calculated dpa cross section for ferritic iron, as given in this practice, is determined by the procedure given in 6.3. This dpa cross section has been used as a neutron exposure parameter for reporting a **A** considerable body of irradiated materials data. Therefore, data has been reported using dpa cross sections based on the iron ENDF/B-IV **(1, 2)**³ cross section. The recent changes in the iron cross section ~~has not been~~ **(3)**, the recommendation to use the updated iron cross sections in radiation transport calculations of pressure vessel spectra **(4)**, and the recent availability of ENDF/B-VI iron dpa cross section calculations **(1, 2, 5)** have resulted in the update of the recommended dpa cross section to reflect ~~model or~~ the ENDF/B-VI cross sections **(1)**. Although the ENDF/B-VI based dpa cross section differs from the previously recommended ENDF/B-IV dpa cross section **(1)** by about 60 % in the energy region around 10 keV, by about 10 % for energies between 100 keV and 2 MeV, and by a factor of 4 near 1 keV due to the opening of reaction channels in the cross section, the integral iron dpa values are much less sensitive to the change in cross sections. The update from ENDF/B-IV to ENDF/B-VI dpa rates when applied to the H. B. Robinson-2 pressurized water reactor results in “up to ~4 % higher dpa rates in the region close to the pressure vessel outer surface” and in “slightly lower dpa rates ... close to the pressure vessel inner wall” **(6, 7)**. Thus the update of the recommended dpa exposure parameter to reflect an iron cross section is justified pending improved damage theories consistent with that can determine exposure parameters that do correspond used in the current radiation transport calculations is “not expected to introduce a bias in embrittlement data bases” **(6)** based on the change in the dpa cross section. Table 1 presents a comparison of the previous edition (Practice E 693-94) and currently recommmended dpa estimates for several neutron spectra.

5. Procedure

5.1 The displacement rate at time t is calculated as follows:

$$\text{dpa/s} = \int_0^{\infty} \sigma_d(E)\phi(E,t) dE \quad (1)$$

where:

$\sigma_d(E)$ = the displacement cross section for a particular material, and

$\phi(E,t) dE$ = the fluence rate of neutrons in the energy interval E to $E + dE$.

5.2 The exposure index, dpa, is then the time integrated value of the displacement rate, calculated as follows:

$$\text{dpa} = \int_0^{t_r} \phi_{\text{tot}}(t) \int_0^{\infty} \sigma_d(E)\phi(E,t) dE dt \quad (2)$$

² Annual Book of ASTM Standards, Vol 12.02.

³ The boldface numbers in parentheses refer to the list of references appended to this practice.

TABLE 1 Changes in Spectrum-Integrated dpa for Benchmark Neutron Spectra

Neutron Spectrum	Spectrum-averaged dpa cross section (barns) ^A		
	"Old" ENDF/B-IV-based E 693 response	"Current" ENDF/B-VI-based E 693 response	Difference ((Current - Old)/ Old) (%)
ENDF/B-VI ²³⁵ U Thermal Fission (1, 2)	875.55	858.54	-1.9
Materials Dosimetry Reference Facility (MDRF) (8)	345.03	343.58	-0.42
CFRMF (9, 10)	382.94	387.08	1.08
Intermediate-energy Standard Neutron Field (ISNF) (10, 11)	483.63	480.00	-0.75
Arkansas Nuclear ONE-1 (ANO) Cavity (12, 13)	134.40	139.44	3.75
ORNL Poolside Facility (PSF) T/4 position (12, 14)	242.14	238.33	-1.57
Oak Ridge Research Reactor (ORR) (10)	291.68	288.86	-0.97
Yayoi (10)	613.12	609.03	-0.67
BIGTEN (10, 15)	334.98	341.25	1.87
H.B. Robinson-2, in the vessel wall, close to the inner surface (6, 7)	219.43	218.81	-0.28
H.B. Robinson-2, ~1/4 T vessel wall (6, 7)	245.17	249.24	1.66
H.B. Robinson-2, ~3/4 T vessel wall (6, 7)	203.68	211.23	3.71

^A The spectrum-average dpa values in this table were computed using Eq 11 in a 640 SAND-II energy group representation and a lower integration bound of E₀ = 10⁻¹⁰ MeV.

NOTE 1—Table 1 is included to illustrate the effect on the dpa cross sections resulting from the change from the ENDF/B-IV to ENDF/B-VI cross sections. The spectrum-average cross section values given are not recommended for other uses because of their sensitivity to the assumed spectrum representations and the lower energy integration limit.

where:

$\phi_{tot}(t)$ = the time dependent fluence rate intensity, and

$\psi(E,t)$ = the fluence rate spectrum normalized to give unit integral fluence rate at any time when integrated over energy.

5.2.1 If the fluence rate spectrum is constant over the duration, t_r , of the irradiation, then:

$$dpa = \phi_{tot} t_r \int_0^\infty \sigma_d(E) \psi(E) dE = \phi_{tot} t_r \bar{\sigma}_d \quad (3)$$

where $\bar{\sigma}_d$ = the spectrum-average displacement cross section.

5.3 It is assumed for purposes of this practice that the fluence $\phi_{tot} t_r$ and the spectrum $\psi(E)$ are known.

6. Calculation

6.1 The integral can be evaluated by a simple numerical integration as follows:

$$\int_0^\infty \sigma_d(E) \phi(E) dE = \sum_{i=1}^N (\sigma_d)_i \phi_i \Delta E_i \quad (4)$$

where $(\sigma_d)_i$ and ϕ_i are grouped-averaged values over the interval $E_i < E < E_{i+1}$, and ΔE_i is the width of the interval and is given by $E_{i+1} - E_i$.

6.2 The only computational problem, then, is to obtain $\sigma_d(E)$ and $\phi(E)$ in the same group structure. $\sigma_d(E)$ is available (16) in the SAND-II group structure (included here as Table 1-2), which is as fine or finer than the group structure in which $\phi(E)$ is generally available. Hence the problem is to collapse $\sigma_d(E)$ to match the $\phi(E)$ group structure.

6.2.1 If the $\phi(E)$ group structure is sufficiently fine, for example, one-quarter lethargy or less, a simple group averaging is sufficient:

$$(\sigma_d)_i = \frac{1}{\Delta E_i} \sum_{k=1}^{M_i} (\sigma_d)_{ik} \Delta E_{ik} \quad (5)$$

where M_i is the number of groups in $\sigma_d E$ between E_i and E_{i+1} , and the $\Delta E_{ik} \equiv E_{ik+1} - E_{ik}$ are the group widths.

6.2.1.1 If the ΔE_{ik} are constant (as above 1 MeV in Table 1-2), this becomes a simple average of the M_i groups in ΔE_i as follows:

$$(\sigma_d)_i = \frac{1}{M_i} \sum_{k=1}^{M_i} (\sigma_d)_{ik} \quad (6)$$

6.2.2 For a coarse group representation of $\phi(E)$, the group averages of $\sigma_d(E)$ should be weighted averages, unless such weighting has been shown to have negligible effects. The ideal weighting function is, of course, the actual spectrum $\phi(E)$. For light-water reactor applications, a generalized spectrum is often used consisting of a fission spectrum plus a low energy 1/E tail. Let the weighting spectrum be designated by $W(E)$. Then the recommended form and energy regimes are as follows:

C_1/E
E < 0.82 MeV

— $W(E)$

=

=

$$C_2 E^{1/2} e^{-E/1.4}$$

$$E \geq 0.82 \text{ MeV}$$

$$\begin{aligned} W(E) &= C_1/E & E < 0.82 \text{ MeV} \\ &= C_2 E^{1/2} e^{-E/1.4} & E \geq 0.82 \text{ MeV} \end{aligned} \tag{7}$$

The constants C_1 and C_2 are arbitrary. The group averages are then computed from the following equation:

$$(\sigma_d)_i = \frac{\sum_{k=1}^{M_i} (\sigma_d)_{ik} W(E_{ik}) \Delta E_{ik}}{\sum_{k=1}^{M_i} W(E_{ik}) \Delta E_{ik}} \tag{8}$$

$$(\sigma_d)_i = \frac{\sum_{k=1}^{M_i} (\sigma_d)_{ik} W(\hat{E}_{ik}) \Delta E_{ik}}{\sum_{k=1}^{M_i} W(\hat{E}_{ik}) \Delta E_{ik}} \tag{8}$$

where \hat{E}_{ik} = the average energy of the k^{th} group, or

$$E_{ik} \equiv (E_{ik+1} + E_{ik})/2 \tag{8}$$

$$\hat{E}_{ik} \equiv (E_{ik+1} + E_{ik})/2 \tag{9}$$

NOTE 1—This standard does not address the adequacy of the neutron group structure used for the representation and calculation of the energy dependent variations in the neutron spectrum. At positions within thick pressure vessels, Eq 8 may not provide correct results unless the energy groups, indexed by the letter i, are chosen to be adequate for representing the neutron spectrum variations.

6.2.3 It may be that the group structure of $\phi(E)$ is not a subset of the group structure of $\sigma_d(E)$; that is, none of the values of E_{ik} coincide with E_i or E_{i+1} , or both. This should pose no problem because the $\sigma_d(E)$ group structure is sufficiently fine that accurate interpolation is easily accomplished.

6.3 The recommended displacement cross section for iron $\sigma_d(E)$, is given as a function of energy in Table 1.2. The energy values chosen for the table entries are those of the SAND-II energy group structure (217). The table is a listing of energies and corresponding displacement cross sections. A graphical display of the displacement cross sections as a function of energy appears in Fig. 1. This damage energy to displacement conversion procedure is consistent with Practices E 521 and E 821 recommendations on the treatment of radiation damage by charged particles. The values of the displacement cross section are based on ENDF/B-VI (revision 5) cross sections (3)-(1, 2) as processed into dpa cross sections with the NJOY-97 code (18) using the Robinson-analytical function analytic representation (419) of the Lindhard model of energy partition between atoms and electrons (5)-(20) and the IAEA Norgett-Robinson-Torrens (NRT) recommended conversion of damage energy to displacements (621); with an effective displacement threshold energy of $E_d=40$ eV and an atomic scattering correction factor of $\beta=0.8$. The NRT displacement equation defines the number of displacements, N_d , corresponding to a given damage energy, T_d , through the equation

$$N_d(T_d) = \begin{cases} 0 & T_d < E_d \\ 1 & E_d \leq T_d < 2 E_d/\beta \\ \frac{\beta T_d}{2 E_d} & 2 E_d/\beta \leq T_d < \infty \end{cases} \tag{10}$$

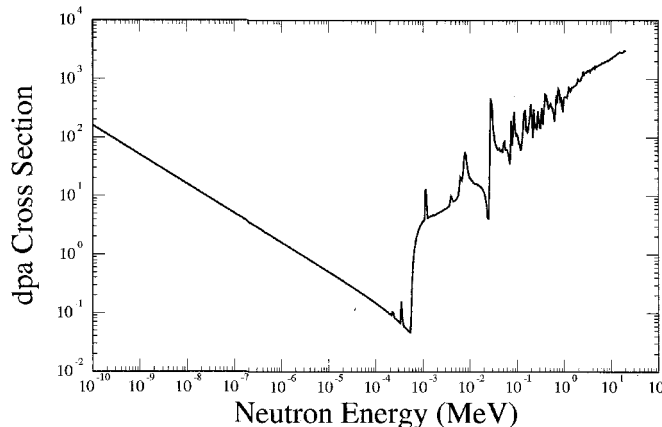


FIG. 1 ENDF/B-VI-based Iron Displacement Cross Section

NOTE 2—The iron dpa cross section combines dpa from the individual ENDF/B-VI iron isotopic evaluations using the natural iron isotopic abundance values from Ref. (722). The isotopic cross sections and relative abundances used were:

26-Fe-54, Mat = 2625, Rev. 5, tape 140; rel. abundance = 5.9 %

26-Fe-56, Mat = 2631, Rev. 1, tape 123; rel. abundance = 91.72 %

26-Fe-57, Mat = 2634, Rev. 1, tape 123; rel. abundance = 2.1 %

26-Fe-58, Mat = 2637, Rev. 5, tape 140; rel. abundance = 0.28 %

NOTE 3—Version 97.45 of the NJOY97 code used in this analysis was modified to implement the NRT displacement threshold model.

6.4 A single calculation suffices, of course, to characterize a given spectrum in terms of the spectrum-averaged displacement cross section $\bar{\sigma}_d$.

6.4.1 The quantity $\bar{\sigma}_d$ is a good measure of spectrum hardness if the thermal-to-fast ratio is not large. However, a modified- $\bar{\sigma}_d$ can be used with any thermal-to-fast ratio, if it is assumed that displacements are caused predominantly by neutrons of energies greater than E_o . Then one can define $\bar{\sigma}_d(E > E_o)$ by the following equation:

$$\sigma_d(E > E_o) = \frac{\int_{E_o}^{\infty} \sigma_d(E)\phi(E)dE}{\int_{E_o}^{\infty} \phi(E) dE} \quad (9)$$

$$\bar{\sigma}_d(E > E_o) = \frac{\int_{E_o}^{\infty} \sigma_d(E)\phi(E)dE}{\int_{E_o}^{\infty} \phi(E) dE} \quad (11)$$

and

$$\text{dpa/s} \cong \bar{\sigma}_d(E > E_o) \times \phi(E > E_o) \quad (12)$$

$$\text{dpa/s} \cong \bar{\sigma}_d(E > E_o) \times \phi(E > E_o) \quad (12)$$

A reasonable value for E_o is 0.01 MeV. The quantity $\bar{\sigma}_d(E > 0.01 \text{ MeV})$ is then a good index of spectrum hardness irrespective of the thermal-to-fast ratio.

7. Precision and Accuracy

7.1 *Precision*—For a neutron fluence spectrum, the energy group structure selected to perform the integral in a fine-group structure, 6.1 should be selected such that the precision integral of the dpa calculation exposure parameter over the neutron spectrum is estimated within 1 % of that obtained when the complete 640-group SAND-II energy structure is used to be better than 1%. For typical coarse group structures, represent the need for more group averaging energy dependence of $\sigma_d(E)$ will lead to some loss the dpa exposure parameter and the energy-dependent structure of the neutron spectrum. The precision in the spectrum-averaged dpa is dominated by the precision in the neutron spectrum characterization, including its representation of the fine energy structure.

7.2 *Accuracy*:

7.2.1 *Absolute Accuracy*—The absolute accuracy of the dpa calculation is not important when dpa is used as an exposure unit or correlation parameter for neutron irradiations, so long as a standard practice is used by all laboratories in calculating dpa. The absolute uncertainty is estimated to be 40 % or more when applied to a light water reactor spectrum (less in a softer spectrum). The major sources of error are the fluence spectrum, the reaction cross sections used in calculating $\sigma_d(E)$, the Lindhard model for the partition of energy between atoms and electrons, and the conversion of deposited energy to displacements.

7.2.2 *Relative Accuracy*—The relative accuracy of dpa calculations for different environments depends on the energy dependence of $\sigma_d(E)$ and on the relative accuracy of fluence-spectrum determinations. The covariance matrix for the iron dpa cross section is not available at present, although covariance matrices for the individual File 3 nuclear reaction cross sections which contribute to the dpa can be found in File 33 of the ENDF/B-VI cross section evaluations (1). For a discussion of the effect of the energy dependence of $\sigma_d(E)$ on the relative accuracy of the dpa calculation see Ref 723 and Practice E 521. Losses in the relative accuracy of the dpa calculation due to this effect are estimated to be less than 10 % for most reactor spectra (723). The relative accuracy of the fluence-spectrum determination depends on the method of determination. (For recommended methods see E-10.05 E 706, Matrix Standard, E-706.) Standard.) Any uncertainty in the total fluence is, of course, reflected directly in the dpa calculation (see 5.2.1).

NOTE 4—Measurement uncertainty is described by a precision-and-bias statement in this standard. Another acceptable approach is to use Type A and B uncertainty components (24, 25). This Type A/B uncertainty specification is now used in International Organization for Standardization (ISO) standards and this approach can be expected to play a more prominent role in future uncertainty analyses.

8. Damage Correlation

8.1 This practice is concerned with standardizing a radiation exposure unit. It is concerned only secondarily with the correlation of damage produced in different environments. As stated in 4.1, the dpa is a logical first step in attempting to correlate displacement damage. Active research programs on improving the damage correlation methodology are in progress, and recent results (26) indicate that dpa can, in some cases, produce improved damage correlation when compared to fast neutron fluence. Because many

past data correlations have been based on “fast fluence” ($E > 1$ MeV), this quantity should also be given, along with the dpa value, when expressing irradiation exposures. (For a general discussion of the damage correlation problem, see Ref [827](#).)

9. Keywords

9.1 atomic displacements; cross section; irradiation; materials damage; neutron; steel

TABLE 12 ENDF/B-VI-based Iron Displacement Cross-Section for Iron Section

Energy, Bin	Eng ^A MeV (MeV)	Sigma, σ_d (barns)	Bin	Eng ^A barns (MeV)	Energy, MeV σ_d (barns)	Sigma, barns Bin	Energy, MeV Eng ^A (MeV)	Sigma, barns σ_d (barns)
1	0.100E-09	158.3543	2	0.1050E-09	154.6209	3	0.110E-09	151.1395
1.000E-10	1.710E+02	1.050E-10	1.669E+02	1.100E-10	1.632E+02	1.150E-10	1.597E+02	1.200E-10
4	0.1150E-09	147.8895	5	0.120E-09	144.1054	6	0.1275E-09	139.9202
7	1.556E+02	1.275E-10	1.511E+02	0.1425E-09	132.5445	9	0.150E-09	128.7502
7	0.1350E-09	136.0860	8	0.1425E-09	132.5445	9	0.150E-09	128.7502
1.350E-10	1.470E+02	1.425E-10	1.431E+02	1.500E-10	1.391E+02	1.600E-10	1.348E+02	1.700E-10
10	0.160E-09	124.7860	11	0.170E-09	121.1728	12	0.180E-09	117.8527
13	1.309E+02	1.800E-10	1.273E+02	0.200E-09	111.9561	15	0.210E-09	109.3199
13	0.190E-09	114.8137	14	0.200E-09	111.9561	15	0.210E-09	109.3199
1.900E-10	1.240E+02	2.000E-10	1.209E+02	1.100E-10	1.180E+02	2.200E-10	1.154E+02	2.300E-10
16	0.220E-09	106.8646	17	0.230E-09	104.5694	18	0.240E-09	101.8930
19	1.129E+02	2.400E-10	1.100E+02	0.270E-09	96.65981	21	0.280E-09	94.12717
19	0.2550E-09	98.93331	20	0.270E-09	96.65981	21	0.280E-09	94.12717
2.550E-10	1.068E+02	2.700E-10	1.044E+02	1.800E-10	1.017E+02	3.000E-10	1.833E+01	3.200E-10
22	0.300E-09	91.05218	23	0.320E-09	88.24872	24	0.340E-09	85.68787
25	9.530E+01	3.400E-10	9.253E+01	0.380E-09	81.17265	27	0.400E-09	78.92472
25	0.360E-09	83.33912	26	0.380E-09	81.17265	27	0.400E-09	78.92472
3.600E-10	1.999E+01	3.800E-10	3.765E+01	1.400E-10	3.524E+01	4.250E-10	1.8276E+01	4.500E-10
28	0.4250E-09	76.63646	29	0.450E-09	74.53734	30	0.4750E-09	72.59930
34	8.049E+01	4.750E-10	7.840E+01	0.5250E-09	69.14790	33	0.550E-09	67.59222
31	0.500E-09	70.81827	32	0.5250E-09	69.14790	33	0.550E-09	67.59222
5.000E-10	1.646E+01	5.250E-10	7.466E+01	5.500E-10	7.298E+01	5.750E-10	1.7141E+01	6.000E-10
34	0.5750E-09	66.13822	35	0.600E-09	64.64189	36	0.630E-09	63.12039
37	6.980E+01	6.300E-10	6.816E+01	0.690E-09	60.37332	39	0.720E-09	58.92732
37	0.660E-09	61.70157	38	0.690E-09	60.37332	39	0.720E-09	58.92732
6.600E-10	1.662E+01	6.900E-10	6.519E+01	7.200E-10	6.364E+01	7.600E-10	1.6198E+01	8.000E-10
40	0.760E-09	57.39681	41	0.800E-09	55.97892	42	0.840E-09	54.65984
43	6.045E+01	8.400E-10	5.903E+01	0.920E-09	52.28703	45	0.960E-09	51.21545
43	0.880E-09	53.43220	44	0.920E-09	52.28703	45	0.960E-09	51.21545
8.800E-10	1.5770E+01	9.200E-10	5.646E+01	9.600E-10	5.529E+01	1.000E-09	1.5407E+01	1.050E-09
46	0.100E-08	50.07727	47	0.1050E-08	48.89598	48	0.110E-08	47.79609
49	5.279E+01	1.100E-09	5.161E+01	0.120E-08	45.57125	51	0.1275E-08	44.25006
49	0.1150E-08	46.76870	50	0.120E-08	45.57125	51	0.1275E-08	44.25006
1.150E-09	9.950E+01	1.200E-09	4.921E+01	1.275E-09	4.778E+01	1.350E-09	9.647E+01	1.425E-09
52	0.1350E-08	43.03653	53	0.1425E-08	41.91761	54	0.150E-08	40.71708
55	4.526E+01	1.500E-09	4.397E+01	0.170E-08	38.32018	57	0.180E-08	37.26968
55	0.160E-08	39.46333	56	0.170E-08	38.32018	57	0.180E-08	37.26968
1.600E-09	9.262E+01	1.700E-09	4.138E+01	1.800E-09	4.025E+01	1.900E-09	9.920E+01	2.000E-09
58	0.190E-08	36.30967	59	0.200E-08	35.40710	60	0.210E-08	34.57391
64	3.823E+01	2.100E-09	3.733E+01	0.230E-08	33.06956	63	0.240E-08	32.22424
61	0.220E-08	33.79705	62	0.230E-08	33.06956	63	0.240E-08	32.22424
2.200E-09	9.649E+01	2.300E-09	3.571E+01	2.400E-09	3.480E+01	2.550E-09	9.379E+01	2.700E-09
64	0.2550E-08	31.28942	65	0.270E-08	30.57002	66	0.280E-08	29.76999
67	3.301E+01	2.800E-09	3.215E+01	0.320E-08	27.91048	69	0.340E-08	27.10139
67	0.300E-08	28.79791	68	0.320E-08	27.91048	69	0.340E-08	27.10139
3.000E-09	9.109E+01	3.200E-09	3.014E+01	3.400E-09	2.926E+01	3.600E-09	9.846E+01	3.800E-09
70	0.360E-08	26.35879	71	0.380E-08	25.67357	72	0.400E-08	24.96309
73	2.772E+01	4.000E-09	2.695E+01	0.450E-08	23.57548	75	0.4750E-08	22.96268
73	0.4250E-08	24.23960	74	0.450E-08	23.57548	75	0.4750E-08	22.96268

TABLE 12 *Continued*

166	0.500E-06	2.257462	167	0.5250E-06	2.205331	168	0.550E-06	2.154114
169	2.364E+00	5.500E-07	170	0.600E-06	2.060134	171	0.630E-06	2.011735
169	0.5750E-06	2.108733	170	0.600E-06	2.060134	171	0.630E-06	2.011735
5.750E-07	2.258E+00	6.000E-07	2.207E+00	6.300E-07	2.155E+00	6.600E-07	2.107E+00	6.900E-07
172	0.660E-06	1.966045	173	0.690E-06	1.923586	174	0.720E-06	1.877395
175	2.064E+00	7.200E-07	2.042E+00	0.800E-06	1.783008	177	0.840E-06	1.741254
175	0.760E-06	1.828596	176	0.800E-06	1.783008	177	0.840E-06	1.741254
7.600E-07	1.960E+00	8.000E-07	1.912E+00	0.800E-07	1.866E+00	8.800E-07	1.825E+00	9.200E-07
178	0.880E-06	1.703417	179	0.920E-06	1.667792	180	0.960E-06	1.632082
181	1.785E+00	9.600E-07	1.748E+00	0.1050E-05	1.558720	183	0.110E-05	1.522295
181	0.100E-05	1.595754	182	0.1050E-05	1.558720	183	0.110E-05	1.522295
1.000E-06	0.710E+00	1.050E-06	1.669E+00	0.100E-06	1.632E+00	1.150E-06	0.597E+00	1.200E-06
184	0.1150E-05	1.490200	185	0.120E-05	1.451554	186	0.1275E-05	1.409592
187	1.556E+00	1.275E-06	1.511E+00	0.1425E-05	1.334635	189	0.150E-05	1.296298
187	0.1350E-05	1.370247	188	0.1425E-05	1.334635	189	0.150E-05	1.296298
1.350E-06	0.470E+00	1.425E-06	1.431E+00	0.1500E-06	1.391E+00	1.600E-06	0.348E+00	1.700E-06
190	0.160E-05	1.256143	191	0.170E-05	1.219824	192	0.180E-05	1.187621
193	1.309E+00	1.800E-06	1.273E+00	0.200E-05	1.126746	195	0.210E-05	1.099981
193	0.190E-05	1.156028	194	0.200E-05	1.126746	195	0.210E-05	1.099981
1.900E-06	0.240E+00	2.000E-06	1.209E+00	0.2100E-06	1.180E+00	2.200E-06	0.154E+00	2.300E-06
196	0.220E-05	1.075226	197	0.230E-05	1.051885	198	0.240E-05	1.026221
199	1.129E+00	2.400E-06	1.100E+00	0.270E-05	0.9722222	201	0.280E-05	0.9476674
199	0.2550E-05	0.9965719	200	0.270E-05	0.9722222	201	0.280E-05	0.9476671
2.550E-06	0.068E+00	2.700E-06	1.044E+00	0.2800E-06	1.017E+00	3.000E-06	0.833E-04	3.200E-06
202	0.300E-05	0.9157118	203	0.320E-05	0.8876799	204	0.340E-05	0.8611951
205	9.530E-04	3.400E-06	9.253E-04	0.380E-05	0.8153836	207	0.400E-05	0.7928756
205	0.360E-05	0.8377314	206	0.380E-05	0.8153836	207	0.400E-05	0.7928756
3.600E-06	0.999E-04	3.800E-06	8.765E-04	0.400E-06	8.524E-04	4.250E-06	0.276E-04	4.500E-06
208	0.4250E-05	0.7695923	209	0.450E-05	0.7481711	210	0.4750E-05	0.7286609
244	8.049E-04	4.750E-06	7.840E-04	0.5250E-05	0.6941600	243	0.550E-05	0.6778895
211	0.500E-05	0.7107515	212	0.5250E-05	0.6941600	213	0.550E-05	0.6778895
5.000E-06	0.764E-04	5.250E-06	7.466E-05	0.500E-06	7.298E-04	5.750E-06	0.7144E-04	6.000E-06
214	0.5750E-05	0.6635014	215	0.600E-05	0.6480775	216	0.630E-05	0.6327240
217	6.980E-04	6.300E-06	6.816E-04	0.690E-05	0.6047435	219	0.720E-05	0.5900444
217	0.660E-05	0.6182052	218	0.690E-05	0.6047435	219	0.720E-05	0.5900444
6.600E-06	0.662E-04	6.900E-06	6.519E-07	0.7200E-06	6.364E-04	7.600E-06	0.6198E-04	8.000E-06
220	0.760E-05	0.5745604	221	0.800E-05	0.5600318	222	0.840E-05	0.5467011
223	6.045E-04	8.400E-06	5.903E-04	0.920E-05	0.5232394	225	0.960E-05	0.5118709
223	0.880E-05	0.5345984	224	0.920E-05	0.5232391	225	0.960E-05	0.5118709
8.800E-06	0.5770E-04	9.200E-06	5.646E-09	0.9600E-06	5.529E-04	1.000E-05	0.5407E-04	1.050E-05
226	0.100E-04	0.5002917	227	0.1050E-04	0.4884902	228	0.110E-04	0.4769112
229	5.279E-04	1.100E-05	5.161E-04	0.120E-04	0.4543560	231	0.1275E-04	0.4409762
229	0.1150E-04	0.4666898	230	0.120E-04	0.4543560	231	0.1275E-04	0.4409762
1.150E-05	0.950E-04	1.200E-05	4.921E-04	1.275E-05	4.778E-04	1.350E-05	0.647E-04	1.425E-05
232	0.1350E-04	0.4284223	233	0.1425E-04	0.4170648	234	0.150E-04	0.4048129
235	4.526E-04	1.500E-05	4.397E-04	0.170E-04	0.3802993	237	0.180E-04	0.3699498
235	0.160E-04	0.3919477	236	0.170E-04	0.3802993	237	0.180E-04	0.3699498
1.600E-05	0.262E-04	1.700E-05	4.138E-04	0.1800E-05	4.025E-04	1.900E-05	0.920E-04	2.000E-05
238	0.190E-04	0.3598211	239	0.200E-04	0.3504475	240	0.210E-04	0.3418580
241	3.823E-04	2.100E-05	3.733E-04	0.230E-04	0.3263810	243	0.240E-04	0.3181047
241	0.220E-04	0.3339029	242	0.230E-04	0.3263810	243	0.240E-04	0.3181047
2.200E-05	0.649E-04	2.300E-05	3.571E-04	0.2400E-05	3.480E-04	2.550E-05	0.379E-04	2.700E-05
244	0.2550E-04	0.3085413	245	0.270E-04	0.3006880	246	0.280E-04	0.2927655
247	3.301E-04	2.800E-05	3.215E-04	0.320E-04	0.2733916	249	0.340E-04	0.2648267
247	0.300E-04	0.2824593	248	0.320E-04	0.2733916	249	0.340E-04	0.2648267
3.000E-05	0.109E-04	3.200E-05	3.014E-04	0.3400E-05	2.926E-04	3.600E-05	0.2846E-04	3.800E-05
250	0.360E-04	0.2572175	251	0.380E-04	0.2499703	252	0.400E-04	0.2426542
253	2.772E-04	4.000E-05	2.695E-04	0.450E-04	0.2280936	255	0.4750E-04	0.2217044
253	0.4250E-04	0.2350771	254	0.450E-04	0.2280936	255	0.4750E-04	0.2217044
4.250E-05	0.2617E-04	4.500E-05	2.545E-04	0.4750E-05	2.479E-04	5.000E-05	0.2418E-04	5.250E-05

TABLE 12 *Continued*

256	0.500E-04	0.2158471	257	0.5250E-04	0.2104036	258	0.550E-04	0.2050605	
259	2.361E-04	5.500E-05	2.308E-04	0.600E-04	0.1952700	264	0.630E-04	0.1902102	
259	0.5750E-04	0.2003403	260	0.600E-04	0.1952700	261	0.630E-04	0.1902102	
5.750E-05	2.258E-04	6.000E-05	2.207E-04	6.300E-05	2.155E-04	6.600E-05	2.107E-04	6.900E-05	0.1761094
262	0.660E-04	0.1854221	263	0.690E-04	0.1809756	264	0.720E-04	0.1761094	
265	2.061E-04	7.200E-05	266	0.900E-04	0.1661474	267	0.840E-04	0.1	
265	0.760E-04	0.1709726	266	0.800E-04	0.1661474	267	0.840E-04	0.1616956	
7.600E-05	1.960E-04	8.000E-05	1.912E-04	8.400E-05	1.866E-04	8.800E-05	1.825E-04	9.200E-05	0.1500470
268	0.880E-04	0.1576549	269	0.920E-04	0.1538460	270	0.960E-04	0.1500470	
274	1.785E-04	9.600E-05	1.748E-04	0.1050E-03	0.1421933	273	0.110E-03	0.1382971	
271	0.100E-03	0.1461601	272	0.1050E-03	0.1421933	273	0.110E-03	0.1382971	
1.000E-04	1.710E-04	1.050E-04	1.669E-04	1.100E-04	1.632E-04	1.150E-04	1.597E-04	1.200E-04	0.1261477
274	0.1150E-03	0.1348528	275	0.120E-03	0.1306799	276	0.1275E-03	0.1261477	
277	1.556E-04	1.275E-04	1.511E-04	0.1425E-03	0.1180186	279	0.150E-03	0.1138330	
277	0.1350E-03	0.1218873	278	0.1425E-03	0.1180186	279	0.150E-03	0.1138330	
1.350E-04	1.470E-04	1.425E-04	1.431E-04	1.500E-04	1.391E-04	1.600E-04	1.348E-04	1.700E-04	0.1018602
280	0.160E-03	0.1094287	281	0.170E-03	0.1054279	282	0.180E-03	0.1018602	
283	1.309E-04	1.800E-04	1.273E-04	0.200E-03	0.9515446E-04	285	0.210E-03	0.9224781E-04	
283	0.190E-03	0.9837523E-01	284	0.200E-03	0.9515446E-01	285	0.210E-03	0.9224781E-01	
1.900E-04	1.240E-04	2.900E-04	1.209E-04	2.100E-04	1.180E-04	2.200E-04	1.154E-04	2.300E-04	0.8397242E-04
286	0.220E-03	0.1048459	287	0.230E-03	0.1028288	288	0.240E-03	0.8397242E-01	
289	1.129E-04	2.400E-04	1.400E-04	0.270E-03	0.7782596E-04	294	0.280E-03	0.7506079E-04	
289	0.2550E-03	0.8057346E-01	290	0.270E-03	0.7782596E-01	291	0.280E-03	0.7506079E-01	
2.550E-04	1.068E-04	2.700E-04	1.044E-04	2.800E-04	1.017E-04	3.000E-04	0.833E-02	3.200E-04	0.1581744
292	0.300E-03	0.7147984E-01	293	0.320E-03	0.6842791E-01	294	0.340E-03	0.1581741	
295	9.530E-02	3.400E-04	9.253E-02	0.380E-03	0.6020231E-04	297	0.400E-03	0.5752645E-04	
295	0.360E-03	0.7452445E-01	296	0.380E-03	0.6020231E-01	297	0.400E-03	0.5752645E-01	
3.600E-04	3.999E-02	3.800E-04	3.765E-04	4.000E-04	3.524E-02	4.250E-04	3.276E-02	4.500E-04	0.5017326E-04
298	0.4250E-03	0.5484677E-01	299	0.450E-03	0.5239946E-01	300	0.4750E-03	0.5017326E-01	
304	8.049E-02	4.750E-04	7.840E-02	0.5250E-03	0.4750492E-04	303	0.550E-03	0.8634498E-04	
301	0.500E-03	0.4855164E-01	302	0.5250E-03	0.4750492E-01	303	0.550E-03	0.8634498E-01	
5.000E-04	7.608E-02	5.250E-04	7.354E-04	5.500E-04	9.936E-02	5.750E-04	1.535E-04	6.000E-04	1.085166
304	0.5750E-03	0.3684567	305	0.600E-03	0.7230662	306	0.630E-03	1.085166	
307	2.144E-04	6.300E-04	2.818E-04	0.690E-03	1.753764	309	0.720E-03	2.100540	
307	0.660E-03	1.433057	308	0.690E-03	1.753764	309	0.720E-03	2.100540	
6.600E-04	3.473E-04	6.900E-04	4.149E-04	7.200E-04	5.030E-04	7.600E-04	5.989E-04	8.000E-04	0.42.998771
310	0.760E-03	2.428895	311	0.800E-03	2.722788	312	0.840E-03	2.998771	
313	6.942E-04	8.400E-04	7.884E-04	0.920E-03	3.465372	315	0.960E-03	3.618973	
313	0.880E-03	3.258461	314	0.920E-03	3.465372	315	0.960E-03	3.618973	
8.800E-04	8.768E-04	9.200E-04	9.694E-04	9.600E-04	1.050E+00	1.000E-04	1.168E+00	1.050E-04	0.313.13789
316	0.100E-02	3.787081	317	0.1050E-02	3.964271	318	0.110E-02	13.13789	
319	1.334E+00	1.100E-03	1.299E+04	0.120E-02	4.262693	324	0.1275E-02	4.338387	
319	0.1150E-02	10.69382	320	0.120E-02	4.262693	321	0.1275E-02	4.338387	
1.150E-04	1.238E+04	1.200E-03	1.686E+00	1.275E-03	1.821E+00	1.360E-04	1.967E+00	1.425E-03	0.34.592575
322	0.1350E-02	4.435367	323	0.1425E-02	4.534225	324	0.150E-02	4.592575	
325	2.110E+00	1.500E-03	2.274E+00	0.170E-02	4.701623	327	0.180E-02	4.841220	
325	0.160E-02	4.783180	326	0.170E-02	4.701623	327	0.180E-02	4.841220	
1.600E-02	2.585E+00	1.700E-03	2.626E+00	1.800E-03	2.792E+00	1.900E-02	2.952E+00	2.000E-02	0.35.183993
328	0.190E-02	4.999009	329	0.200E-02	5.111335	330	0.201E-02	5.183993	
334	3.107E+00	2.100E-03	3.258E+00	0.230E-02	5.408910	333	0.240E-02	5.523736	
331	0.220E-02	5.279069	332	0.230E-02	5.408910	333	0.240E-02	5.523736	
2.200E-03	3.405E+00	2.300E-03	3.575E+00	2.400E-03	3.715E+00	2.550E-03	3.910E+00	2.700E-03	0.36.975410
334	0.2550E-02	5.695442	335	0.270E-02	5.826853	336	0.280E-02	5.975410	
337	4.068E+00	2.800E-03	4.248E+00	0.320E-02	6.395415	339	0.340E-02	6.658582	
337	0.300E-02	6.173523	338	0.320E-02	6.395415	339	0.340E-02	6.658582	
3.000E-03	1.487E+00	3.200E-03	4.734E+00	3.400E-03	4.986E+00	3.600E-03	3.5.414E+00	3.800E-03	0.39.194485
340	0.360E-02	7.183939	341	0.380E-02	10.01168	342	0.400E-02	9.194485	
343	7.472E+00	4.000E-03	6.842E+00	0.450E-02	8.229657	345	0.4750E-02	8.508525	
343	0.4250E-02	8.178266	344	0.450E-02	8.229657	345	0.4750E-02	8.508525	
4.250E-03	6.121E+00	4.500E-03	6.251E+00	1.750E-03	6.502E+00	5.000E-03	6.849E+00	5.250E-03	0.310.59739
346	0.500E-02	8.910876	347	0.5250E-02	9.525395	348	0.550E-02	10.59739	

TABLE 12 Continued

349	7.359E+00	5.500E-03	8.188E+00	0.600E-02	21.17466	351	0.630E-02	49.67340
349	0.5750E-02	13.20411	350	0.600E-02	21.17466	351	0.630E-02	19.67340
5.750E-03	0.039E+01	6.000E-03	1.731E+01	6.300E-03	1.548E+01	6.600E-03	0.438E+01	6.900E-0339.42936
352	0.660E-02	18.59203	353	0.690E-02	24.36627	354	0.720E-02	39.42936
355	1.826E+01	7.200E-03	2.993E+01	0.800E-02	48.66102	357	0.840E-02	35.11790
355	0.760E-02	56.38621	356	0.800E-02	48.66102	357	0.840E-02	35.11790
7.600E-03	0.576E+01	8.000E-03	8.840E+01	8.400E-03	2.580E+01	8.800E-03	0.924E+01	9.200E-0320.66808
358	0.880E-02	27.24892	359	0.920E-02	23.52159	360	0.960E-02	20.66808
364	1.614E+01	9.600E-03	1.422E+01	0.1050E-01	48.41869	363	0.110E-01	48.54923
361	0.100E-01	19.98392	362	0.1050E-01	18.41869	363	0.110E-01	18.51923
1.000E-02	0.308E+01	1.050E-02	1.230E+01	1.100E-02	1.191E+01	1.150E-02	0.145E+01	1.200E-0216.00651
364	0.1150E-01	16.80365	365	0.120E-01	16.40945	366	0.1275E-01	16.00651
367	1.114E+01	1.275E-02	1.086E+01	0.1425E-01	45.55876	369	0.150E-01	45.08970
367	0.1350E-01	16.06792	368	0.1425E-01	15.55876	369	0.150E-01	15.08970
1.350E-02	0.061E+01	1.425E-02	1.038E+01	1.500E-02	9.947E+00	1.600E-02	0.448E+00	1.700E-0213.21823
370	0.160E-01	14.61809	371	0.170E-01	13.99511	372	0.180E-01	13.21823
373	8.834E+00	1.800E-02	8.124E+00	0.200E-01	10.61530	375	0.210E-01	8.888706
373	0.190E-01	12.01959	374	0.200E-01	10.61530	375	0.210E-01	8.888706
1.900E-02	0.339E+00	2.000E-02	6.538E+00	2.100E-02	5.863E+00	2.200E-02	0.008E+00	2.300E-024.034283
376	0.220E-01	6.857686	377	0.230E-01	4.435299	378	0.240E-01	4.034283
379	3.605E+00	2.400E-02	3.919E+00	0.270E-01	462.4204	381	0.280E-01	374.2036
379	0.2550E-01	51.58856	380	0.270E-01	462.4204	381	0.280E-01	374.2036
2.550E-02	0.076E+01	2.700E-02	4.366E+02	2.800E-02	4.289E+02	3.000E-02	0.579E+02	3.200E-0275.21491
382	0.300E-01	138.8582	383	0.320E-01	91.99242	384	0.340E-01	75.21491
385	1.011E+02	3.400E-02	86	0.1	0611	387	E+01	
385	0.360E-01	66.92896	386	0.380E-01	62.40611	387	0.400E-01	65.56062
3.600E-02	0.140E+01	3.800E-02	6.620E+01	4.000E-02	6.275E+01	4.250E-02	0.052E+01	4.500E-0255.61853
388	0.4250E-01	59.51893	389	0.450E-01	61.42897	390	0.4750E-01	55.61853
394	5.931E+01	4.750E-02	5.932E+01	0.5250E-01	84.93746	393	0.550E-01	61.63473
391	0.500E-01	80.54994	392	0.5250E-01	84.93746	393	0.550E-01	61.63473
5.000E-02	0.029E+01	5.250E-02	8.424E+01	5.500E-02	7.094E+01	5.750E-02	0.825E+01	6.000E-0251.44463
394	0.5750E-01	61.83547	395	0.600E-01	61.39486	396	0.630E-01	51.44463
397	6.025E+01	6.300E-02	5.230E+01	0.690E-01	35.18787	399	0.720E-01	195.2115
397	0.660E-01	41.05520	398	0.690E-01	35.18787	399	0.720E-01	195.2115
6.600E-02	0.575E+01	6.900E-02	4.135E+07	7.200E-02	1.999E+02	7.600E-02	0.815E+01	8.000E-02276.0543
400	0.760E-01	72.97270	401	0.800E-01	139.3801	402	0.840E-01	276.0543
403	1.617E+02	8.400E-02	2.784E+02	0.920E-01	104.0743	405	0.960E-01	113.7160
403	0.880E-01	138.4568	404	0.920E-01	104.0743	405	0.960E-01	113.7160
8.800E-02	0.407E+02	9.200E-02	1.141E+02	9.600E-02	1.146E+02	1.000E-01	0.052E+02	1.050E-0178.06753
406	0.100	105.5489	407	0.1050	78.43095	408	0.110	78.06753
409	9.306E+01	1.100E-01	9.024E+01	0.120	70.47430	411	0.1275	134.1587
409	0.1150	60.44543	410	0.120	70.47430	411	0.1275	134.1587
1.150E-01	0.7400E+01	1.200E-01	7.067E+01	1.275E-01	1.295E+02	1.350E-01	0.2200E+02	1.425E-01133.0900
412	0.1350	255.3630	413	0.1425	293.0161	414	0.150	133.0900
415	2.531E+02	1.500E-01	1.306E+02	0.170	156.0143	417	0.180	244.4100
415	0.160	122.7596	416	0.170	156.0143	417	0.180	244.4100
1.600E-01	0.148E+02	1.700E-01	1.475E+01	1.800E-01	2.230E+02	1.900E-01	0.3249E+02	2.000E-01101.0349
418	0.190	370.7627	419	0.200	205.3339	420	0.210	101.0349
424	2.014E+02	2.100E-01	1.124E+02	0.230	146.9613	423	0.240	171.8077
421	0.220	307.5111	422	0.230	146.9613	423	0.240	171.8077
2.200E-01	0.2675E+02	2.300E-01	1.540E+02	2.400E-01	1.783E+02	2.550E-01	0.1339E+02	2.700E-01187.6945
424	0.2550	135.3387	425	0.270	282.5501	426	0.280	187.6945
427	2.411E+02	2.800E-01	1.921E+02	0.320	315.5791	429	0.340	166.5530
427	0.300	142.0391	428	0.320	315.5791	429	0.340	166.5530
3.000E-01	0.422E+02	3.200E-01	2.977E+02	3.400E-01	1.503E+02	3.600E-01	0.2917E+02	3.800E-01528.4010
430	0.360	302.1184	431	0.380	545.7117	432	0.400	528.4010
433	5.052E+02	4.000E-01	5.088E+02	0.450	309.7825	435	0.4750	351.4453
433	0.4250	400.4412	434	0.450	309.7825	435	0.4750	351.4453
4.250E-01	0.876E+02	4.500E-01	3.023E+02	4.750E-01	3.189E+02	5.000E-01	0.3643E+02	5.250E-01316.9469
436	0.500	381.0001	437	0.5250	327.4008	438	0.550	316.9469

TABLE 12 Continued

439	2.972E + 02	5.500E - 04	2.686E + 02	0.600	190.8042	441	0.630	255.5292	
439	0.5750	264.2091	440	0.600	190.8042	441	0.630	255.5292	
5.750E - 04	2.789E + 02	6.000E - 04	1.931E + 02	5.300E - 04	2.257E + 02	6.600E - 04	4.492E + 02	6.900E - 04	680.4310
442	0.660	529.8745	443	0.690	389.0167	444	0.720	680.4310	
445	3.499E + 02	7.200E - 04	6.007E + 02	0.800	427.2328	447	0.840	461.2467	
445	0.760	627.3019	446	0.800	427.2328	447	0.840	461.2467	
7.600E - 04	6.220E + 02	8.000E - 04	4.099E + 02	8.400E - 04	4.068E + 02	8.800E - 04	3.191E + 02	9.200E - 04	1479.7678
448	0.880	327.1398	449	0.920	278.1719	450	0.960	479.7678	
454	2.486E + 02	9.600E - 04	4.607E + 02	1.10	477.6893	453	1.20	707.1735	
451	1.00	498.4922	452	1.10	477.6893	453	1.20	707.1735	
1.000E + 06	5.042E + 02	1.100E + 00	4.377E + 02	1.200E + 00	6.974E + 02	1.300E + 06	5.12E + 02	1.400E + 06	10734.1659
454	1.30	616.4640	455	1.40	716.4101	456	1.50	734.1659	
457	7.855E + 02	1.500E + 00	9.153E + 02	1.70	784.5580	459	1.80	819.3325	
457	1.60	758.8353	458	1.70	784.5580	459	1.80	819.3325	
1.600E + 06	3.127E + 02	1.700E + 00	7.757E + 02	1.800E + 00	8.195E + 02	1.900E + 06	9.886E + 02	2.000E + 06	9923.3754
460	1.90	989.3265	461	2.00	928.7681	462	2.10	923.3754	
463	1.068E + 03	2.100E + 00	1.028E + 03	2.30	1079.716	465	2.40	1143.224	
463	2.20	969.4800	464	2.30	1079.716	465	2.40	1143.224	
2.200E + 06	1.006E + 03	2.300E + 00	1.096E + 03	2.400E + 00	1.214E + 03	2.500E + 06	1.373E + 03	2.600E + 06	1263.538
466	2.50	1348.954	467	2.60	1192.105	468	2.70	1263.538	
469	1.198E + 03	2.700E + 00	1.259E + 03	2.90	1271.578	471	3.00	1364.006	
469	2.80	1277.801	470	2.90	1271.578	471	3.00	1364.006	
2.800E + 06	1.275E + 03	2.900E + 00	1.265E + 03	3.000E + 00	1.365E + 03	3.100E + 06	1.389E + 03	3.200E + 06	1346.851
472	3.10	1387.724	473	3.20	1358.466	474	3.30	1346.851	
475	1.352E + 03	3.300E + 00	1.342E + 03	3.50	1334.743	477	3.60	1424.447	
475	3.40	1398.034	476	3.50	1334.743	477	3.60	1424.447	
3.400E + 06	1.395E + 03	3.500E + 00	1.330E + 03	3.600E + 00	1.434E + 03	3.700E + 06	1.457E + 03	3.800E + 06	1464.868
478	3.70	1440.708	479	3.80	1483.880	480	3.90	1464.868	
481	1.508E + 03	3.900E + 00	1.490E + 03	4.10	1560.443	483	4.20	1530.309	
481	4.00	1526.371	482	4.10	1560.443	483	4.20	1530.309	
4.000E + 06	1.556E + 03	4.100E + 00	1.595E + 03	4.200E + 00	1.562E + 03	4.300E + 06	1.615E + 03	4.400E + 06	1626.724
484	4.30	1582.916	485	4.40	1523.340	486	4.50	1626.724	
487	1.555E + 03	4.500E + 00	1.663E + 03	4.70	1617.455	489	4.80	1653.609	
487	4.60	1600.863	488	4.70	1617.455	489	4.80	1653.609	
4.600E + 06	1.643E + 03	4.700E + 00	1.676E + 03	4.800E + 00	1.719E + 03	4.900E + 06	1.705E + 03	5.000E + 06	1682.554
490	4.90	1642.833	491	5.00	1600.075	492	5.10	1682.554	
493	1.718E + 03	5.100E + 00	1.747E + 03	5.30	1716.469	495	5.40	1731.089	
493	5.20	1687.286	494	5.30	1716.469	495	5.40	1731.089	
5.200E + 06	1.752E + 03	5.300E + 00	1.785E + 03	5.400E + 00	1.793E + 03	5.500E + 06	1.792E + 03	5.600E + 06	1760.538
496	5.50	1729.785	497	5.60	1760.852	498	5.70	1760.538	
499	1.826E + 03	5.700E + 00	1.825E + 03	5.90	1792.105	501	6.00	1811.511	
499	5.80	1768.656	500	5.90	1792.105	501	6.00	1811.511	
5.800E + 06	1.830E + 03	5.900E + 00	1.851E + 03	6.000E + 00	1.872E + 03	6.100E + 06	1.862E + 03	6.200E + 06	1859.081
502	6.10	1800.940	503	6.20	1811.547	504	6.30	1859.081	
505	1.873E + 03	6.300E + 00	1.928E + 03	6.50	1879.237	507	6.60	1890.037	
505	6.40	1859.125	506	6.50	1879.237	507	6.60	1890.037	
6.400E + 06	1.927E + 03	6.500E + 00	1.948E + 03	6.600E + 00	1.958E + 03	6.700E + 06	1.964E + 03	6.800E + 06	1909.076
508	6.70	1891.762	509	6.80	1909.485	510	6.90	1909.076	
511	1.982E + 03	6.900E + 00	1.980E + 03	7.10	1936.414	513	7.20	1941.750	
511	7.00	1914.442	512	7.10	1936.414	513	7.20	1941.750	
7.000E + 06	1.987E + 03	7.100E + 00	2.010E + 03	7.200E + 00	2.010E + 03	7.300E + 06	2.040E + 03	7.400E + 06	1986.044
514	7.30	1966.663	515	7.40	1963.306	516	7.50	1986.044	
517	2.038E + 03	7.500E + 00	2.062E + 03	7.70	1989.243	519	7.80	2003.646	
517	7.60	1976.213	518	7.70	1989.243	519	7.80	2003.646	
7.600E + 06	2.052E + 03	7.700E + 00	2.068E + 03	7.800E + 00	2.085E + 03	7.900E + 06	2.089E + 03	8.000E + 06	2013.259
520	7.90	2006.771	521	8.00	2009.093	522	8.10	2013.259	
523	2.092E + 03	8.100E + 00	2.095E + 03	8.30	2064.755	525	8.40	2063.837	
523	8.20	2032.588	524	8.30	2064.755	525	8.40	2063.837	
8.200E + 06	2.117E + 03	8.300E + 00	2.150E + 03	8.400E + 00	2.150E + 03	8.500E + 06	2.146E + 03	8.600E + 06	2072.344
526	8.50	2061.365	527	8.60	2059.507	528	8.70	2072.344	

TABLE 12 Continued

529	2.143E + 03	8.700E + 00	2.163E + 03	8.90	2107.525	531	9.00	2122.580	
529	8.80	2089.976	530	8.90	2107.525	531	9.00	2122.580	
8.800E + 00	2.181E + 03	8.900E + 00	2.194E + 03	9.000E + 00	2.207E + 03	9.100E + 00	2.220E + 03	9.200E + 00	2160.074
532	9.10	2135.077	533	9.20	2147.577	534	9.30	2160.074	
535	2.232E + 03	9.300E + 00	2.245E + 03	9.50	2185.892	537	9.60	2199.950	
535	9.40	2172.482	536	9.50	2185.892	537	9.60	2199.950	
9.400E + 00	2.258E + 03	9.500E + 00	2.269E + 03	9.600E + 00	2.279E + 03	9.700E + 00	2.289E + 03	9.800E + 00	2238.281
538	9.70	2213.918	539	9.80	2226.698	540	9.90	2238.281	
544	2.299E + 03	9.900E + 00	2.308E + 03	40.40	2263.392	543	40.20	2276.220	
541	10.0	2250.482	542	10.10	2263.392	543	10.20	2276.220	
1.000E + 00	2.320E + 03	1.010E + 01	2.332E + 03	1.020E + 01	2.344E + 03	1.030E + 01	2.356E + 03	1.040E + 01	2313.910
544	10.30	2288.971	545	10.40	2301.725	546	10.50	2313.910	
547	2.369E + 03	1.050E + 01	2.381E + 03	40.70	2337.342	549	40.80	2348.869	
547	10.60	2325.628	548	10.70	2337.342	549	10.80	2348.869	
1.060E + 00	2.394E + 03	1.070E + 01	2.407E + 03	1.080E + 01	2.419E + 03	1.090E + 01	2.432E + 03	1.100E + 01	2383.112
550	10.90	2360.301	551	11.0	2371.744	552	11.10	2383.112	
553	2.444E + 03	1.110E + 01	2.455E + 03	41.30	2407.952	555	41.40	2421.344	
553	11.20	2395.212	554	11.30	2407.952	555	11.40	2421.344	
1.120E + 00	2.466E + 03	1.130E + 01	2.479E + 03	1.140E + 01	2.490E + 03	1.150E + 01	2.503E + 03	1.160E + 01	2458.956
556	11.50	2434.325	557	11.60	2446.243	558	11.70	2458.956	
559	2.514E + 03	1.170E + 01	2.524E + 03	41.90	2482.247	561	42.0	2493.659	
559	11.80	2471.205	560	11.90	2482.247	561	12.0	2493.659	
1.180E + 00	2.532E + 03	1.190E + 01	2.540E + 03	1.200E + 01	2.546E + 03	1.210E + 01	2.551E + 03	1.220E + 01	2534.971
562	12.10	2506.016	563	12.20	2519.598	564	12.30	2534.971	
565	2.556E + 03	1.230E + 01	2.567E + 03	42.50	2562.977	567	42.60	2576.115	
565	12.40	2549.086	566	12.50	2562.977	567	12.60	2576.115	
1.240E + 00	2.582E + 03	1.250E + 01	2.592E + 03	1.260E + 01	2.601E + 03	1.270E + 01	2.615E + 03	1.280E + 01	2615.468
568	12.70	2586.936	569	12.80	2600.011	570	12.90	2615.468	
571	2.629E + 03	1.290E + 01	2.642E + 03	43.40	2644.455	573	43.20	2658.475	
571	13.0	2630.343	572	13.10	2644.455	573	13.20	2658.475	
1.300E + 00	2.655E + 03	1.310E + 01	2.668E + 03	1.320E + 01	2.683E + 03	1.330E + 01	2.697E + 03	1.340E + 01	2698.683
574	13.30	2672.218	575	13.40	2685.520	576	13.50	2698.683	
577	2.713E + 03	1.350E + 01	2.730E + 03	43.70	2725.313	579	43.80	2738.112	
577	13.60	2711.990	578	13.70	2725.313	579	13.80	2738.112	
1.360E + 00	2.747E + 03	1.370E + 01	2.767E + 03	1.380E + 01	2.786E + 03	1.390E + 01	2.806E + 03	1.400E + 01	2775.980
580	13.90	2750.418	581	14.0	2763.164	582	14.10	2775.980	
583	2.824E + 03	1.410E + 01	2.840E + 03	44.30	2800.214	585	44.40	2811.915	
583	14.20	2788.331	584	14.30	2800.214	585	14.40	2811.915	
1.420E + 00	2.857E + 03	1.430E + 01	2.874E + 03	1.440E + 01	2.890E + 03	1.450E + 01	2.905E + 03	1.460E + 01	2849.781
586	14.50	2824.208	587	14.60	2837.183	588	14.70	2849.781	
589	2.917E + 03	1.470E + 01	2.929E + 03	44.90	2874.424	591	45.0	2877.552	
589	14.80	2862.184	590	14.90	2874.421	591	15.0	2877.552	
1.480E + 00	2.941E + 03	1.490E + 01	2.954E + 03	1.500E + 01	2.958E + 03	1.510E + 01	2.955E + 03	1.520E + 01	2885.147
592	15.10	2871.084	593	15.20	2864.617	594	15.30	2885.147	
595	2.952E + 03	1.530E + 01	2.948E + 03	45.50	2844.839	597	45.60	2837.641	
595	15.40	2851.581	596	15.50	2844.839	597	15.60	2837.641	
1.540E + 00	2.942E + 03	1.550E + 01	2.938E + 03	1.560E + 01	2.936E + 03	1.570E + 01	2.932E + 03	1.580E + 01	2816.329
598	15.70	2830.538	599	15.80	2823.427	600	15.90	2816.329	
604	2.928E + 03	1.590E + 01	2.924E + 03	46.10	2814.819	603	46.20	2816.344	
601	16.0	2813.386	602	16.10	2814.819	603	16.20	2816.344	
1.600E + 00	2.924E + 03	1.610E + 01	2.928E + 03	1.620E + 01	2.932E + 03	1.630E + 01	2.936E + 03	1.640E + 01	2819.920
604	16.30	2817.782	605	16.40	2819.124	606	16.50	2819.920	
607	2.940E + 03	1.650E + 01	2.944E + 03	46.70	2819.846	609	46.80	2819.725	
607	16.60	2819.883	608	16.70	2819.846	609	16.80	2819.725	
1.660E + 00	2.948E + 03	1.670E + 01	2.951E + 03	1.680E + 01	2.955E + 03	1.690E + 01	2.958E + 03	1.700E + 01	2831.455
610	16.90	2819.631	611	17.0	2823.437	612	17.10	2831.455	
613	2.966E + 03	1.710E + 01	2.978E + 03	47.30	2847.220	615	47.40	2855.056	
613	17.20	2839.475	614	17.30	2847.220	615	17.40	2855.056	
1.720E + 00	2.990E + 03	1.730E + 01	3.003E + 03	1.740E + 01	3.014E + 03	1.750E + 01	3.026E + 03	1.760E + 01	2878.960
616	17.50	2862.956	617	17.60	2870.913	618	17.70	2878.960	

TABLE 12 Continued

619	3.037E + 03	1.770E + 04	3.049E + 03	47.90	2894.594	624	48.0	2903.983
			620					
619	17.80	2886.826	620	17.90	2894.594	621	18.0	2903.983
1.780E + 03	3.064E + 03	1.790E + 04	3.073E + 03	1.800E + 04	3.087E + 03	1.810E + 03	3.102E + 03	1.820E + 01
622	18.10	2914.913	623	18.20	2925.791	624	18.30	2936.340
625	3.118E + 03	1.830E + 04	3.133E + 03	48.50	2956.448	627	48.60	2965.448
			626					
625	18.40	2946.712	626	18.50	2956.448	627	18.60	2965.448
1.840E + 03	3.149E + 03	1.850E + 04	3.164E + 03	1.860E + 04	3.180E + 03	1.870E + 03	3.195E + 03	1.880E + 01
1.900E + 03	3.239E + 03	1.910E + 04	3.249E + 03	1.920E + 04	3.259E + 03	1.930E + 03	3.269E + 03	1.940E + 01
1.960E + 03	3.300E + 03	1.970E + 04	3.310E + 03	1.980E + 04	3.320E + 03	1.990E + 03	3.334E + 03	2.000E + 01
628	18.70	2974.450	629	18.80	2983.453	630	18.90	2992.455
634	3.214E + 03	1.890E + 04	3.226E + 03	49.10	3004.583	633	49.20	3009.698
	3.279E + 03	1.950E + 04	3.289E + 03					
	3.00 E + 00		632					
631	19.0	2999.561	632	19.10	3004.583	633	19.20	3009.698
634	19.30	3014.721	635	19.40	3019.741	636	19.50	3025.406
637	19.60	3031.526	638	19.70	3037.737	639	19.80	3043.950
640	19.90	3050.161	641					

^AEnergies given are Energies represent the lower bounds of each group. Cross sections are given in units of 10^{-24}cm^2 bin boundary. The upper bin limit is 20.0 MeV

REFERENCES

- (1) McLane, V. (Ed.), *ENDF/B-6 Summary Documentation*, U. S. National Nuclear Data Center, Brookhaven National Laboratory, Upton, NY, Report BNL-NCS-17541, ENDF-102, October 1991, Supplement 1, December 1996.
- (2) Lemmel, H. D., McLaughlin, P. K., Pronyaev, V. G., *ENDF/B-VI release 5: The U.S. Evaluated Nuclear Data Library for Neutron Reaction Data*, International Atomic Energy Agency, Vienna, Austria, Report IAEA-NDS-100, Revision 8, October 1998.
- (3) Fu, C. Y., Hetrick, D. M., Perey, C. M., Perey, F. G., Larson, N. M., Larson, D. C., "Improvements in ENDF/B-VI Iron and Possible Impacts on Pressure Vessel Surveillance Dosimetry," *Proceedings of the Seventh ASTM-EURATOM Symposium on Reactor Dosimetry*, held in Strasbourg, France, August 27-31, 1990, Kluwer Academic Publishers, 1992.
- (4) *Computing Radiation Dose to Reactor Pressure Vessel and Internals: State of the Art Report*, Nuclear Energy Agency, Organization for Economic Co-Operation and Development, France, Report NEA/NSC/DOC(96)5, 1997.
- (5) Ougouag, A. M., Danjaji, M. B., Williams, J. G., Stubbins, J. F., "Neutron Displacement Damage Functions for Iron," in *Proceedings of the Seventh ASTM-EURATOM Symposium on Reactor Dosimetry*, Tsotridis, G., Dierckx, R., D'Hondt, P., Eds., Kluwer Academic Publishers, Dordrecht, 1992, pp. 729-737. This references presents ENDF/B-V updated iron dpa cross section but states that computation of ENDF/B-VI-based dpa cross sections were in progress. A private communication from these authors to Subcommittee E10.05 updating the dpa to reflect ENDF/B-VI iron cross section was received on Feb. 15, 1999.
- (6) Remec, I., White, J. E., *Development of the ENDF/B-VI Atom Displacement Cross Sections for Iron*, Oak Ridge National Laboratory, Oak Ridge, TN, Letter Report ORNL/NRC/LTR-99/4, June 1999.
- (7) Remec, I., Kam, F. B., *H. B. Robinson-2 Pressure Vessel Benchmark*, NUREG/CR-6453, ORNL/TM-13204, U. S. Regulatory Commission, 1998.
- (8) Hawari, A. I., Venkataraman, R., Fleming, R., Eisenhauer, C., Grundl, J., McGarry, E. D., "The Materials Dosimetry Reference Facility," *Reactor Dosimetry, ASTM STP 1228*, Farrar, IV, H., Lippincott, E. P., Williams, J. G., Vehar, D. W., Eds., American Society for Testing and Materials, Philadelphia, 1994.
- (9) Rogers, J. W., Millsap, D. A., Harker, Y. D., "CFRMF Neutron Field Flux Spectral Characterization," *Nuclear Technology*, Vol 25, 1975, p. 330.
- (10) Kocherov, N. P., McLaughlin, P. K., *The International Reactor Dosimetry File (IRDF-90)*, Report IAEA-NDS-141, Rev. 2, October 1993, International Atomic Energy Agency, Vienna, Austria.
- (11) Eisenhauer, C. M., Grundl, J. A., Fabry, A., "Neutron Transport Calculations for the Intermediate-Energy Standard Neutron Field (ISNF) at the National Bureau of Standards," *Proceedings International Symposium on Neutron Standards and Applications*, NBS Special Publication 493, U. S. Dept. of Commerce, Washington D.C., March 1997.
- (12) Kocherov, N. P., *Neutron Metrology File NMR-90: An Integrated Database for Performing Neutron Spectrum Adjustment Calculations*, International Atomic Energy Agency, Report IAEA-NDS-171, January 1996.
- (13) Maerker, R. E., Broadhead, B. L., Worley, B. A., "Application of the LEPRICON Unfolding Procedure to the Arkansas Nuclear One-Unit 1 Reactor," *Nuclear Science and Engineering*, Vol 93, 1986, pp. 137-170.
- (14) Maerker, R. E., *Gamma-Ray Characterization of the Two-Year Irradiation Experiment Performed at the Poolside Facility*, NUREG/CR-4039, ORNL/TM-1440, Oak Ridge National Laboratory, 1985.
- (15) *Cross Section Evaluation Working Group Benchmark Specifications*, Fast Reactor Benchmark No. 20, Report ENDF-202, BNL-19302, Brookhaven National Laboratory, Upton, NY, September 1991.
- (16) Doran, D. G., and Graves, N. J., "Neutron Displacement Damage Cross Sections for Structural Metals," *Irradiation Effects on the Microstructure and Properties of Metals*, ASTM STP 611, Am. Soc. Testing Mats., 1976, pp. 463-482.
- (217) McElroy, W. N., Berg, S., and Crockett, T., "A Computer Automated Iterative Method for Neutron Flux Spectra Determined by Foil Activation," AFWL-TR-67-4, Vols 1-4, Air Force Weapons Laboratory, 1967.
- (318) ~~Evaluated~~ MacFarlane, R. E., Muir, D. W., *The NJOY Nuclear Data File/B; Processing System, Version 91*, Los Alamos National ~~Neutron Cross Section Center, Brookhaven National Laboratory, Upton, NY, Report LA-12740-M, October 1994. Code version updated to version 97.0 in a "Readme0" memorandum by R. E. MacFarlane dated October 31, 1997. This version of the code is distributed by the Radiation Safety Information Computational Center at Oak Ridge National Laboratory as Code Package PSR-368. The code further updated to version 97.45 using~~

an update file available from the web address <http://t2.lanl.gov/codes/njoy97/>.

- (419) Robinson, M. T., "The Energy Dependence of Neutron Radiation Damage in Solids," in *Nuclear Fusion Reactor*, Proceedings of International Conference (British Nuclear Energy Society, London), 1970, pp. 364–377.
- (520) Lindhard, J., Scharff, M., and Schiøtt, H. E., "Range Concepts and Heavy Ion Ranges," *Matematisk-fysiske Meddelelser-Kongelige Danske Videnskabernes Selskab*, KDVSA, Vol 33, No. 14, 1963.
- (621) ~~"Recommendations for~~ Norgett, M. J., Robinson, M. T., Torrens, I. M., "A Proposed Method of Calculating Displacement Calculations for Reactor/Accelerator Studies in Austenitic Steel," Dose Rates," *Nuclear Engineering and Design*, Vol 33, 1975, p. 91, pp. 50.
- (722) Tuli, J. K., *Nuclear Wallet Cards*, U. S. National Nuclear Data Center, Brookhaven National Laboratory, Upton, NY, July 1990.
- (23) Doran, D. G., Parkin, D. M., and Robinson, M. T., "Damage Energy and Displacement Cross Sections: Survey and Sensitivity," CONF-761146-1, November 1976. Available from National Technical Information Service, U. S. Department of Commerce, Springfield, VA 22161.
- (824) Taylor, B. N., Kuyatt, C. E., *Guidelines for Evaluating and Expressing the Uncertainty of NIST Measurement Results*, NIST Technical Note 1297, National Institute of Standards and Technology, Gaithersburg, MD, 1994.
- (25) *Guide in the Expression of Uncertainty in Measurement*, International Organization for Standardization, 1993, ISBN 92-67-10188-9.
- (26) Stoller, R. E., Odette, G. R., "Recommendations on Damage Exposure Units for Ferritic Steel Embrittlement Correlations," *J. Nucl. Mater.* Vol 186, 1992, pp. 203–205.
- (27) Doran, D. G., Odette, G. R., Mansur, L. K., and Simons, R. L., "Damage Correlation in Theory and Practice," *Radiation Effects in Breeder Reactor Structural Materials*, M. L. Bleibert and J. W. Bennett, eds., AIME, New York, NY, 1977, p. 591.

ASTM International takes no position respecting the validity of any patent rights asserted in connection with any item mentioned in this standard. Users of this standard are expressly advised that determination of the validity of any such patent rights, and the risk of infringement of such rights, are entirely their own responsibility.

This standard is subject to revision at any time by the responsible technical committee and must be reviewed every five years and if not revised, either reapproved or withdrawn. Your comments are invited either for revision of this standard or for additional standards and should be addressed to ASTM International Headquarters. Your comments will receive careful consideration at a meeting of the responsible technical committee, which you may attend. If you feel that your comments have not received a fair hearing you should make your views known to the ASTM Committee on Standards, at the address shown below.

This standard is copyrighted by ASTM International, 100 Barr Harbor Drive, PO Box C700, West Conshohocken, PA 19428-2959, United States. Individual reprints (single or multiple copies) of this standard may be obtained by contacting ASTM at the above address or at 610-832-9585 (phone), 610-832-9555 (fax), or service@astm.org (e-mail); or through the ASTM website (www.astm.org).