



Designation: E 822 – 92 (Reapproved 1996)

Standard Practice for Determining Resistance of Solar Collector Covers to Hail by Impact With Propelled Ice Balls¹

This standard is issued under the fixed designation E 822; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon (ϵ) indicates an editorial change since the last revision or reapproval.

1. Scope

1.1 This practice covers a procedure for determining the ability of cover plates for flat-plate solar collectors to withstand impact forces of falling hail. Propelled ice balls are used to simulate falling hailstones. This practice is not intended to apply to photovoltaic cells or arrays.

1.2 This practice defines two types of test specimens, describes methods for mounting specimens, specifies impact locations on each test specimen, provides an equation for determining the velocity of any size ice ball, provides a method for impacting the test specimens with ice balls, and specifies parameters that must be recorded and reported.

1.3 This practice does not establish pass or fail levels. The determination of acceptable or unacceptable levels of ice-ball impact resistance is beyond the scope of this practice.

1.4 The size of ice ball to be used in conducting this test is not specified in this practice. This practice can be used with various sizes of ice balls.

1.5 The categories of solar collector cover plate materials to which this practice may be applied cover the range of:

1.5.1 Brittle sheet, such as glass,

1.5.2 Semirigid sheet, such as plastic, and

1.5.3 Flexible membrane, such as plastic film.

1.6 Solar collector cover materials should be tested as:

1.6.1 Part of an assembled collector (Type 1 specimen), or

1.6.2 Mounted on a separate test frame cover plate holder (Type 2 specimen).

1.7 The values stated in SI units are to be regarded as the standard. The values given in parentheses are for information only.

1.8 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.*

2. Significance and Use

2.1 In many geographic areas there is concern about the effect of falling hail upon solar collector covers. This practice may be used to determine the ability of flat-plate solar collector covers to withstand the impact forces of hailstones. In this practice, the ability of a solar collector cover plate to withstand hail impact is related to its tested ability to withstand impact from ice balls. The effects of the impact on the material are highly variable and dependent upon the material.

2.2 This practice describes a standard procedure for mounting the test specimen, conducting the impact test, and reporting the effects.

2.2.1 The procedures for mounting cover plate materials and collectors are provided to ensure that they are tested in a configuration that relates to their use in a solar collector.

2.2.2 The corner locations of the four impacts are chosen to represent vulnerable sites on the cover plate. Impacts near corner supports are more critical than impacts elsewhere. Only a single impact is specified at each of the impact locations. For test control purposes, multiple impacts in a single location are not permitted because a subcritical impact may still cause damage that would alter the response to subsequent impacts.

2.2.3 Resultant velocity is used to simulate the velocity that may be reached by hail accompanied by wind. The resultant velocity used in this practice is determined by vector addition of a 20 m/s (45 mph) horizontal velocity to the vertical terminal velocity.

2.2.4 Ice balls are used in this practice to simulate hailstones because natural hailstones are not readily available to use, and ice balls closely approximate hailstones. However, no direct relationship has been established between the effect of impact of ice balls and hailstones. Hailstones are highly variable in properties such as shape, density, and frangibility.² These properties affect factors such as the kinetic energy delivered to the cover plate, the period during which energy is delivered, and the area over which the energy is distributed. Ice balls, with a density, frangibility, and terminal velocity near the range of hailstones, are the nearest hailstone approximation known at this time. Perhaps the major difference between ice balls and hailstones is that hailstones are much more variable than ice

¹ These test methods are under the jurisdiction of ASTM Committee E44 on Solar, Geothermal, and Other Alternative Energy Sources and is the direct responsibility of Subcommittee E44.05 on Solar Heating and Cooling Subsystems and Systems.

Current edition approved Sept. 15, 1992. Published June 1993. Originally published as E 822 – 81. Last previous edition E 822 – 81(1987).

² Gokhale, N. R., *Hailstorms and Hailstone Growth*, State University of New York Press, Albany, NY, 1975.

balls. However, ice balls can be uniformly and repeatedly manufactured to ensure a projectile with known properties.

2.2.5 A wide range of observable effects may be produced by impacting the various types of cover plate materials. The effects may vary from no effect to total destruction. Some changes in the cover material may be visible when there is no apparent functional impairment of the cover plate material. All effects of each impact must be described in the report so that an estimate of their significance can be made.

2.3 Data generated using this practice may be used: (1) to evaluate impact resistance of a single material or collector, (2) to compare the impact resistance of several materials or collectors, (3) to provide a common basis for selection of cover materials or collectors for use in various geographic areas, or (4) to evaluate changes in impact resistance due to environmental factors such as weather.

2.4 This practice does not state the size(s) of ice ball(s) to be used in making the impact. Either the person requesting the test or the person performing the test must determine ice ball size to be used in the testing. Choice of ice ball size may relate to the intent of the testing.

2.4.1 If the testing is being performed to evaluate impact resistance of a single material or collector, or several materials or collectors, it may be desirable to repeat the test using several sizes of ice balls. In this manner the different effects of various sizes of ice balls may be determined.

2.4.2 The size and frequency of hail varies significantly among various geographic areas. If testing is being performed to evaluate materials or collectors intended for use in a specific geographic area, the ice ball size should correspond to the level of hail impact resistance required for that area. Information on hail size and frequency may be available from local historical weather records or may be determined from the publications listed in Appendix X1.

2.5 The hail impact resistance of materials may change as the materials are exposed to various environmental factors. This practice may be used to generate data to evaluate degradation by comparison of hail impact resistance data measured before and after exposure to such aging.

3. Apparatus

3.1 *Launcher*—A mechanism capable of propelling a selected ice ball at the corresponding resultant velocity. The aiming accuracy of the launcher must be sufficient to propel the ice ball to strike the cover plate within 25 mm (± 1 in.) of the specified impact points. See Fig. 1.

NOTE 1—A launcher that has proven suitable uses a compressed air supply, an accumulator tank, a large-diameter quick-opening valve and interchangeable barrels to accommodate the sizes of ice balls to be used. Barrels should be made from materials with low thermal conductivity to reduce melting of the ice ball. Barrels should be sized such that the ice ball remains intact during loading and launching.

3.2 *Velocity Meter*, for measuring the ice ball velocity with an accuracy of ± 2.0 %.

3.3 *Test Base*—A structurally rigid support for mounting a complete solar collector panel (Type 1 specimen), or for mounting a solar collector cover plate material (Type 2 specimen) set in the cover holder.

3.4 *Cover Holder*—A rigid edging frame (see Fig. 1 and

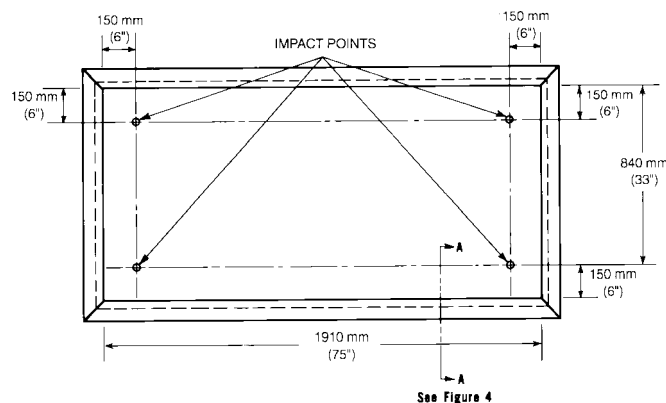


FIG. 1 Frame Dimensions and Location of Test Impact Points

Fig. 2) designed to hold an approximately 860 by 1930-mm (34 by 76-in.) cover plate.

NOTE 2—Hardwood, such as oak, birch, maple, or hickory, is mandatory if wood is used for the cover holder.

NOTE 3—Corner straps, as shown in Fig. 3 and Fig. 4, have been found useful to ensure the cover holder is rigid.

3.5 *Molds*, for casting spherical crack-free ice balls of appropriate diameter.

NOTE 4—Molds made from room-temperature vulcanizing rubber and expanded polystyrene have been found suitable.

3.6 *Freezer*—A device controlled at $-12 \pm 5^\circ\text{C}$ ($10 \pm 9^\circ\text{F}$) for making and storing ice balls.

4. Test Specimen

4.1 *Type 1*—The test specimen shall consist of a complete glazing assembly or a complete solar collector panel with necessary mounting brackets or fixtures.

4.2 *Type 2*—The test specimen shall consist of a section of solar collector cover plate material mounted in the cover holder.

5. Mounting

5.1 *Type 1*—Position and support the test specimen on a suitable test base using necessary mounting brackets or fixtures, or both. Do not obstruct the specified impact points by the mounting fixtures.

5.2 *Type 2*—Secure the test specimen in the cover holder, as shown in Fig. 2 and Fig. 5, and mount the cover holder (with the cover), on a suitable test base. Provide sufficient clearance


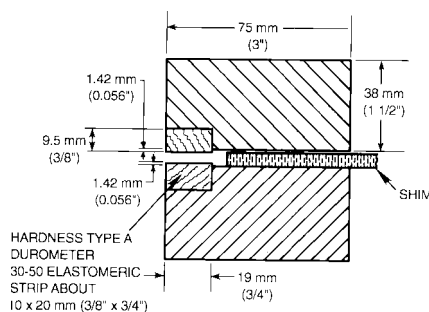


FIG. 2 Cover Holder, Empty (Section A-A of Fig. 1)

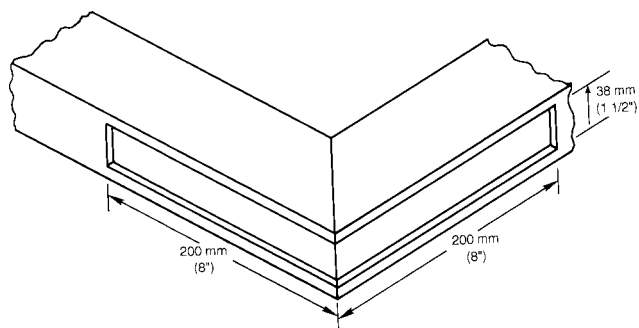

NOTE 1—Slot corner as indicated to fit steel corner straps. Straps should be flush with surface.

FIG. 3 Slots for Corner Straps of Cover Holder

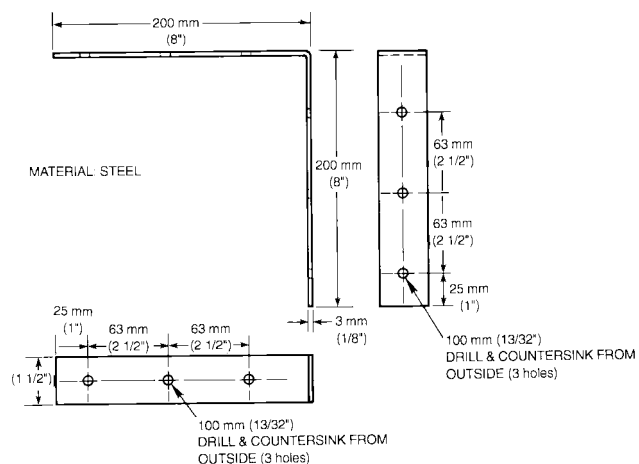


FIG. 4 Detail of Corner Straps for Cover Holder

on the side opposite the impact surface to permit unobstructed deflection of the cover material.

5.2.1 Lay brittle sheet cover materials, approximately 860 by 1930 mm (34 by 76 in.), on the elastomeric gasket (Type A durometer rating 30 to 50) of one member of the cover holder. Put the shim in place. Lay the other member of the cover holder on top. Tighten the bolts or C-clamp screws until the elastomeric gaskets are compressed and the shim is firmly held, as shown in Fig. 5. (Note 5). Mount the specimen firmly on the test base for testing.

NOTE 5—If the cover plate material will be damaged by the procedure specified herein, the bolts or C-clamp screws should be tightened sufficiently to hold the specimen in the frame, but not tightened to the extent that permanent deformations are made in the cover plate material.

5.2.2 Clamp semirigid sheet (plastic) cover materials in the cover holder in the same manner as brittle sheet cover materials.

5.2.3 Flexible Membrane:

5.2.3.1 Mount the material in accordance with the manufacturer's recommendations on a suitable rigid subframe approximately 860 by 1930 mm (34 by 76 in.). Mount the subframe in the cover holder in the same manner as described for brittle sheet in 5.2.1.

5.2.3.2 Alternatively, set flexible membrane cover materials in the holder and place under biaxial tension (normal to length and width).

NOTE 6—This may be accomplished by cutting the films oversize, notching the four corners to the dimensions of the holder frame, and draping the four flaps with suitable mass attached over the frame. The mass must be located to uniformly distribute the tension over the area of the film. Experience has shown that a 0.13-mm (0.005-in.) film requires a mass of approximately 9 kg/m (6 lb/linear foot) of perimeter. After tightening the clamps to prevent slippage during testing, the flaps and excess material may be trimmed away, and the clamped specimens mounted as described in 5.2.1.

6. Preconditioning

6.1 Precondition Type 1 test specimen or the test material for the Type 2 test specimen at $23 \pm 2^\circ\text{C}$ ($73.4 \pm 4^\circ\text{F}$) and $50 \pm 5\%$ relative humidity for not less than 24 h prior to testing.

7. Safety Considerations

7.1 The operation of the described equipment may expose the operator to risk of injury from the propelled or rebounded ice ball, fragments of the broken test specimen, and from the noise that may develop. Eye and ear protection should be considered as the minimum protection for the operator.

8. Procedure

8.1 Using the ice ball mold(s), make sufficient quantities of ice balls of the size(s) anticipated for testing.

8.2 Precondition the Type 1 test specimen or the material for the Type 2 test specimen as described in 6.1.

8.3 Determine the ice ball size to be used in the test.

NOTE 7—The size of the ice ball shall be determined by the sponsor of the test or the testing facility personnel.

8.4 Calculate the resultant velocity corresponding to the ice ball diameter. Determine the resultant velocity as follows:

$$V_r = \sqrt{V_t^2 + V_w^2} \quad (1)$$

where:

$V_w = 20 \text{ m/s}$ or 66 ft/s (45 mph), and
 $V_t = 14.04 \sqrt{d \text{ cm}}$ or $73.4 \sqrt{d \text{ in.}}$

where:

$V_r =$ resultant velocity of ice ball,
 $V_t =$ terminal velocity of ice ball,
 $V_w =$ wind velocity of 20 m/s (66 ft/s), and
 $d =$ ice ball diameter.

8.5 Mount the test specimen as described in Section 5.

8.6 Mark the four target impact points shown in Fig. 1 on the cover plate material. Each impact point is located in a corner 150 mm (6 in.) from both supporting edges.


NOTE 8—Care should be taken to ensure that the marking does not react with the cover material or influence test results.

8.7 Position the launcher as necessary to ensure that the path of the propelled ice ball at impact will be essentially perpendicular ($90 \pm 5^\circ$) to the surface of the cover plate material.

NOTE 9—The apparatus may be designed so that the path of the ice ball is horizontal or vertical, as long as the other requirements of the test are met.

NOTE 10—This practice may also be used to evaluate collector cover plates that are not flat. Due to the many configurations in nonflat cover plates, considerable judgment and knowledge of the particular configurations are necessary in applying this practice.

8.8 Aim the launcher at a target impact point (as shown in

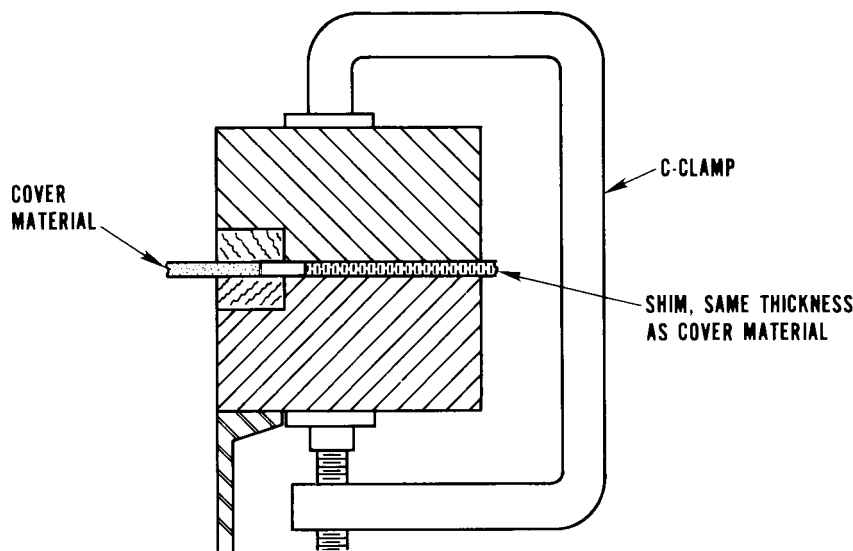

NOTE 1—Bolts may be used in place of C-clamps if the bolt does not penetrate the test specimen (that is, for rigid sheet).

FIG. 5 Cover Holder, Loaded

Fig. 1) not previously impacted. Impact each impact point one time only.

8.9 Position the velocity meter such that the ice ball velocity will be measured between the launcher and the test specimen. The ice ball should leave the velocity meter not more than 1.0 m (3.1 ft) in front of the impact location. Prepare the velocity meter for the test.

8.10 Remove from the freezer an ice ball of the size determined in 8.3. Inspect the ice ball to ensure it is uncracked, uniform, and spherical. Measure and record the nominal diameter and mass of the ice ball. Report the mass measurement to the nearest 0.1 g.

8.11 Place the ice ball in the launcher.

8.12 Set the launcher controls to ensure that the ball will be propelled at the velocity determined in 8.4.

8.13 **Caution:** Personnel protective equipment may be required during this operation, see 7.1. Launch the ice ball using its corresponding resultant velocity. Measure and record the velocity of the ice ball. Ice balls shall impact the test specimen within 60 s of removal from the freezer.

8.14 Inspect the ice ball impact location. If the actual impact location deviates more than 25 mm (1 in.) from the marked target impact point, do not use the target area again. If the results from such an impact are reported, also report the location of the impact.

8.15 Describe and record all observable effects of the impact, even though they may not impair the functionality of the cover plate material.

8.16 Repeat steps 8.7 to 8.15 until the test is complete. The test shall be considered complete when all four impact target points have been impacted once, or when total destruction of the cover plate material occurs before each target point has been impacted once.

8.17 Complete the test within 1 h of removal of the test specimen from preconditioning.

9. Report

9.1 The report shall include the following:

9.1.1 Any deviation from this practice.

9.1.2 Description of launcher and velocity meter.

9.1.3 For *Type 1 Test Specimens (complete collector panel)*:

9.1.3.1 Manufacturer and product designation,

9.1.3.2 Collector and glazing dimensions,

9.1.3.3 Type and thickness of glazing including manufacturer product designation, and

9.1.3.4 Procedure for mounting test specimen on test base.

9.1.4 For *Type 2 Test Specimens (cover plate material mounted in holder)*:

9.1.4.1 Type and thickness of glazing including manufacturer product designation, and

9.1.4.2 Procedure for mounting cover material in cover holder and cover holder on test base.

9.1.5 Documentation of the nominal diameter, weight, and velocity of each ice ball.

9.1.6 For nonflat cover materials, a description of the geometry of the material at each impact location.

9.1.7 Description of all observable effects of each impact, even though there may be no apparent functional impairment of the cover plate material.

10. Keywords

10.1 hail; ice balls; impact; impact resistance; solar collector



E 822

APPENDIX

(Nonmandatory Information)

X1. HAIL SIZE AND FREQUENCY DATA

X1.1 The size and frequency of hail varies significantly among various geographic areas. Information on hail size and frequency may be available from local historical weather

records, or it may be determined from the publications listed below.

REFERENCES

- (1) Beckwith, W. B., "Characteristics of Denver Hailstorms," *Bulletin of the American Meteorological Society*, Vol 38, No. 1, January 1957, p. 20.
- (2) Carte, A. E., "Areal Hail Frequency," *Journal of Applied Meteorology*, Vol 6, April 1967, pp. 336-338.
- (3) Cox, M., and Armstrong, P. R., "A Statistical Model for Assessing The Risk of Hail Damage To Any Ground Installation," *Technical Report For U.S. Department of Energy*, Contract EM-78-C-04-4291, September 1979.
- (4) Flora, S. D., *Hailstorms of the United States*, University of Oklahoma Press, Norman, OK, 1956.
- (5) Changnon, S. A., Jr., "Note on Hailstone Size Distributions," *Journal of Applied Meteorology*, April 1970, pp. 168-170.
- (6) Changnon, S. A., Jr., and Towery, N. G., "Studies of Hail Data in 1970-1972," Final Report of Grant entitled, "Study of Hailfall Data from a Hail and Rain Network," Illinois State Water Survey, December 1972.
- (7) Douglas, R. H., "Hail Size Distribution," *Proceedings of the World Conference on Radio Meteorology*, American Meteorological Society, Boston, pp. 146-149.
- (8) Gonzales, C., "Environmental Hail Model for Assessing Risk to Solar Collectors," *Jet Propulsion Laboratory Report 5101-45*, California Institute of Technology, Pasadena, CA, 1977.
- (9) Greenfeld, S. H., "Hail Resistance of Roofing Products," *Building Science Series*, Vol 23, National Bureau of Standards, 1969.
- (10) Gokhale, N. R., *Hailstorms and Hailstone Growth*, State University of New York Press, Albany, NY, 1975.
- (11) Gringorten, I. I., "Hailstone Extremes for Design," U.S. Air Force, ARCRL-No. 72-0081, December 25, 1971.
- (12) Mathey, R. G., "Hail Resistance Tests of Aluminum Skin Honeycomb Panels for the Relocatable Lewis Building, Phase II," *National Bureau of Standards Report No. 10193*, National Bureau of Standards, April 1970.
- (13) Schleusener, R. A., Marwitz, J. D., and Cox, W. L., "Hailfall Data from a Fixed Network for the Evaluation of a Hail Modification Experiment," *Journal of Applied Meteorology*, Vol 4, February 1965, pp. 61-68.
- (14) Smith, M. L., "Hail Testing of Solar Reflector Panels," presented at the Solar Reflector Materials Technology Workshop, Denver, CO, March 1978.
- (15) Stout, G. E., and Changnon, Jr., S. A., "Climatology of Hail in the Central United States," *Crop Hail Insurance Actuarial Association Report No. 38*, February 1968.
- (16) Thom, H. C. S., "The Frequency of Hail Occurrence," Advisory Committee on Weather Control, *Technical Report No. 3*, 1957.
- (17) "Intermediate Minimum Property Standards Supplement—Solar Heating and Domestic Hot Water Systems," No. 4930.2, U.S. Department of Housing and Urban Development, 1977 Ed.
- (18) Interim Performance Criteria for Solar Heating and Cooling Systems in Commercial Buildings, NBSIR No. 76-1187, National Bureau of Standards, November 1976.
- (19) Interim Performance Criteria for Solar Heating and Cooling Systems in Residential Buildings, NBSIR No. 78-1562, National Bureau of Standards, November 1978.

ASTM International takes no position respecting the validity of any patent rights asserted in connection with any item mentioned in this standard. Users of this standard are expressly advised that determination of the validity of any such patent rights, and the risk of infringement of such rights, are entirely their own responsibility.

This standard is subject to revision at any time by the responsible technical committee and must be reviewed every five years and if not revised, either reapproved or withdrawn. Your comments are invited either for revision of this standard or for additional standards and should be addressed to ASTM International Headquarters. Your comments will receive careful consideration at a meeting of the responsible technical committee, which you may attend. If you feel that your comments have not received a fair hearing you should make your views known to the ASTM Committee on Standards, at the address shown below.

This standard is copyrighted by ASTM International, 100 Barr Harbor Drive, PO Box C700, West Conshohocken, PA 19428-2959, United States. Individual reprints (single or multiple copies) of this standard may be obtained by contacting ASTM at the above address or at 610-832-9585 (phone), 610-832-9555 (fax), or service@astm.org (e-mail); or through the ASTM website (www.astm.org).