



Standard Test Method for Sonic Velocity in Refractory Materials at Room Temperature and Its Use in Obtaining an Approximate Young's Modulus¹

This standard is issued under the fixed designation C 1419; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon (ϵ) indicates an editorial change since the last revision or reapproval.

1. Scope

1.1 This test method describes a procedure for measuring the sonic velocity in refractory materials at room temperature. The sonic velocity can be used to obtain an approximate value for Young's modulus.

1.2 The sonic velocity may be measured through the length, thickness, and width of the specimen.

1.3 *This standard does not purport to address the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.*

2. Referenced Documents

2.1 ASTM Standards:

C 134 Test Methods for Size, Dimensional Measurements, and Bulk Density of Refractory Brick and Insulating Firebrick²

C 179 Test Method for Drying and Firing Linear Change of Refractory Plastic and Ramming Mix Specimens²

C 769 Test Method for Sonic Velocity in Manufactured Carbon and Graphite Materials for Use in Obtaining an Approximate Young's Modulus²

C 885 Test Method for Young's Modulus of Refractory Shapes by Sonic Resonance²

E 177 Practice for Use of the Terms Precision and Bias in ASTM Test Methods³

E 380 Practice for Use of the International System of Units (SI) (the Modernized Metric System)³

E 691 Practice for Conducting an Interlaboratory Study to Determine the Precision of a Test Method³

3. Terminology

3.1 Definitions of Terms Specific to This Standard:

3.1.1 *longitudinal sonic pulse, n*—a sonic pulse in which the displacements are in the direction of propagation of the pulse.

3.1.2 *pulse travel time, (T_t), n*—the total time, measured in microseconds, required for the sonic pulse to traverse the

specimen being tested, and for the associated electronic signals to traverse the circuits of the pulse propagation circuitry.

3.1.3 *zero time, (T_o), n*—the travel time (correction factor), measured in microseconds, associated with the electronic circuits in the pulse-propagation system.

4. Summary of Test Method

4.1 The velocity of sound waves passing through the test specimen is determined by measuring the distance through the specimen and dividing by the time lapse between the transmitted pulse and the received pulse.^{4,5} An approximate value for Young's modulus can be obtained as follows:

$$E = \rho v^2 \quad (1)$$

where:

E = Young's modulus of elasticity, Pa,

ρ = density, kg/m³, and

v = signal velocity, m/s.

4.2 Strictly speaking, the elastic constant given by this measurement is not E but C_{33} , provided the sonic pulse is longitudinal and the direction of propagation is along the axis of symmetry.^{4,5}

5. Significance and Use

5.1 This test method is used to determine the sonic velocity and approximate Young's modulus of refractory shapes at room temperature. Since this test is nondestructive, specimens may be used for other tests as desired.

5.2 This test method is useful for research and development, engineering application and design, manufacturing quality and process control, and for developing purchasing specifications.

6. Apparatus

6.1 *Driving Circuit*, which consists of an ultra sonic pulse generator capable of producing pulses in a frequency range from 0.5 to 2.5 MHz.

6.2 *Transducer*, input.

6.3 *Transducer*, output.

6.4 *Oscilloscope*, dual trace with a preamplifier and time delay circuitry.

¹ This test method is under the jurisdiction of ASTM Committee C-8 on Refractories and is the direct responsibility of Subcommittee C08.01 on Strength. Current edition approved Oct. 10, 1999. Published November 1999. Originally published as C 1419 – 99. Last previous edition C 1419 – 99.

² *Annual Book of ASTM Standards*, Vol 15.01.

³ *Annual Book of ASTM Standards*, Vol 14.02.

⁴ Schreiber, Anderson, and Soga, "Elastic Constants and Their Measurement," McGraw-Hill Book Co., 1221 Avenue of the Americas, New York, NY 10020, 1973.

⁵ *American Institute of Physics Handbook*, 3rd ed., McGraw-Hill Book Co., 1221 Avenue of the Americas, New York, NY 10020, 1972, pp. 3–98ff.

6.5 See Fig. 1 for a typical set-up.

7. Test Specimen

7.1 Specimens may be prisms of any desired length with parallel smooth surfaces. Opposite surfaces across the length, width, and thickness shall be parallel. The smallest dimension shall be greater than 5 times the diameter of the largest aggregate in the refractory. The surface on which the transducers will be located must have a width of at least 1.5 times the diameter of the transducer being used.

7.2 Dry the specimens in an oven at 110°C (230°F) for a minimum of 5 h. Cool to room temperature. Test for sonic velocity within 5 h of drying.

7.3 *Measurement of Density and Dimensions*—Calculate the density of the specimens by Test Methods C 134 and determine the specimen lengths by either Test Methods C 134 or C 179.

8. Procedure

8.1 Assemble and connect the apparatus as shown in Fig. 1 and refer to the equipment manufacturer’s instructions for hook

up precautions. If using commercially available equipment designed to measure sonic velocity, refer to the manufacturer’s set-up and operating instructions.⁶ Allow adequate time for the test apparatus to warm up and stabilize.

8.2 Provide a suitable coupling medium on the transducer faces.

NOTE 1—Petroleum jelly or grease couple well but may be difficult to remove for subsequent tests on the same specimen.

8.3 Position the transducers on opposite surfaces so that they provide a mirror image and that the distance between the input transducer and the output transducer is minimal and equals the dimension through which the measurement is performed.

8.4 Bring the transducer faces into intimate contact, but do not exceed the manufacturer’s recommended contact pressure.

8.5 Determine T_o , the zero time (zero correction) measured in microseconds, associated with the electronic circuits in the pulse propagation instrument and coupling. Alternately, if a commercially available apparatus is used, which utilizes a zero offset and a supplied calibration standard, the instrument can be zeroed using the standard and T_o does not have to be determined or used in the final calculation.

8.6 Measure and weigh and calculate the density of the test specimen as in 7.3.

8.7 Lightly coat the faces of the test specimen that will be in contact with the transducers with the coupling medium. Place the transducers against the test specimen. Apply firm pressure until the pulse travel time stabilizes.

8.8 Determine T_p , the pulse travel time from the oscilloscope traces as illustrated in Fig. 2, or, if the instrument used has a zero correction, T_c , the corrected travel time.

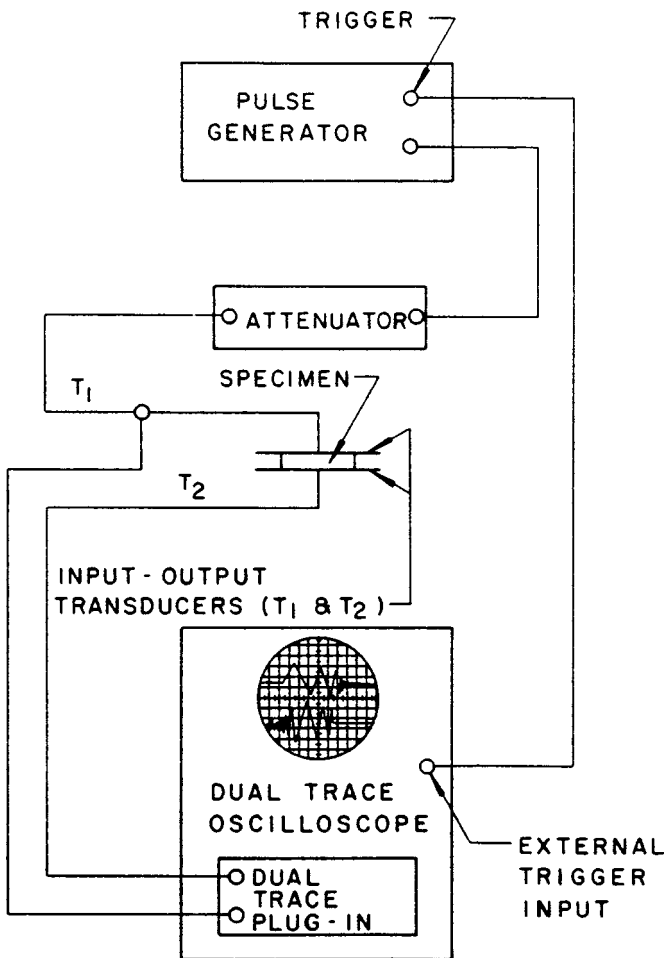


FIG. 1 Equipment Set-up

⁶ Equipment found suitable for use is available from James Instruments Inc., 3727 N. Kedzie Avenue, Chicago, IL 60618.

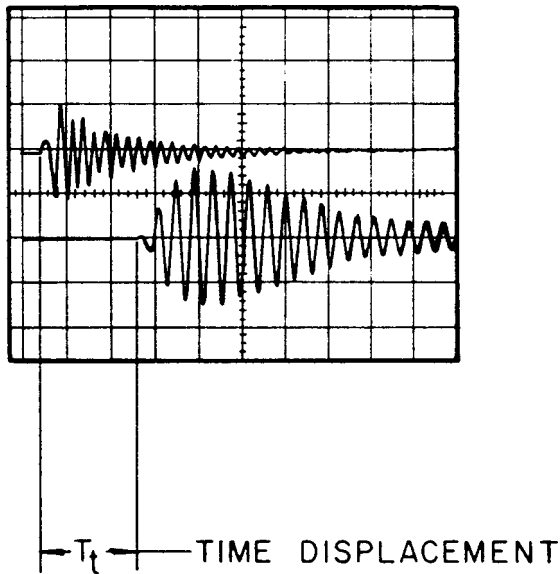


FIG. 2 Typical Oscilloscope Display

9. Calculation

9.1 Velocity of Signal:

$$v = \frac{L}{T_t - T_o} \tag{2}$$

or

$$v = \frac{L}{T_c} \tag{3}$$

where:

- v = velocity of signal, m/s,
- L = distance between the two transducers, the dimension through which the measurement is performed, m,
- T_t = pulse travel time, s,
- T_o = zero times, s, and
- T_c = corrected travel time ($T_t - T_o$), s.

9.2 An appropriate value for Young’s modulus of the specimen can be obtained using the following equation:

$$E = \rho v^2 \tag{4}$$

where:

- E = Young’s modulus of elasticity, Pa (approximate),
- ρ = density, kg/m³, and
- v = signal velocity, m/s.

9.3 Conversion Factors—See Practice E 380.

10. Report

10.1 Report the following information:

- 10.1.1 Specimen dimensions and weight.
- 10.1.2 Sonic velocity for each specimen.
- 10.1.3 Density for each specimen, if calculated.
- 10.1.4 Young’s modulus for each specimen, if calculated.
- 10.1.5 It is recommended that the average and standard deviation values be included for each group of specimens.
- 10.1.6 Frequency of the transducers used and sonic velocity

TABLE 1 Precision Statistics for Sonic Velocity

Material	Average (m/s)	Std. Dev. Within Labs, S_r	Std. Dev. Between Labs, S_R	Repeatability Limit, r	Reproducibility Limit, R
Plexiglas	2731.3	1.19	28.97	3.37	81.93
A-1148	9223.3	18.29	182.59	51.73	516.36
B-301	2511.6	6.96	43.49	19.68	122.98
SR-90	3911	19.5	81.26	55.15	229.8
SR-99	4697.5	9.35	81.12	26.45	229.44
ZRX	5789.8	39.99	126.94	113.09	358.99

TABLE 2 Precision Statistics for Approximate Young’s Modulus

Material	Average (MPa)	Std. Dev. Within Labs, S_r	Std. Dev. Between Labs, S_R	Repeatability Limit, r	Reproducibility Limit, R
Plexiglas	8970	8.42	191	23.8	541
A-1148	293000	1190	11500	3370	32600
B-301	9380	52	317	147	896
SR-90	43400	434	1590	1230	4500
SR-99	67900	829	2180	2340	6170
ZRX	90400	1270	4370	3590	12300

equipment identification.

10.1.7 Method of coupling the transducers to the specimen.

10.1.8 As available a complete identification of the material being tested including manufacturer, brand, lot number, firing history, and specimen sampling plan.

11. Precision and Bias

11.1 Interlaboratory Test Data—An interlaboratory study was completed among nine laboratories in 1996. A standard set of samples consisting of five different refractory materials and a Plexiglas prism were circulated and tested by each laboratory.⁷ The samples tested were Plexiglas, two high alumina brick (SR-90 and SR-99), an alumina insulating brick (B-301), an isopressed alumina shape (A-1148), and a zircon brick (ZRX). The dimensions of all samples were approximately 228 mm × 114 mm × 75 mm (9 in. × 4.5 in. × 3 in.). Each laboratory measured and weighed each sample and tested each for signal travel time. Each time was the average of three test determinations.


11.2 Precision—Tables 1 and 2 contain the precision statistics for the sonic velocity and approximate Young’s modulus results, respectively. The terms repeatability limit and reproducibility limit are used as specified in Practice E 177.

11.3 Bias—No justifiable statement can be made on the bias of the test method for measuring the sonic velocity and approximate Young’s modulus of refractories because the value of the sonic velocity and approximate Young’s modulus can be defined only in terms of the test method.

12. Keywords

12.1 modulus of elasticity; refractories; sonic velocity; Young’s modulus

⁷ Since these samples were not destroyed in testing, they are being retained in custody by C08.01 for future reference and test development.

 **C 1419**

The American Society for Testing and Materials takes no position respecting the validity of any patent rights asserted in connection with any item mentioned in this standard. Users of this standard are expressly advised that determination of the validity of any such patent rights, and the risk of infringement of such rights, are entirely their own responsibility.

This standard is subject to revision at any time by the responsible technical committee and must be reviewed every five years and if not revised, either reapproved or withdrawn. Your comments are invited either for revision of this standard or for additional standards and should be addressed to ASTM Headquarters. Your comments will receive careful consideration at a meeting of the responsible technical committee, which you may attend. If you feel that your comments have not received a fair hearing you should make your views known to the ASTM Committee on Standards, 100 Barr Harbor Drive, West Conshohocken, PA 19428.

This standard is copyrighted by ASTM, 100 Barr Harbor Drive, West Conshohocken, PA 19428-2959, United States. Individual reprints (single or multiple copies) of this standard may be obtained by contacting ASTM at the above address or at 610-832-9585 (phone), 610-832-9555 (fax), or service@astm.org (e-mail); or through the ASTM website (<http://www.astm.org>).